



# Quaternary ammonium-based biomedical materials: State-of-the-art, toxicological aspects and antimicrobial resistance



Yang Jiao<sup>a,b,1</sup>, Li-na Niu<sup>a,1</sup>, Sai Ma<sup>a</sup>, Jing Li<sup>c</sup>, Franklin R. Tay<sup>d,\*</sup>, Ji-hua Chen<sup>a,\*</sup>

<sup>a</sup> State Key Laboratory of Military Stomatology & National Clinical Research Center for Oral Diseases & Shaanxi Key Laboratory of Oral Diseases, Department of Prosthodontics, School of Stomatology, The Fourth Military Medical University, 710032, Xi'an, Shaanxi, China

<sup>b</sup> Department of Stomatology, PLA Army General Hospital, 100700, Beijing, China

<sup>c</sup> Department of Orthopaedic Oncology, Xijing Hospital Affiliated to the Fourth Military Medical University, 710032, Xi'an, Shaanxi, China

<sup>d</sup> Department of Endodontics, The Dental College of Georgia, Augusta University, Augusta, GA, 30912, USA

## ARTICLE INFO

### Article history:

Received 18 August 2016

Received in revised form 7 March 2017

Accepted 7 March 2017

Available online 12 March 2017

### Keywords:

Quaternary ammonium compounds

Antimicrobial surfaces

Toxicological aspects

Antimicrobial resistance

## ABSTRACT

Microbial infections affect humans worldwide. Many quaternary ammonium compounds have been synthesized that are not only antibacterial, but also possess antifungal, antiviral and anti-matrix metalloproteinase capabilities. Incorporation of quaternary ammonium moieties into polymers represents one of the most promising strategies for preparation of antimicrobial biomaterials. Various polymerization techniques have been employed to prepare antimicrobial surfaces with quaternary ammonium functionalities; in particular, syntheses involving controlled radical polymerization techniques enable precise control over macromolecular structure, order and functionality. Although recent publications report exciting advances in the biomedical field, some of these technological developments have also been accompanied by potential toxicological and antimicrobial resistance challenges. Recent evidenced-based data on the biomedical applications of antimicrobial quaternary ammonium-containing biomaterials that are based on randomized human clinical trials, the golden standard in contemporary medicinal science, are included in the present review. This should help increase visibility, stimulate debates and spur conversations within a wider scientific community on the implications and plausibility for future developments of quaternary ammonium-based antimicrobial biomaterials.

Published by Elsevier B.V.

## Contents

1. Introduction.....	55
2. Bioactive functions of QACs.....	56
2.1. Antibacterial activities.....	56
2.2. Antifungal activities.....	60
2.3. Antiviral activities.....	61
2.4. Anti-MMP activities.....	61
3. QA-based antimicrobial surfaces.....	62
3.1. "Grafting onto" vs "grafting from" approaches.....	62
3.2. Controlled radical polymerization.....	63
3.3. Ring-opening polymerization.....	63
3.4. Click chemistry.....	64
4. Orthopedics-related materials.....	67
5. Sutures and wound dressings.....	74
6. Dental materials.....	75

\* Corresponding authors.

E-mail addresses: [ftay@augusta.edu](mailto:ftay@augusta.edu) (F.R. Tay), [jhchen@fmmu.edu.cn](mailto:jhchen@fmmu.edu.cn) (J.-h. Chen).

<sup>1</sup> Equal contributors.

7. Toxicological aspects of QACs .....	78
8. QACs and antimicrobial resistance .....	81
9. Concluding remarks and future perspectives .....	81
Acknowledgements .....	82
Appendix A. Supplementary data .....	82
References .....	82

## Nomenclature

AAM	Acrylamide
AME	Antimicrobial enzyme
AMP	Antimicrobial peptide
ATRP	Atom transfer radical polymerization
BPEA	2-(2-Bromopropionate)-ethyl acrylate
CCR5	C–C chemokine receptor type 5
CRP	Controlled radical polymerization
CTA	Chain transfer agent
CuAAC	Cu-catalyzed azide–alkyne cycloaddition
DADMAC	Diallyl-dimethylammonium chloride
DBCO	Dibenzocyclooctynes
DCAMA	Dipicolyl aminoethyl methacrylate
DDMAI	2-Dimethyl-2-dodecyl-1-methacrylammonium iodine
DEPN	<i>N</i> - <i>tert</i> -butyl- <i>N</i> -(1-diethylphosphonodimethylpropyl)] (2,2-
DMADDM	Dimethylaminododecyl methacrylate
DMAEDM	Dimethylammoniummethyl dimethacrylate
DMAEMA	2-Dimethylamino ethyl methacrylate
DMAE-CB	Methacryloxyethyl cetyl ammonium chloride
DMAHDM	Dimethylaminohexadecyl methacrylate
DODAB	Diocetadecyldimethyl-ammonium bromide
EA	Ethyl acrylate
EDAX	Energy dispersive X-ray
EPsiQA	Epoxy silicone quaternary ammonium salt
EPS	Exopolysaccharides
FAc	Fluorinated acrylate-heptadecafluorodecyl acrylate
FE-SEM	Field emission scanning electron microscopy
FRP	Free radical polymerization
GIC	Glass ionomer cement
gtf	Glucosyltransferase
GTAC	Glycidyltrialkylammoniumchloride
GTMAC	Glycidyltrimethylammonium chloride
GTEACI	Glycidyltriethylammonium chloride
HACC	Hydroxypropyltrimethyl ammonium chloride chitosan
HDPC	Human dental pulp cell
HEMA	2-Hydroxyethyl methacrylate
HGF	Human gingival fibroblast
HSV	Herpes simplex virus
IC <sub>50</sub>	Half maximal inhibitory concentration
IDMA	Ionic dimethacrylate
IMQ	<i>N,N</i> -bis[2-(3-(Methacryloyloxy) propanamido)ethyl]- <i>N</i> -methylhexadecyl ammonium bromide
LCST	Lower critical solution temperature
LC <sub>50</sub>	Lethal concentration that kills 50% of a sample
MAE-DB	2-Methacryloxyethyl dodecyl methyl ammonium bromide
MBC	Minimum bactericidal concentration
MDPB	12-Methacryloyloxy dodecyl pyridinium bromide

MFC	Minimum fungicidal concentrations
MIC	Minimum inhibitory concentration
MMA	Methyl methacrylate
MMP	Matrix metalloproteinase
Monomer	II <i>N</i> -Benzyl-11-(methacryloyloxy)- <i>N,N</i> -dimethylundecan-1-aminium fluoride
MRSA	Methicillin-resistant <i>Staphylococcus aureus</i>
MRSE	Methicillin-resistant <i>Staphylococcus epidermidis</i>
MTT	3-(4,5-Dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide
MUPB	Methacryloyloxyundecylpyridinium bromide
NACP	Nanoparticles of amorphous calcium phosphate
NIPAAm	<i>N</i> -Isopropylacrylamide
NM	Not mentioned
NMR	Nuclear magnetic resonance
NMP	Nitroxide-mediated polymerization
NO	Nitric oxide
NP	Nanoparticle
Nrf2	Nuclear factor E2-related factor 2
P(AA-co-Ada)	Poly(acrylic acid-co-1-adamantan-1-ylmethyl acrylate)
PAMAM	Poly amidoamine
PAH	Poly(allylamine hydrochloride)
PB	Poly(1-butene)
PCL-PJDMA	Poly caprolactone-poly quaternary ammonium salt
pDADMAC-PU	Poly diallyl-dimethylammonium chloride-polyurethane
PDMS	Poly(dimethylsiloxane)
PEG	Polyethylene glycol
PMMA	Poly(methyl methacrylate)
PTEA	2-Phenyl-2-(2,2,6,6-tetramethylpiperidin-1-yloxy)ethyl acrylate
PU	Polyurethane
QA	Quaternary ammonium
QAB	Quaternary ammonium bromide
QAC	Quaternary ammonium compound
QADM	Quaternary ammonium dimethacrylate
QADMA	Quaternary amine dimethacrylate
QADMAI-12	<i>N,N</i> -bis[2-(3-(Methacryloyloxy)propanamido)ethyl]- <i>N</i> -methyl dodecyl ammonium iodide
QADMAI-16	<i>N,N</i> -bis[2-(3-(Methacryloyloxy)propanamido)ethyl]- <i>N</i> -methylhexadecyl ammonium iodide
QADMAI-18	<i>N,N</i> -bis[2-(3-(methacryloyloxy)propanamido)ethyl]- <i>N</i> -methyloctadecyl ammonium iodide
QAES	Quaternary ammonium epoxy silicate
QAMA	Quaternized ethylene glycol dimethacrylate piperazine octyl ammonium iodide

QASM	Quaternary ammonium salt containing monomers
QCS	Quaternary ammonium chitosan derivative
QPEI	Quaternary ammonium polyethylenimine
QPGMA	Quaternized poly glycidyl methacrylate
RAFT	Reversible addition fragmentation chain transfer
ROS	Reactive oxygen species
RCT	Randomized controlled trial
ROP	Ring opening polymerization
SEM	Scanning electron microscopy
SIP	Surface-initiated polymerization
SNP	Single nucleotide polymorphism
SPAAC	Strain-promoted cycloaddition of alkynes and azide
SPH	5,5-Dimethyl-3-(3'-triethoxysilyl-propyl)hydantoin
SPMA	3-sulfopropylmethacrylate
SPODA	3-(Trimethoxysilylpropyl) octadecyl dimethyl ammonium chloride
TBAEMA	2- <i>tert</i> -Butylamino ethyl methacrylate
TEM	Transmission electron microscopy
Ti	Titanium
TGA	Thermogravimetric analysis
TMSPMA	Poly(3-(trimethoxysilyl)propyl methacrylate)
TPGDA	Tripropylene glycol diacrylate
XPS	X-ray photoelectron spectroscopy
XRD	X-ray diffraction
Zn	Zinc
2AE	[2-(Acryloyloxy)ethyl]trimethyl- ammonium chloride
4VP	4-Vinylpyridine
8QA	8-Quinolinylnyl acrylate

## 1. Introduction

Microbial infection is a major challenge to human health worldwide. Pathogenic microorganisms, including bacteria, viruses and fungi, are of special concern in hospitals and other health care settings, and adversely affect the optimal functioning of medical devices, drugs, surgical equipment, dental restorations and bone cements [1]. According to a systematic analysis, infectious diseases result in 9.2 million deaths in 2013 alone (about 17% of all deaths), most of which are associated with biofilm formation [2,3]. The discovery that microorganisms cause infectious diseases resulted in development of antibiotics, disinfectants and antiseptics against those microbial pathogens [4,5]. However, the widespread and indiscriminate use of antibiotics and disinfectants has resulted in the emergence of antibiotic-resistant bacterial strains that are becoming a serious threat to human health [6]. There has been a constant race between researchers developing new antimicrobial agents and bacteria acquiring resistance to those agents. According to the U.S. Center for Disease Control and Prevention, more than two million people are infected with antibiotic-resistant bacteria and at least 23,000 patients die annually from those infections [7]. The World Health Organization 2014 report on global surveillance of antimicrobial resistance surmised that the world is heading towards a post-antibiotic era in which what used to be common, treatable infections are rapidly becoming life-threatening diseases. The organization has appealed to researchers worldwide to prioritize their efforts toward concerted efforts in combating the spread of antimicrobial-resistant microorganisms [8]. Over the past decade, new strains of infectious pathogens, such as severe acute respiratory syndrome, antibiotic-resistant tuberculosis, avian influenza A (e.g. H5N1, H7N9), the Ebola and Zika viruses have emerged. These new life-threatening pathogens have the tendency to spread

globally instead of being confined to their niches of origin. Pragmatically, there is increasing need for exploring more efficient, broad-spectrum and long-lasting antimicrobial agents for biomedical applications.

To circumvent the uneven release kinetics and reservoir exhaustion issues of release-based antimicrobial biomaterials, contact-killing surfaces incorporating immobilized bactericides have been developed in which monomeric antimicrobial agents are covalently attached to the polymer backbone [9]. Compared with release-based biomaterials, the contact-killing approach have distinct advantages, in that they: (1) improve and prolong antimicrobial activities; (2) possess non-toxic and non-irritant properties without affecting the interaction with host tissues or modifying the host immune responses; (3); exert no adverse effects on the physical and mechanical properties of the loading materials; (4) are different from antibiotics in that their mode of action involves physically puncturing and destroying bacterial cell walls and membranes as well as viral envelopes [10]; and (5) are unlikely to develop antibiotic resistance [11]. The most commonly used antimicrobial compounds include quaternary ammonium compounds (QACs), chitosan, silver nanoparticles (AgNPs), antimicrobial peptides (AMPs) and antimicrobial enzymes (AMEs) (Table 1).

The use of QACs as antiseptics and disinfectants dated back to the 1930s [23]. The QACs employed in that era provided the first line of defense against pathogenic bacteria [24]. Structurally, QACs are composed of nitrogen (N<sup>+</sup>)-containing compounds in which the N atom is attached to four different groups by covalent bonds. The representative formula is N<sup>+</sup>R<sub>1</sub>R<sub>2</sub>R<sub>3</sub>R<sub>4</sub>X<sup>-</sup>, where R may be a hydrogen atom, a plain alkyl group or an alkyl group substituted with other functionalities, and X represents an anion, which is most often a halide anion. Most QAC salts are composed predominantly of chloride or bromide salts, while iodide salts tend to exhibit decreased solubility. Synthetic polymers with quaternary ammonium (QA) functionalities are produced using two general approaches: (1) quaternization of reactive precursor polymers (post-polymerization). This method generally generates products with variable degrees of cationization as a result of the unpredictable impact of steric hindrance from neighboring groups, and (2) direct copolymerization of monomers containing QA functional

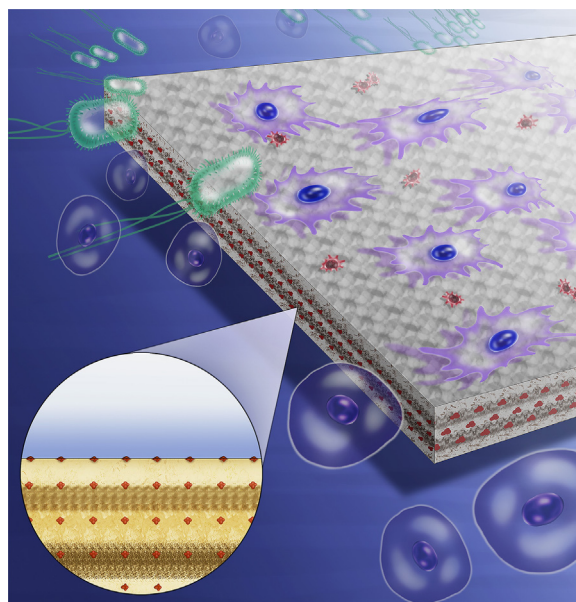


Fig. 1. Schematic illustration of the use of quaternary ammonium compounds in antimicrobial biomedical materials.

**Table 1**  
Major antibacterial materials and their mechanisms of action.

Material type	Representative compounds	Mechanisms of action	Refs.
Antibiotics	Aminoglycosides (e.g. gentamicin, tobramycin)	Bind to the bacterial 30S ribosomal subunit and inhibit protein synthesis	[12]
	Glycopeptides (e.g. vancomycin)	Bind to amino acids and disrupt cell wall peptidoglycan synthesis	
	Penicillins (e.g. ampicillin)	Inhibit related enzymes and disrupt cell wall peptidoglycan synthesis	
	Quinolones (e.g. ciprofloxacin, norfloxacin)	Inhibit DNA replication and transcription, targeting DNA topoisomerases II and IV	
	Rifamycins (e.g. rifampin)	Bind to RNA polymerase and inhibit transcription	
Antimicrobial enzymes (AMEs)	Tetracyclines (e.g. minocycline, tetracycline)	Inhibit protein synthesis	[13]
	Lysozyme	Catalyze glycosidic bond hydrolysis in bacterial cell wall peptidoglycans	
Antimicrobial peptides (AMPs)	Acylase	Quorum-quenching	[14,15]
	Natural AMPs (e.g. human $\beta$ -defensin 1–3, magainin and nisin) Synthetic AMPs (e.g. $\beta$ -17, human neutrophil peptides 1 and 2, histatins 5 and 8)	Transmembrane pore formation, intracellular targeting and metabolic inhibition mechanisms (inhibition of microbial functional proteins, DNA and RNA synthesis)	
Cationic compounds	Chitosan	Interaction between positively charged chitosan molecules and negatively charged bacterial cell membranes leads to disruption of cell membrane	[16]
	Chlorhexidine	Bind to negatively charged bacterial walls and disrupt cell walls	
	Poly( $\epsilon$ -lysine)	Electrostatic adsorption onto bacterial cell membranes and stripping of the outer membrane lead to cell death	
	Quaternary ammonium compounds (QACs)	Disruption of bacterial enzymes and cell membranes by positively charged polymers	
		Induce oxidative stresses, deactivate bacterial enzymes by binding to thiol groups and affect the function and permeability of the cell membranes	
Metal and metal oxides	AgNPs	Contribute to ROS formation and induce lipid peroxidation in bacterial membranes	[17,18]
	CuNPs	Photocatalytically activate the production of ROS and interfere with phosphorylation, thereby causing oxidative cell death	
	TiO <sub>2</sub> NPs	Generate ROS and binds to lipids and proteins, thus changing the osmotic balance and increasing membrane permeability	
	ZnONPs	Induce cellular nitrosative and oxidative stresses and act as a bacterial signaling disruptor	
Other non-cationic compounds	Nitric oxide (NO) donors	Induce cellular nitrosative and oxidative stresses and act as a bacterial signaling disruptor	[19,20]
	Triclosan	Deactivate bacterial fatty acid biosynthesis through inhibition of the enoylacyl carrier protein reductase enzyme	[21,22]

groups, coined as QA monomers, within the polymer network. These methods generate polymers with 100% functionality but with difficult molecular characterization (Fig. 1).

There are already excellent reviews that summarize the synthesis of antimicrobial polymers and their chemical structures [16,25–28]. Hence, the present review is targeted toward providing an overview of the state-of-the-art of QACs and their antimicrobial applications in the biomedical field (Fig. 2), and describing the currently-accepted mechanisms on how antibacterial, antifungal, antiviral and the recently discovered anti-matrix metalloproteinase (MMP) activities of QACs are achieved. The use of controlled radical polymerization (CRP) techniques, in particular, has provided a major thrust in the synthesis of novel QA-based antimicrobial surfaces. Because of increasing concerns over the biocompatibility of QACs, a critique on the toxicological aspects of QACs is also included. Similar to antimicrobial peptides, QACs are potential candidates for combating antibiotic resistance. Thus, the potential impact of QACs on the emergence of antibiotic resistance is also discussed. Apart from reviewing bench-top work and animal studies, recent evidenced-based data on the biomedical applications of antimicrobial QA-containing copolymers based on

randomized human clinical trials will also be highlighted in the present review.

## 2. Bioactive functions of QACs

### 2.1. Antibacterial activities

Quaternary ammonium compounds are cationic surfactants and antimicrobials with a broad spectrum of activities [29] (Table 2). Although QACs are lethal to a wide variety of organisms, including vegetative cells of gram-positive and gram-negative bacteria, fungi, parasites (e.g. *Leishmania major*, *Plasmodium falciparum*), and lipophilic (enveloped) viruses [30–32], they are generally not considered sporicidal (e.g. *Bacillus subtilis*, *Clostridium sporogenes*), tuberculocidal (e.g. *Mycobacterium tuberculosis*, *Mycobacterium bovis*) or virucidal against hydrophilic (non-enveloped) viruses (e.g. *Coxsackievirus*, *Rhinovirus*) [27]. Although the exact antimicrobial mechanism of QACs has not been fully elucidated, it is generally believed that the predominant mode of action is disruption of the cell membrane [33]. The antimicrobial effect of QACs has been attributed to a multitude of factors [16]. The molecular weight of QACs has a profound impact on the efficacy of many

**Table 2**  
Antimicrobial activities of representative QACs against various pathogenic microorganisms and their cytocompatibility.

Microorganism	QACs	Antimicrobial activity	Related niche	Cytotoxicity
<i>A. israelii</i>	MDPB	MIC 12.5 µg/mL [50] MBC 25.0 µg/mL [50]	A/C/E	0–40 µg/mL for 48 h. No cytotoxicity to HDPCs [51] 0–50 µg/mL for 3d. No cytotoxicity to mouse odontoblast-like MDPB-23 cells [52] IC <sub>50</sub> 62.5–75 µM to mouse osteoblast-like MC3T3-E1 cells [53]
<i>A. gerencseriae</i>	MDPB	MIC 3.13 µg/mL [50] MBC 6.25 µg/mL [50]	A/E	
<i>A. naeslundii</i>	MDPB	MIC 3.13–25.0 µg/mL [50] MBC 6.25–50.0 µg/mL [50]	A/C/E	
	QAMP	MIC 20 µg/mL [54,55] MBC 20 µg/mL [54,55]		Not assessed
<i>A. odontolyticus</i>	MDPB	MIC 6.25 µg/mL [50] MBC 12.5 µg/mL [50]	A/C/E	
<i>A. viscosus</i>	DMADDM	MIC 4.9 µg/mL [56] MBC 9.8 µg/mL [56]	A/C/E	LC <sub>50</sub> 20–40 µg/mL to HGFs [56]
	DMAEDM	MIC 20,000 µg/mL [56] MBC 40,000 µg/mL [56]		LC <sub>50</sub> 20–40 µg/mL to HGFs [56]
	DMAE-CB	MIC 12.2 µg/mL [57] MBC 24.4 µg/mL [57] MIC 4.8 µg/mL [58] MBC 9.6 µg/mL [58]		0–2 µg/mL for 24 h. No cytotoxicity to L929 mouse fibroblasts [59] 0–10 µM for 24 h. No cytotoxicity to HDPCs [60] IC <sub>50</sub> 25–35 µM to L929 mouse fibroblasts [61]
	MAE-DB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]		LC <sub>50</sub> 10000–20000 µg/mL to HGFs [57]
	MAE-HB	MIC 24.4 µg/mL [57] MBC 48.8 µg/mL [57]		LC <sub>50</sub> 10000–20000 µg/mL to HGFs [57]
<i>B. bifidum</i>	MDPB	MIC 31.3 µg/mL [62] MBC 62.5 µg/mL [62]	A/E	
<i>B. subtilis</i>	EPSiQA	MIC 2.5 µg/mL [63]	B/W	Not assessed
<i>C. albicans</i>	MDPB	MIC 3.13–12.5 µg/mL [50] MBC 3.13–12.5 µg/mL [50]	A/B/E/W	
	MUPB	MIC 630 µg/mL [64] MBC 5830 µg/mL [64]		IC <sub>50</sub> 50 µg/mL to L929 mouse fibroblasts [64]
<i>C. dubliniensis</i>	MUPB	MIC 830 µg/mL [64] MBC 6670 µg/mL [64]	A/E	
<i>C. glabrata</i>	MUPB	MIC 1040 µg/mL [64] MBC 5210 µg/mL [64]	A/E	
<i>Clinical isolate S. aureus</i>	HACC	MIC <2.5 mg/mL [65]	B/W	2500 µg/mL 6% or 18% substitution HACC for 48 h. No cytotoxicity to L929 mouse fibroblasts [65]
<i>Clinical isolate S. epidermidis</i>	HACC	MIC <2.5 mg/mL [65]	B/W	
<i>E. alactolyticum</i>	MDPB	MIC 31.3 µg/mL [62] MBC 125.0 µg/mL [62]	A/E	
<i>E. coli</i>	EPSiQA	MIC 5.0 µg/mL [63]	A/B/C/E/W	Not assessed
<i>E. faecalis</i>	DMADDM	MIC 9.8 µg/mL [56] MBC 19.5 µg/mL [56]	A/E	

Table 2 (Continued)

Microorganism	QACs	Antimicrobial activity	Related niche	Cytotoxicity
<i>L. acidophilus</i>	DMAEDM	MIC 80,000 µg/mL [56] MBC 160,000 µg/mL [56]	A/C/E	
	DMAE-CB	MIC 12.2 µg/mL [57] MBC 24.4 µg/mL [57]		
	MAE-DB	MIC 12.2 µg/mL [57] MBC 24.4 µg/mL [57]		
	MAE-HB	MIC 24.4 µg/mL [57] MBC 48.8 µg/mL [57]		
	DMADDM	MIC 9.8 µg/mL [56] MBC 19.5 µg/mL [56]		
	DMAEDM	MIC 40,000 µg/mL [56] MBC 80,000 µg/mL [56]		
	DMAE-CB	MIC 3.1 µg/mL [57] MBC 6.2 µg/mL [57]		
	MAE-DB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]		
	MAE-HB	MIC 3.1 µg/mL [57] MBC 6.2 µg/mL [57]		
	MDPB	MIC 15.6 µg/mL [62] MBC 62.5 µg/mL [62]		
<i>L. brevis</i>	MDPB	MIC 15.6 µg/mL [62] MBC 31.3 µg/mL [62]	A/C/E	
<i>L. casei</i>	DMAE-CB	MIC 2.4 µg/mL [58] MBC 9.6 µg/mL [58]	A/C/E	
	MUPB	MIC 630 µg/mL [64] MBC 4580 µg/mL [64]		
<i>L. fermenti</i>	QAMP	MIC 10 µg/mL [54,55] MBC 20 µg/mL [54,55]	A/C/E	Not assessed
	MDPB	MIC 15.6 µg/mL [62] MBC 15.6 µg/mL [62]		
<i>L. paracasei</i>	MDPB	MIC 15.6 µg/mL [62] MBC 62.5 µg/mL [62]	A/C/E	
<i>L. plantarum</i>	MDPB	MIC 7.8 µg/mL [62] MBC 15.6 µg/mL [62]	A/C/E	
	MDPB	MIC 7.8 µg/mL [62] MBC 62.5 µg/mL [62]		
<i>Lactobacillus salivarius</i> ssp. <i>salivarius</i>	MDPB	MIC 15.6 µg/mL [62] MBC 125 µg/mL [62]	A/C/E	
<i>Lactobacillus salivarius</i> ssp. <i>salicinius</i>	MDPB	MIC 3.13–6.25 µg/mL [50] MBC 3.13–6.25 µg/mL [50]	A/C/E	
<i>Lactobacillus</i> ssp.	MDPB	MIC <2.5 mg/mL [65]	B/W	
methicillin-resistant <i>S. aureus</i>	HACC	MIC <2.5 mg/mL [65]	B/W	
<i>P. acnes</i>	MDPB	MIC 3.9 µg/mL [62] MBC 62.5 µg/mL [62]	A/B/E/W	
<i>P. asaccharolyticus</i>	MDPB	MIC 31.3 µg/mL [62] MBC 31.3 µg/mL [62]	A/E	
	MDPB	MIC 2.4 µg/mL [56] MBC 4.9 µg/mL [56]		
<i>P. gingivalis</i>	DMADDM	MIC 2.4 µg/mL [56] MBC 4.9 µg/mL [56]	A/E	
	DMAEDM	MIC 20,000 µg/mL [56] MBC 40,000 µg/mL [56]		
<i>P. melaninogenica</i>	DMAE-CB	MIC 3.1 µg/mL [57] MBC 6.2 µg/mL [57]	A/E	
	MAE-DB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]		
	MAE-HB	MIC 3.1 µg/mL [57] MBC 6.2 µg/mL [57]		
	DMADDM	MIC 2.4 µg/mL [56] MBC 4.9 µg/mL [56]		
	DMAEDM	MIC 20,000 µg/mL [56] MBC 40,000 µg/mL [56]		
	DMAE-CB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]		
	MAE-DB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]		
	MAE-HB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]		
	DMADDM	MIC 4.9 µg/mL [56] MBC 9.8 µg/mL [56]		
	DMAEDM	MIC 40,000 µg/mL [56] MBC 80,000 µg/mL [56]		
<i>S. aureus</i>	DMAE-CB	MIC 12.2 µg/mL [57] MBC 24.4 µg/mL [57] MIC 1.2 µg/mL [58] MBC 2.4 µg/mL [58]	B/W	
	EPsiQA	MIC 2.5 µg/mL [63]		
	MAE-DB	MIC 12.2 µg/mL [57] MBC 24.4 µg/mL [57]		Not assessed

Table 2 (Continued)

Microorganism	QACs	Antimicrobial activity	Related niche	Cytotoxicity		
<i>S. gordonii</i>	MAE-HB	MIC 24.4 µg/mL [57] MBC 48.8 µg/mL [57]	A/C/E			
	MUPB	MIC 1750 µg/mL [64] MBC 5830 µg/mL [64]				
	MDPB	MIC 16.7 µg/mL [66] MBC 31.3 µg/mL [51]				
	<i>S. mitis</i>	MDPB			MIC 25.0 µg/mL [66] MBC 31.3 µg/mL [51]	
		<i>S. mutans</i>			DMADDM	MIC 4.9 µg/mL [56] MBC 9.8 µg/mL [56] MIC 6.0 µg/mL [67] MBC 12.0 µg/mL [67] MIC 4.9 µg/mL [68] MBC 9.7 µg/mL [68]
	DMAEDM				MIC 20,000 µg/mL [56] MBC 40,000 µg/mL [56]	
	DMAE-CB				MIC 3.1 µg/mL [57] MBC 6.2 µg/mL [57] MIC 2.4 µg/mL [58] MBC 4.8 µg/mL [58]	
	DMAHDM				MIC 0.6 µg/mL [68] MBC 1.2 µg/mL [68]	Not assessed
	DDMAI				MIC 6.25 µg/mL [69]	Not assessed
	MAE-DB				MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]	
<i>S. oralis</i>	MAE-HB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]	A/C/E			
	MDPB	MIC 12.5 µg/mL [50] MBC 50.0 µg/mL [50] MIC 12.5 µg/mL [66] MBC 62.5 µg/mL [51]				
	MUPB	MIC 1040 µg/mL [64] MBC 4170 µg/mL [64]				
	PQAS	MIC 1.563 µg/mL [44]				
	QAB	MIC 25 µg/mL [70]				
	QADM	MIC 13,000 µg/mL [67] MBC 25,000 µg/mL [67]				
	QAMP	MIC 20 µg/mL [54,55] MBC 20 µg/mL [54,55]				
	<i>S. salivarius</i>	MDPB			MIC 12.5 µg/mL [50] MBC 25.0 µg/mL [50] MIC 16.7 µg/mL [66] MBC 31.3 µg/mL [51]	C
		<i>S. sanguis</i>			DMADDM	
	DMAEDM				MIC 20,000 µg/mL [56] MBC 40,000 µg/mL [56]	
DMAE-CB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]					
MAE-DB	MIC 12.2 µg/mL [57] MBC 24.4 µg/mL [57]					
MAE-HB	MIC 6.1 µg/mL [57] MBC 12.2 µg/mL [57]					
<i>S. sobrinus</i>	MDPB		MIC 16.7 µg/mL [66] MBC 31.3 µg/mL [51]	A/C/E		
	MDPB		MIC 7.8 µg/mL [66] MBC 62.5 µg/mL [51]			

Related niche. A: apical periodontitis; B: bone infections; C: caries; E: endodontic infections; W: wound infections.

QAC-based antimicrobial systems [34,35]. The length of the *N*-alkyl chain affects the antimicrobial activities of QACs [36–38]. For different bacteria and fungi, the optimum chain length of QACs is different (14 carbons for gram-positive bacteria, 16 carbons for gram-negative bacteria and 12 carbons for yeast and filamentous fungi) [39,40]. Counter anion has a profound effect on the efficiency and selectivity toward different microbes due to discrepancies in polymer morphology, binding affinity toward quaternary compounds and the solubility of polycations in water, resulting

in variable degrees of antimicrobial performance [41–44]. Some researchers found that the antimicrobial activity of QA dendrimers is dependent on the counter anion and biocides with bromide anions are more potent than those with chloride anions [35]. Conversely, other studies reported that counter anion species have no effect on antibacterial activities [45,46]. In addition, molecular charge density also affects the antimicrobial actions of QACs [47–49]. For example, a threshold of immobilized surface QA groups is required to cause significant reduction in viable bacteria [49].

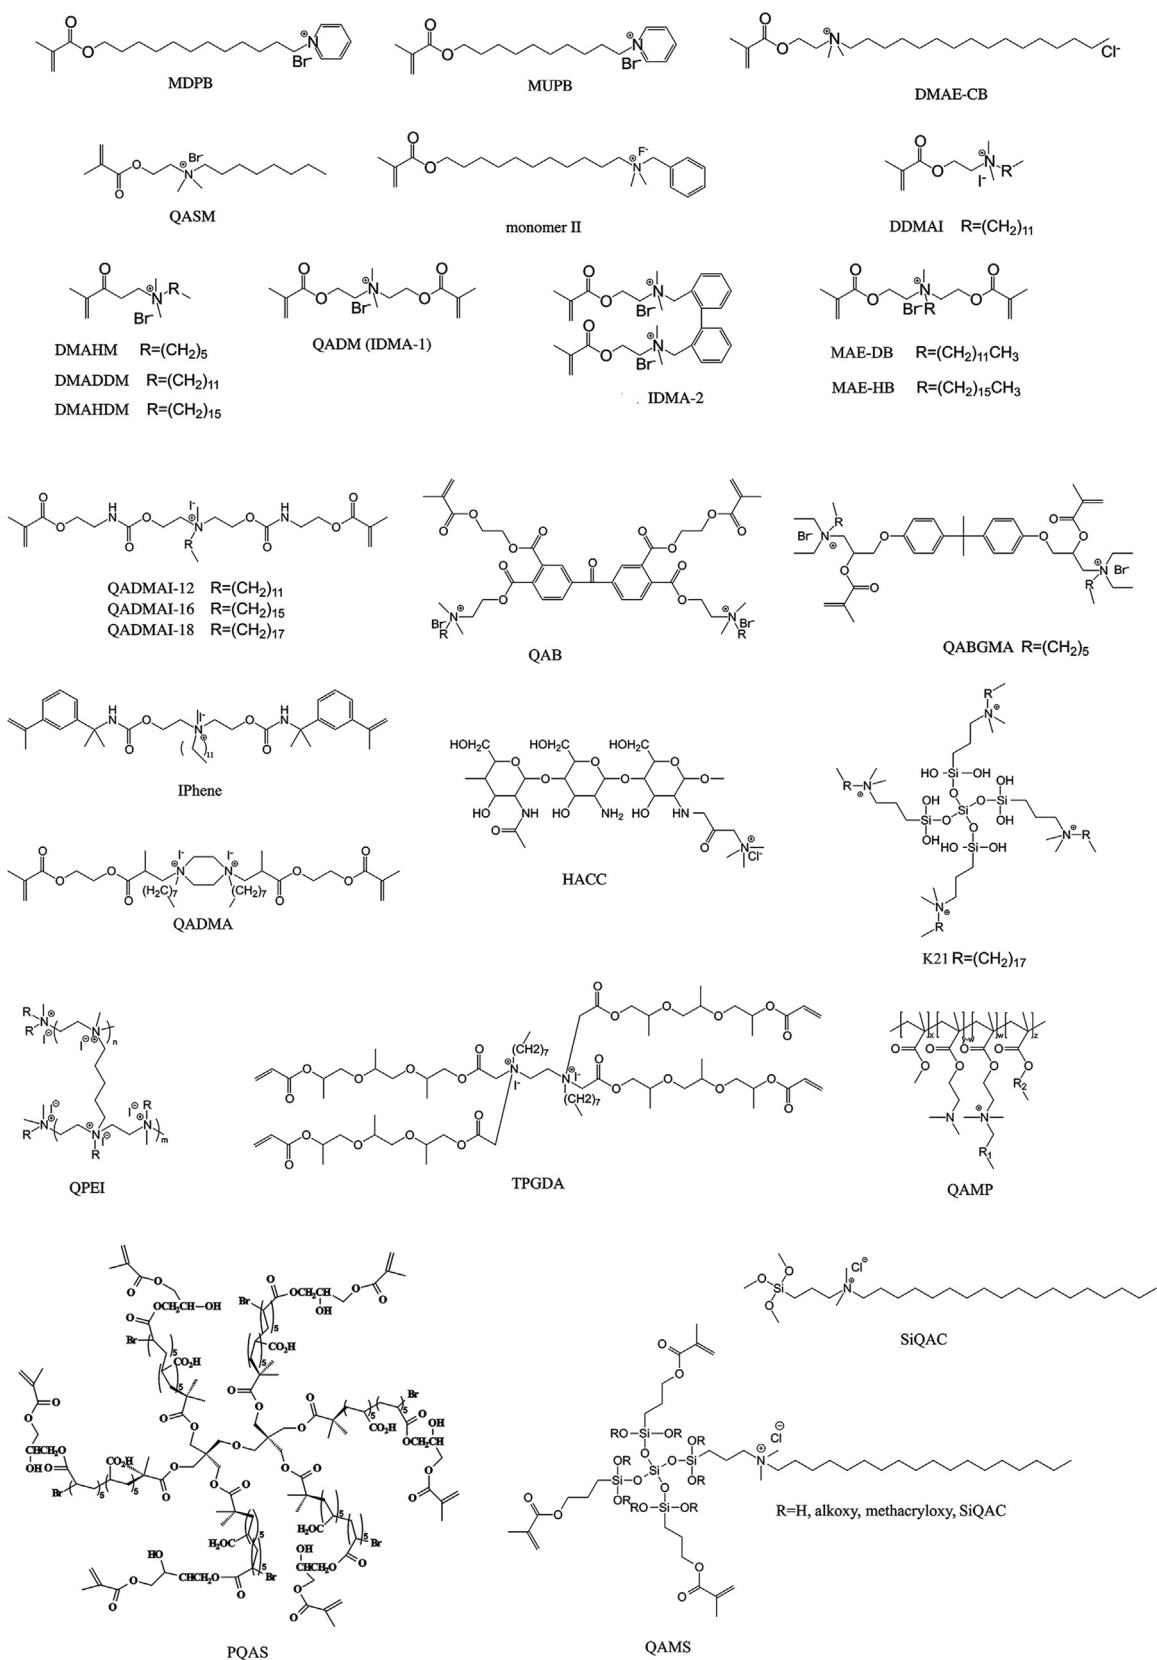


Fig. 2. Chemical structures of representative quaternary ammonium compounds in antimicrobial biomedical materials.

## 2.2. Antifungal activities

Fungi have a single membrane surrounded by a thick cell wall composed of glucan and chitin, similar to the cell envelope of

gram-positive bacteria [71]. Previous studies attributed the antifungal mechanism of QACs to electrostatic interaction with the fungi cell membrane that results in cell lysis [72–74]. More recent work on QACs reported a different antifungal mechanism. In-situ

hybridization with fluorescent oligonucleotide probes shows that fungi express hyphae on untreated prostheses but not on QAC-coated prostheses. This observation suggests that the antifungal activities of QACs may involve impediment of hyphae formation [75]. The micelle-forming cationic detergent cetyltrimethylammonium bromide (CTAB) does not cause disruption of the fungal cell membrane [76]. Instead, its antifungal activity may be associated with the reversal of cell surface charges from negative to positive, as determined from measurements of the cell electrophoretic mobility. The antifungal activities of QACs are largely dependent on molecular structures [77]. To cause fungus death, the cationic QA moiety has to be adsorbed onto the cell, alter the inherent charge of the cell wall and penetrate the latter to reach the fungal cell membrane. The antifungal activity of the bilayer-forming, cationic synthetic lipid dioctadecyldimethyl-ammonium bromide (DODAB) has been reported to be not as strong as CTAB. This phenomenon may be attributed to cell aggregation as a function of cell concentration [78]. Fungal cells that are inside cell aggregates cannot be reached by DODAB and those cells remain viable. Conversely, the aggregated cells are apparently defenseless in the presence of CTAB. These results suggest that CTAB molecules penetrate *Candida albicans* aggregates more effectively to exert their antimicrobial activity. In addition, the rigid gel state of the DODAB molecule may hamper its penetration into the fungal cell wall and cytoplasmic membrane [79].

The mode of action of gemini QACs appears to involve lysis of the cell membrane and organelles without fungal cell wall destruction or protein leakage. Gemini QACs containing two pyridinium residues [3,3'-(2,7-dioxaoctane)bis(1-decylpyridinium bromide)] per molecule. These residues possess fungicidal activity against *Saccharomyces cerevisiae* by causing respiration inhibition and cytoplasmic leakage of adenosine triphosphate, magnesium, and potassium ions [80]. Gemini QACs exhibit more effective antifungal activity in comparison with mono-QACs *N*-cetylpyridinium chloride [81]. In addition, the activity of the gemini surfactant against *S. cerevisiae* and *C. albicans* results in elevated levels of reactive oxygen species (ROS) under aerobic conditions. The potent antifungal activity of *D*-glucosamine QA derivatives against *Coriolus versicolor* and *Poria placenta* may be explained by their capacity to recognize different kinds of enzymes released during fungal growth [82]. Apart from their effects on enzymes, *D*-glucosamine QA derivatives may also form complexes with vital metallic elements in the fungi to block or decrease fungal growth.

### 2.3. Antiviral activities

The virucidal capacity of Zephiran (alkyl-dimethylbenzylammonium chloride) against various types of viruses was summarized by Klein and Deforet as early as 1983 [27]. Zephiran effectively inactivates lipid-containing (enveloped) viruses such as vaccinia virus, and some non-lipid-containing (non-enveloped) viruses such as reovirus, and bacteriophages. However, it is ineffective against smaller non-lipid-containing viruses such as picornaviruses. In some studies, QACs were found to possess antiviral properties against enveloped *Herpes simplex* virus (HSV)-1 [83,84]. The virucidal mechanism of QACs for lipophilic enveloped viruses appears to involve disruption or detachment of the viral envelope with subsequent release of the nucleocapsid. Disruption of the viral envelope may be attributed to the higher affinity of enveloped viruses for QAC through hydrophobic interactions. However, further disruption of the released nucleocapsids by QACs was not observed. The differential virucidal activities of QACs on enveloped or non-enveloped viruses were also investigated in another study [10]; the QACs tested were virucidal against enveloped *Influenza A* (H1N1) virus, but were ineffective against non-enveloped *Poliovirus Sabin1*. Several QA camphor derivatives


have been evaluated against a broad range of influenza viruses [85–88]. These compounds interfered with the viral fusion process and effectively inhibited influenza virus replication in cell cultures. Shiraishi et al. screened the Takeda chemical library for novel anti-HIV-1 agents and identified an anilide derivative with a QA moiety as a potent and selective small-molecule (C–C chemokine receptor type 5) CCR5 antagonist for inhibition of macrophage-tropic HIV-1 replication [89]. Although the exact mechanism has not been fully elucidated, the QA moiety was found to enhance CCR5 antagonistic activity.

The antiviral activities of QACs against enveloped viruses have gained widespread recognition. However, whether QACs are effective against non-enveloped viruses remains controversial. QACs have repeatedly been reported as effective against some specific non-enveloped viruses. In studies evaluating the virucidal activity of disinfectants against various viruses, QACs are virucidal against feline viral rhinotracheitis virus and feline herpesvirus, but ineffective against feline calicivirus, feline panleukopenia virus (a parvovirus), feline parvovirus, canine parvovirus, and foot-and-mouth disease virus [90–94]. The lethal activity of QACs on enveloped viruses is linked to detachment of the viral envelope. In non-enveloped viruses, QACs induce formation of nonstructural substances such as micelles but are not lethal to the viruses [95]. A meta-analysis on virus inactivation by chemical disinfectants indicates that QACs are relatively ineffective against human Norovirus [96]. Recently, a topical QA silane prepared by sol-gel reaction of an antimicrobial trialkoxysilane with an anchoring tetra-alkoxysilane (codenamed “K-21”) has been reported to inhibit the replication of enveloped and non-enveloped DNA and RNA viruses at non-toxic concentrations, including *HSV-1*, *Human Herpesvirus-6* and *Human Herpesvirus-7*. These viruses have the capability to establish lifelong latency in humans and can be reactivated later in life [97]. Because reactivation of the immunosuppressive and neurotrophic *Human Herpesvirus-6* in human brain tissues can cause cognitive dysfunction, permanent disability or death, and may play a role in a subset of patients with chronic neurological conditions such as multiple sclerosis, mesial temporal lobe epilepsy, status epilepticus and chronic fatigue syndrome, there is an urgent need for more studies on the capability for the K-21 agent to inhibit the replication of *Human Herpesvirus-6* *in vivo*.

### 2.4. Anti-MMP activities

Host-derived MMPs and cysteine cathepsins play a major role, among other factors, in compromising the durability of resin-dentin bonds in tooth-colored filling materials via enzymatic hydrolysis of the collagen matrix [98,99]. During dentin formation, MMPs, a group of zinc- and calcium-dependent host-derived proteases, are highly active in enzymatic hydrolysis of the collagen matrix [100]. Inactive MMPs can be activated by mild acids during the dentin caries process [101]. Single nucleotide polymorphisms of *MMP2* and *MMP3* gene are involved in dental caries susceptibility [102,103]. Dental adhesives containing 5 wt% 12-methacryloyloxy dodecyl pyridinium bromide (MDPB) exhibited 89% inhibition of soluble recombinant human MMP-9 and 90% inhibition of matrix-bound endogenous MMPs [104]. The inhibitory effect of MDPB on MMPs may contribute to the improved durability achieved by MDPB-containing adhesives. Since MDPB can be copolymerized with methacrylate resin comonomers in the adhesive-tooth interface, such MMP-inhibitors may keep inhibiting MMPs over time. The inhibitory effect of QA methacrylates on endogenous dentin MMPs has been attributed to prevention of the release of collagen degradation products, including cross-linked carboxyterminal telopeptide of type I collagen (ICTP) by MMPs and C-terminal crosslinked telopeptide of type I collagen fragments (CTX) by cathepsin K [105]. Although the exact mechanisms of the

### “grafting onto” approach

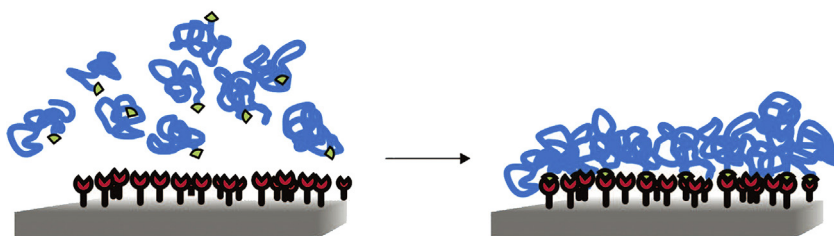

### “grafting from” approach

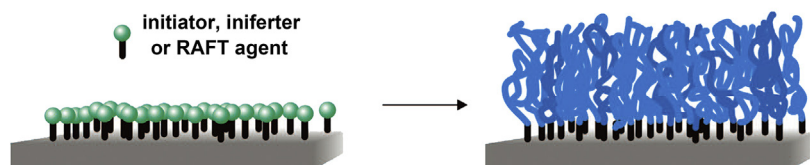


Fig. 3. Immobilization methods to produce antimicrobial surfaces by covalent attachment. [116], Copyright 2009.

Reproduced with permission from American Chemical Society.

anti-MMP effects of QACs have not been elucidated, it has been hypothesized that cationic QACs can electrostatically act on the catalytic site of MMPs, thereby inhibiting MMP-catalyzed hydrolysis of the collagen matrix [106,107].

Matrix metalloproteinases also play important roles in pulp tissue and periapical inflammation [108]. Bacterial lipopolysaccharide (LPS)-induced release of pro-inflammatory mediators elevate levels of MMP-1, -2 and -3 in acute pulpitis [109,110]. Release of MMP-3 can activate other MMP members, mediate collagen degradation in the extracellular matrix, induce inflammation and promote angiogenesis [111]. MMP-13 is the major collagenase in dental pulp tissues and is effective in cleaving type II collagen. In periodontitis, MMP family members have been confirmed to be associated with severe tissue disorganization [112–114]. A recent clinical investigation identified higher levels of MMP-1, -2 and -9 in the periapical interstitial fluid of patients with apical periodontitis [115]. Hence, in addition to their antimicrobial properties, incorporation of QACs into sealers for root canal treatment has the potential to inhibit MMPs directly for controlling the severity of periapical inflammation.

### 3. QA-based antimicrobial surfaces

#### 3.1. “Grafting onto” vs “grafting from” approaches

Tethering of functional polymers with QA functionalities is an effective means to impart antimicrobial properties to biomedical materials. Such antimicrobial surfaces are generally prepared via two major immobilization methods, the “grafting onto” and “grafting from” approaches [116] (Fig. 3).

In the “grafting onto” approach, polymer molecules from solution are directly immobilized on suitable surfaces. Although experimentally simple, such an approach suffers from the drawbacks of relatively low grafting density as a result of steric hindrance from the already-adsorbed/attached polymer chains. These polymers form mushroom-like structures and render potential reactive sites inaccessible, further limiting the grafting density [117]. Thus, only a small amount of the polymers can be immobilized onto the surface using the “grafting onto” approach.

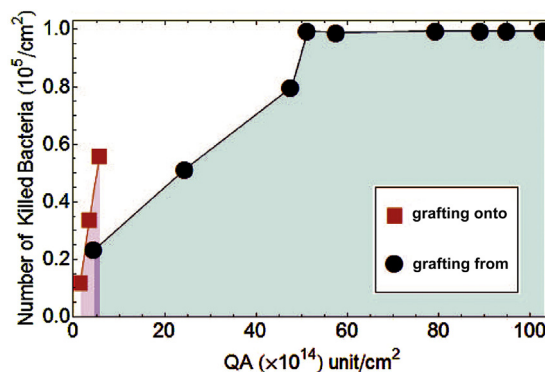


Fig. 4. Difference in biocidal activity of surfaces prepared by the “grafting onto” and the “grafting from” approaches. QA: quaternary amine group. [119], Copyright 2008. Reproduced with permission from American Chemical Society.

Furthermore, the reaction between the polymer end-groups and reactive groups on the substrate surfaces becomes less efficient as the molecular weight of the polymer in solution increases [118].

The “grafting from” approach, also known as “surface-initiated polymerization”, has attracted increasing interest in recent years due to its ability to produce grafted polymers with better control of polymer features including functionality, density and thickness of the grafted polymers. The surface is first modified with suitable initiators. This surface-bound initiator monolayer allows surface-initiated polymerization of monomers to produce functional polymers with optimal thickness and higher density. Steric hindrance is greatly reduced because of the addition of monomers to the end of the growing chains or to primary radicals. Matyjaszewski’s group investigated the differences in bactericidal efficacy between grafted-onto and grafted-from surfaces. Compared with the “grafting onto” approach, the “grafting from” approach produced surfaces with a higher charge density ( $10^{16}$  vs  $6 \times 10^{14}$  charges/cm<sup>2</sup>) and a higher biocidal efficacy [119] (Fig. 4). Based on the “grafting from” approach, many polymerization techniques including conventional free radical polymerization

(FRP) and controlled radical polymerization (CRP) have found widespread use for the synthesis of antimicrobial surfaces.

### 3.2. Controlled radical polymerization

Conventional FRP is a type of instantaneous chain growth polymerization involving chain initiation, propagation and termination [120,121]. The biggest drawback to this technique is the large dispersity and poor control over molecular mass. Free radical polymerization techniques usually produce final products with a broader distribution of polymer chain length and/or equivalent degree of polymerization and functional group density due to unavoidable, fast radical–radical termination reactions [122]. Nevertheless, the compliant nature of FRP, including its versatility in monomer selection, relatively mild polymerization conditions and tolerance to many different solvents (such as water) and impurity, makes this polymerization technique one of the most widely used processes for preparing QA-based polymers from the perspective of industrial production and applications.

Over the last two decades, the advent of CRP techniques enables precise control over macromolecular structure, order and functionality, which are important considerations for emerging biomedical designs. In the following sections, the major surface-initiated controlled radical polymerization (SI-CRP) techniques will be discussed. Table 3 summarizes the typical antimicrobial surfaces immobilized with QA moieties that have been prepared using SI-CRP.

Among the different CRP techniques that are available, atom transfer radical polymerization (ATRP) has been the most extensively studied [124,155,156] and reviewed for the preparation of a wide variety of polymeric materials [157–160]. The first antimicrobial surface with QA moieties prepared via surface initiated-ATRP (SI-ATRP) was reported by Matyjaszewski's group [123]. In that study, 2-(dimethylamino)ethyl methacrylate (DMAEMA) was polymerized directly onto filter paper via SI-ATRP. Subsequent quaternization of the amino groups of p(DMAEMA) generated a high concentration of QA groups on the polymer-modified surface (Fig. 5). These modified surfaces exhibited substantial antimicrobial activities against *Escherichia coli* and *Bacillus subtilis*. The authors found that biocidal activity increased with the density of available QA groups on the modified surface. Different functional monomers have subsequently been polymerized via SI-ATRP followed by quaternization to immobilize QA groups onto the polymer surfaces. Techniques involving SI-ATRP are excellent for preparing antimicrobial surfaces with QA groups because of their: (1) chemical versatility and compatibility with functional groups and monomers, (2) tolerance against a relatively high degree of impurities, and (3) relatively easy synthesis of surface-immobilizable initiators. Nevertheless, it is challenging to achieve controlled polymerization of pyridine-containing monomers, since the latter can complex or react with the metal catalysts. In addition, residual traces of catalysts are difficult to remove, which may result in undesirable toxicity in biomedical materials.

Reversible addition fragmentation chain transfer (RAFT) polymerization was introduced by Moad's group [161,162]. This technique possesses several advantages, the most important being the ability to synthesize well-defined polymers with various polar and nonpolar monomers under mild polymerization conditions. In addition, implementation of RAFT polymerization is relative simple and versatile by adding an appropriate chain transfer agent (CTA) into a conventional FRP system. Usually, the same monomers, initiators, solution and temperatures may be used. Hence, RAFT polymerization has great potential for preparation of antimicrobial coatings [163]. The most critical issue for successful RAFT polymerization is the selection of a suitable CTA. Commonly-used CTAs include dithioesters, xanthates, dithiocarbamates and trithiocar-

bonates [164]. Antimicrobial surfaces with QA moieties have been successfully prepared via surface initiated-RAFT (SI-RAFT) polymerization. For example, cellulose filter paper was polymerized with DMAEMA via SI-RAFT and further quaternized [128] (Fig. 5). When the modified materials were exposed to *E. coli*, cellulose fibers with the highest degree of quaternization or quaternized with the shortest alkyl chains exhibited more potent antimicrobial activities. Recently, Wang et al. reported the synthesis of a temperature-triggered, recyclable bactericidal and antifouling surface [126,127]. At a temperature above the lower critical solution temperature (LCST), the biomaterial surface is able to capture and effectively kill bacteria due to the presence of quaternized p(DMAEMA). Remarkably, the surface is capable of releasing the adhered bacteria corpses when the temperature is reduced to below the LCST. Moreover, the surface maintains its self-cleaning and bactericidal properties by simply washing with cold water and has good biocompatibility. This functionalized coating shows potential for multiple medical applications, including drug delivery, surface modification and tissue engineering. However, a major drawback of RAFT polymerization is that different monomers require specific CTAs, which are usually not commercially available. For example, methyl methacrylate (MMA) requires the use of a dithiobenzoate, whereas vinyl acetate can only be polymerized in the presence of a xanthate [165,166].

Nitroxide-mediated polymerization (NMP), the simplest CRP technique, is accomplished by introducing a free nitroxide to the conventional FRP process. This type of polymerization is based on a reversible termination mechanism between the propagating radical and the nitroxide. The nitroxide acts as a control agent to yield alkoxyamine as the predominant species [167]. Owing to the living nature of NMP, this method can be applied to surface-initiated polymerization (SI-NMP) for preparing antimicrobial surfaces. In a typical SI-NMP process, binding of the initiator depends on the chemical nature of the surface, which may be achieved via covalent bonding, electrostatic interaction or hydrogen bonding. Ignatova et al. reported a two-step “grafting from” method for preparing antimicrobial stainless steel surfaces by sequential cathodic electrografting of an alkoxyamine-containing acrylate with SI-NMP of styrene and DMAEMA, followed by quaternization of the grafted polymers [129] (Fig. 5). The modified surface possesses significant antibacterial activities against both *Staphylococcus aureus* and *E. coli*. The thickness and hydrophilicity of the immobilized polymers may also be tailored by SI-NMP. Because no additional catalysts are required, this avoids the need for additional purification and reduces the chance to introduce impurities. Konn et al. used a similar alkoxyamine anchoring strategy with synthetic laponite clay platelets [154]. In this process, a quaternary ammonium alkoxyamine initiator is first intercalated into the clay galleries by cation exchange. Then, NMP of styrene was initiated from the surface of the functionalized clay platelets to obtain well-defined, ionically-bonded polystyrene chains with narrowly-distributed molecular weight. However, relatively high polymerization temperatures may cause problems when thermally-sensitive monomers are employed. In addition, the selection and synthesis of suitable nitroxides increase the workload in preparing antimicrobial coatings. Nitroxide-mediated polymerization may also be accomplished using the “grafting onto” approach. However, this synthesis pathway is not as popular due to steric hindrance of the grafted polymers.

### 3.3. Ring-opening polymerization

The history of ring-opening polymerization (ROP) dates back to the 1900s and presently, many polymers of industrial importance are produced using ROP [168]. In the ROP process, the terminal end of a polymer chain acts as a reactive center, which may be

**Table 3**  
Typical antimicrobial surfaces immobilized with QA moieties prepared via surface-initiated controlled radical polymerization (SI-CRP).

Substrate	Grafted monomer	SI-CRP technique	Microorganisms tested	Refs.
Glass, filter paper	DMAEMA	SI-ATRP	<i>E. coli</i> , <i>B. subtilis</i>	[123]
Glass, silicon wafer	DMAEMA	SI-ATRP	<i>E. coli</i>	[124]
Glass	DMAEMA, TMSPMA	SI-ATRP	<i>E. coli</i>	[119]
Glass	DMAEMA	SI-ATRP	<i>A. niger</i>	[125]
Glass, PDMS, silicon wafer	DMAEMA, NIPAAm	SI-RAFT	<i>E. coli</i> , <i>S. aureus</i>	[126,127]
Cellulose paper	DMAEMA	SI-RAFT	<i>E. coli</i>	[128]
Stainless steel	DMAEMA	SI-NMP	<i>E. coli</i> , <i>S. aureus</i>	[129]
Stainless steel	EA, PTEA, 8QA	SI-NMP	<i>E. coli</i> , <i>S. aureus</i>	[130]
Stainless steel	4VP	SI-ATRP	<i>D. desulfuricans</i>	[131]
Stainless steel	DMAEMA	SI-ATRP	<i>D. desulfuricans</i>	[132]
Stainless steel	BPEA, FAc	SI-ATRP	<i>S. aureus</i>	[133]
Stainless steel	DMAEMA	SI-ATRP	<i>D. desulfuricans</i>	[134]
Fe <sub>3</sub> O <sub>4</sub> magnetite nanoparticle	DMAEMA	SI-ATRP	<i>E. coli</i>	[135]
Fe(acac) <sub>3</sub> magnetite nanoparticle	4VP	SI-ATRP	NM	[136]
Titanium	HEMA	SI-ATRP	<i>S. aureus</i>	[137]
Gold, Si/SiO <sub>2</sub> surface	SPMA	SI-ATRP	<i>P. aeruginosa</i>	[138]
Silicon wafer	DMAEMA	SI-ATRP	<i>P. sp</i>	[139]
Silicon wafer, gold-coated silicon wafer, glass, cellulose acetate, silicon nanowire array, PU, PDMS, stainless steel	P(AA-co-Ada), PAH	SI-RAFT	<i>E. coli</i> , <i>S. aureus</i>	[140]
Silicon rubber	AAm	SI-ATRP	<i>S. aureus</i> , <i>E. coli</i>	[141]
Silicon rubber	AAm	SI-ATRP	<i>S. aureus</i> , <i>S. salivarius</i> , <i>C. albicans</i>	[142]
Silicon nanowire array	DMAEMA	SI-ATRP	<i>E. coli</i>	[143]
Silicon catheter	DMAEMA	SI-ATRP	<i>S. aureus</i>	[144]
PVDF membrane	DMAEMA	SI-RAFT	<i>E. coli</i>	[145]
PVDF membrane	DMAEMA	SI-ATRP	<i>E. coli</i>	[146]
Polymer microsphere	DMAEMA	SI-ATRP	<i>E. coli</i> , <i>S. aureus</i>	[147]
Polyolefin	TBAEMA	SI-ATRP	<i>E. coli</i>	[148]
Polyolefin	PB	SI-NMP	NM	[149]
Polypropylene	DMAEMA	SI-ATRP	<i>E. coli</i>	[150]
Polypropylene	TBAEMA	SI-ATRP	<i>E. coli</i>	[151]
Polypropylene	DMAEMA	SI-ATRP	<i>E. coli</i> , <i>S. aureus</i>	[152]
Microfiber	DMAEMA	SI-ATRP	<i>E. coli</i> , <i>S. aureus</i>	[153]
Laponite clay platelet	DEPN	SI-NMP	NM	[154]

**Table 4**  
Typical biomaterials grafted with QA-based polymers via ring-opening polymerization (ROP).

Products	Microorganisms tested	Refs.
PEG/quaternary copolyoxetanes	<i>S. aureus</i> , <i>E. coli</i> , <i>P. aeruginosa</i>	[171,172]
Polycarbonate hydrogels	<i>S. aureus</i> , <i>E. coli</i> , <i>P. aeruginosa</i> , <i>C. albicans</i>	[176]
QPGMA polymers	<i>E. coli</i> , <i>S. aureus</i> .	[177]
PAMAM dendrimers	<i>S. aureus</i> , <i>P. aeruginosa</i>	[173]
Silica nanoparticles	<i>S. aureus</i> , <i>P. aeruginosa</i> .	[174]


radical, anionic or cationic. Cyclic monomers can polymerize by opening the ring system using metal catalysts [169]. Depending on the nature of the initiator and catalyst, ROP may proceed via radical, cationic or anionic reaction mechanisms [170]. Examples of antimicrobial surfaces with QA moieties prepared by ROP have also been reported in the literature (Table 4). Wynne's group prepared a series of quaternary/polyethylene glycol (PEG) copolyoxetanes via cationic ROP; these copolyoxetanes possessed biocidal activities against *E. coli*, *S. aureus* and *Pseudomonas aeruginosa* [171,172]. The authors found that both linear charge density and quaternary alkyl chain length affected antimicrobial efficacy, hemolytic activity and cytotoxicity. Other workers concentrated on the synthesis of QA-functionalized surfaces/materials with dual antimicrobial actions [173,174]. Nitric oxide (NO)-releasing, QA-functionalized silica nanoparticles are synthesized by first tethering glycidyl-trialkylammoniumchloride (GTAC) via ROP. This is followed by functionalization of the secondary amine with N-diazeniumdiolate, the NO donor (Fig. 6).

Compared with nanoparticles with NO release or QA functionalities only, combining NO release with QA functionalities on the same nanoparticle resulted in augmented bactericidal efficacy against *S. aureus*. Nitric oxide is an endogenously synthesized small

molecule involved in vital cellular functions and exhibits antimicrobial effects against a wide range of organisms. Hence, exogenous NO donors are promising bactericidal agents [19]. The development of novel monomers and catalysts enables more precise control over the molecular weight, structure and configuration of the polymers. In some cases, ROP and CRP techniques may be implemented together. For example, Leng et al. reported the synthesis of copolymer micelles of poly(caprolactone)-poly(quaternary ammonium salt) by a combination of ROP and ATRP. These copolymer micelles do not only possess antibacterial ability but may also be employed as carriers for antibacterial drugs [175].

### 3.4. Click chemistry

Click chemistry has recently emerged to become one of the most powerful tools in syntheses involving biomedical and chemical applications, including organic synthesis, medicinal chemistry, surface and polymer chemistry, drug discovery and chemical biology. The term "click chemistry" was coined by Sharpless and coworkers in 2001, and refers to a method for attaching a substrate of choice to specific biomolecules (site-specific bioconjugation) [178]. Click reactions are more broadly defined contemporarily as those

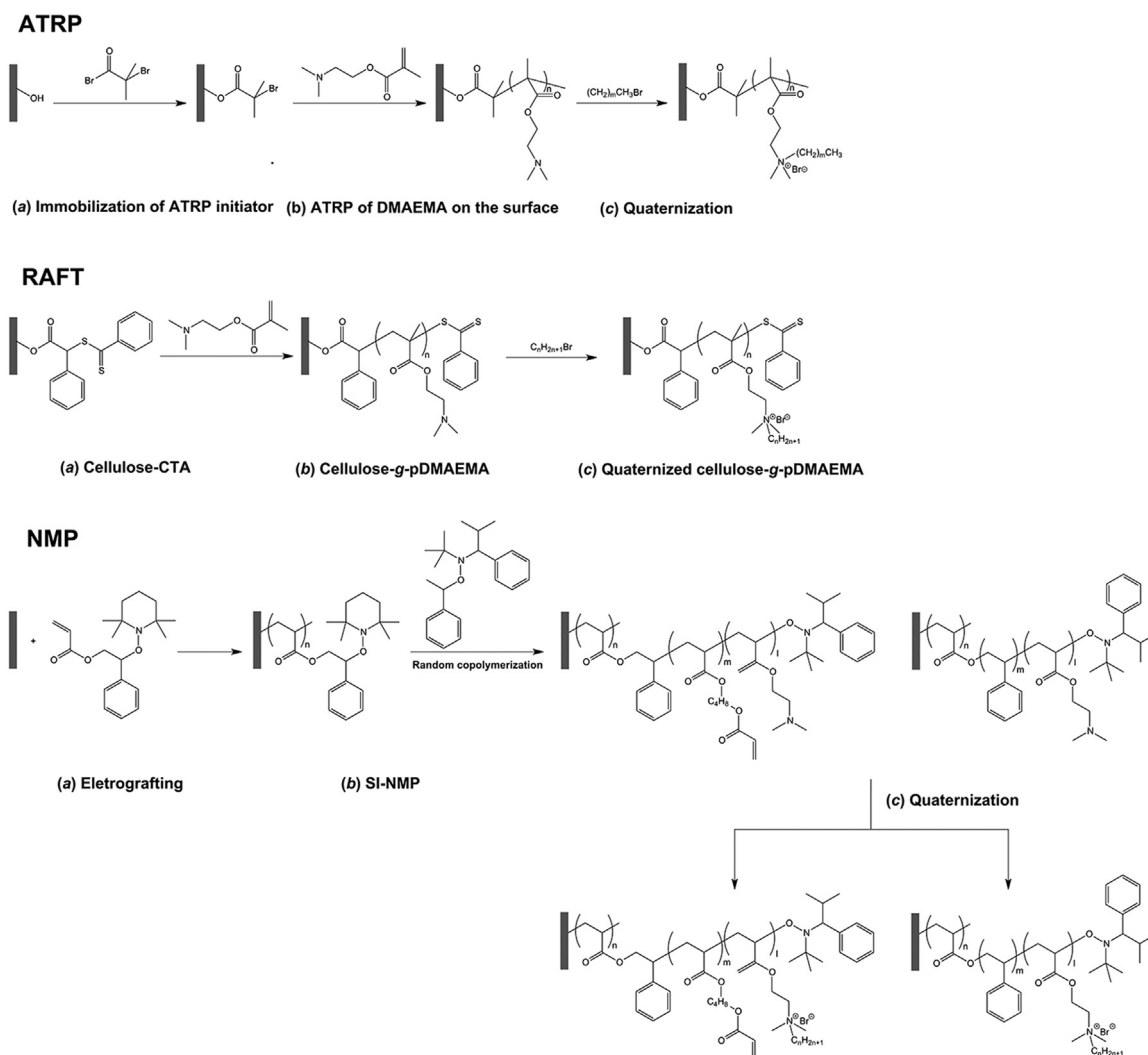


**Fig. 5.** Representative quaternary ammonium-based antimicrobial coatings prepared by controlled radical polymerization (CRP). ATRP: atom transfer radical polymerization; CTA: chain transfer agent; DMAEMA: 2-(dimethylamino)ethyl methacrylate; NMP: nitroxide-mediated polymerization; RAFT: reversible addition fragmentation chain transfer; SINMP: surface initiated nitroxide-mediated polymerization. [123], Copyright 2004. Reproduced with permission from American Chemical Society. [128], Copyright 2008, Reproduced with permission from American Chemical Society. [129], Copyright 2004, Reproduced with permission from American Chemical Society.

that meet the criteria of ready availability of starting materials and reagents, high efficiency under mild conditions, regio- and stereo-selectivity, high yield, minimal by-products and limited side reactions. The aforementioned characteristics may be achieved by reactions possessing a high thermodynamic driving force (usually greater than  $20 \text{ kcal mol}^{-1}$ ). The most common methods for incorporating clickable groups into polymer chains include: (1) the use of functional initiators or transfer agents, (2) direct polymerization of functional monomers yielding pendant functionality and (3) post-polymerization transformation of end groups, each of which yielding terminal functionality [179]. Recently, the application of click techniques has found widespread use in the synthesis chemistry and there are a number of comprehensive reviews highlighting these exciting approaches [180–184]. Some of the most commonly used click reactions for creating antimicrobial surfaces with QA moieties, including Cu-catalyzed azide–alkyne cycloaddition (CuAAC), Cu-free click cycloaddition and thiol–ene reaction are illustrated in Fig. 7.


The quintessential example of click chemistry, CuACC, has generated the highest interest for producing QA antimicrobial surfaces [185,186]. In a CuAAC reaction, [3 + 2] cycloaddition occurs between

an organic azide and a terminal alkyne to produce Cu(I)-catalyzed 1,4-disubstituted 1,2,3-triazole [187]. In general, three key processes are involved in a CuAAC reaction: (1) initial formation of a 5-triazolyl copper intermediate, (2) coordination of the intermediate to organic azide and reaction between the nucleophilic carbon on the Cu(I) acetylide and the electrophilic terminal nitrogen on the azide, (3) ring contraction of the metallocycle and subsequent dissociation of the product to regenerate the catalyst. The reactions can accommodate a wide variety of functional groups and can proceed in many solvents (e.g. water), a wide range of pH values and over a broad temperature range. The reaction rate of CuAAC is more than  $10^7$  times faster than conventional reactions, which means that CuAAC may proceed efficiently at ambient temperature. It does not take long for chemists to realize the practicality and reliability of CuAAC in creating QA-based antimicrobial surfaces. For example, Ganewatta et al. recently produced QA-modified antimicrobial and biofilm-disrupting surfaces via CuAAC between surface-immobilized azide groups and the alkyne moiety on QACs [188] (Fig. 8). Other antimicrobial surfaces are produced by post-polymerization modification, via quaternization of tertiary amines to QA groups [189–191]. These reactions often involve

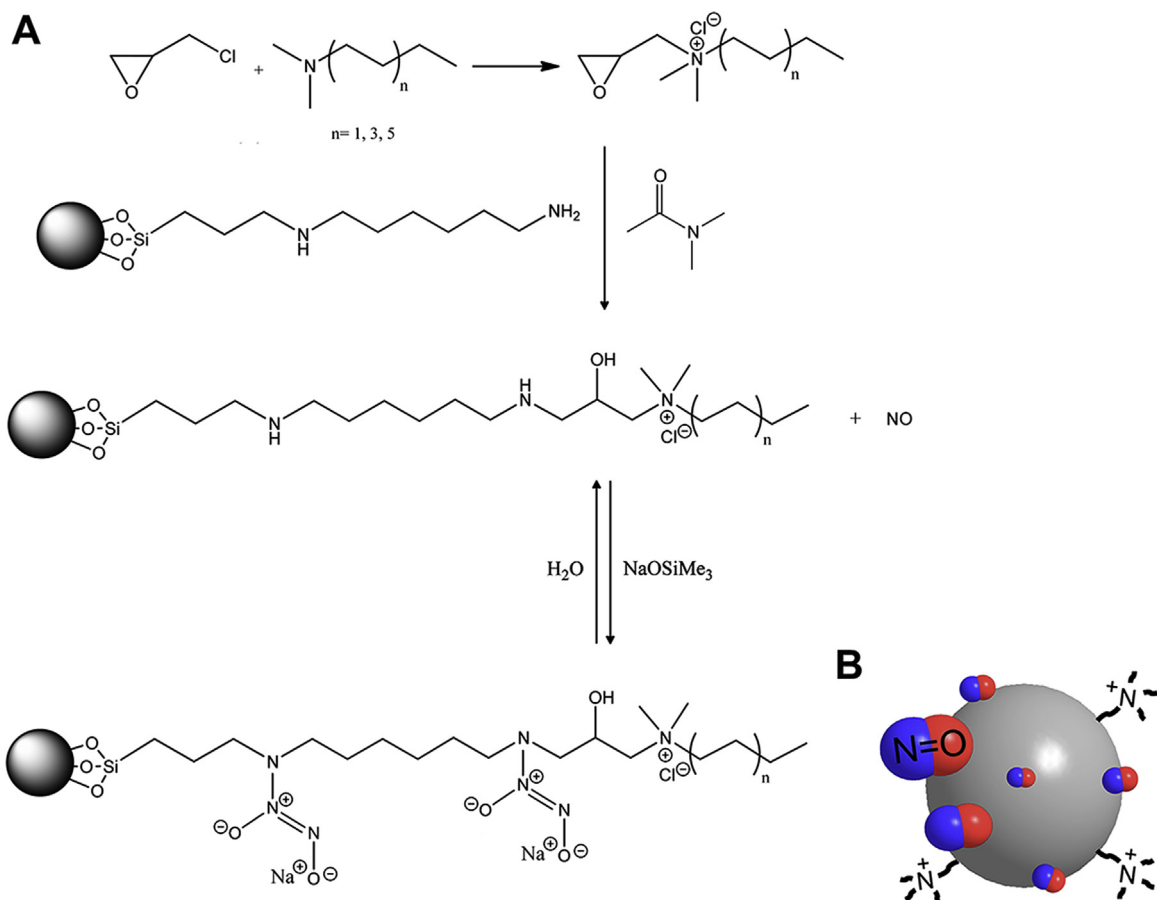


**Fig. 6.** Representative biomaterials grafted with QA-based polymers via ring-opening polymerization (ROP). A. Synthesis of nitric oxide (NO)-releasing QA-functionalized silica nanoparticles. B. Schematic illustration of nitric oxide (NO)-releasing QA-functionalized silica nanoparticles. [174], Copyright 2012.

Reproduced with permission from American Chemical Society.

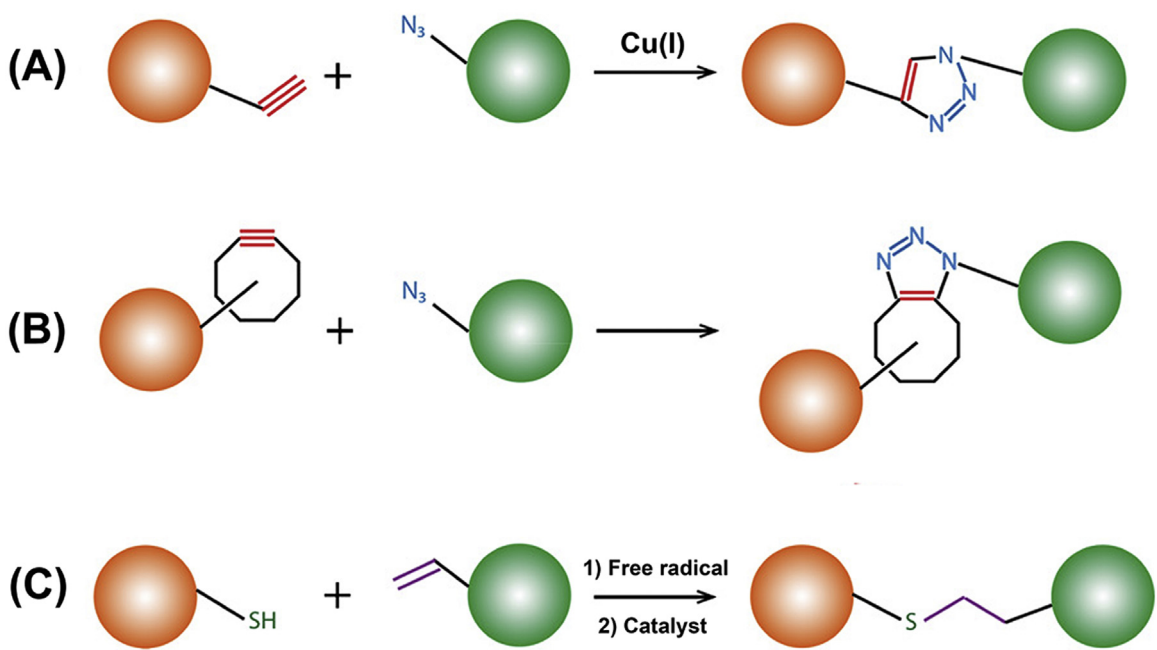

**Fig. 7.** Schematic illustration of reactions that best meet the criteria for a click reaction. A. Cu(I)-catalyzed azide-alkyne cycloaddition (CuAAC); B. Cu-free click cycloaddition; C. thiol-ene reaction. [183], Copyright 2011.

Reproduced with permission from Elsevier Science Ltd.

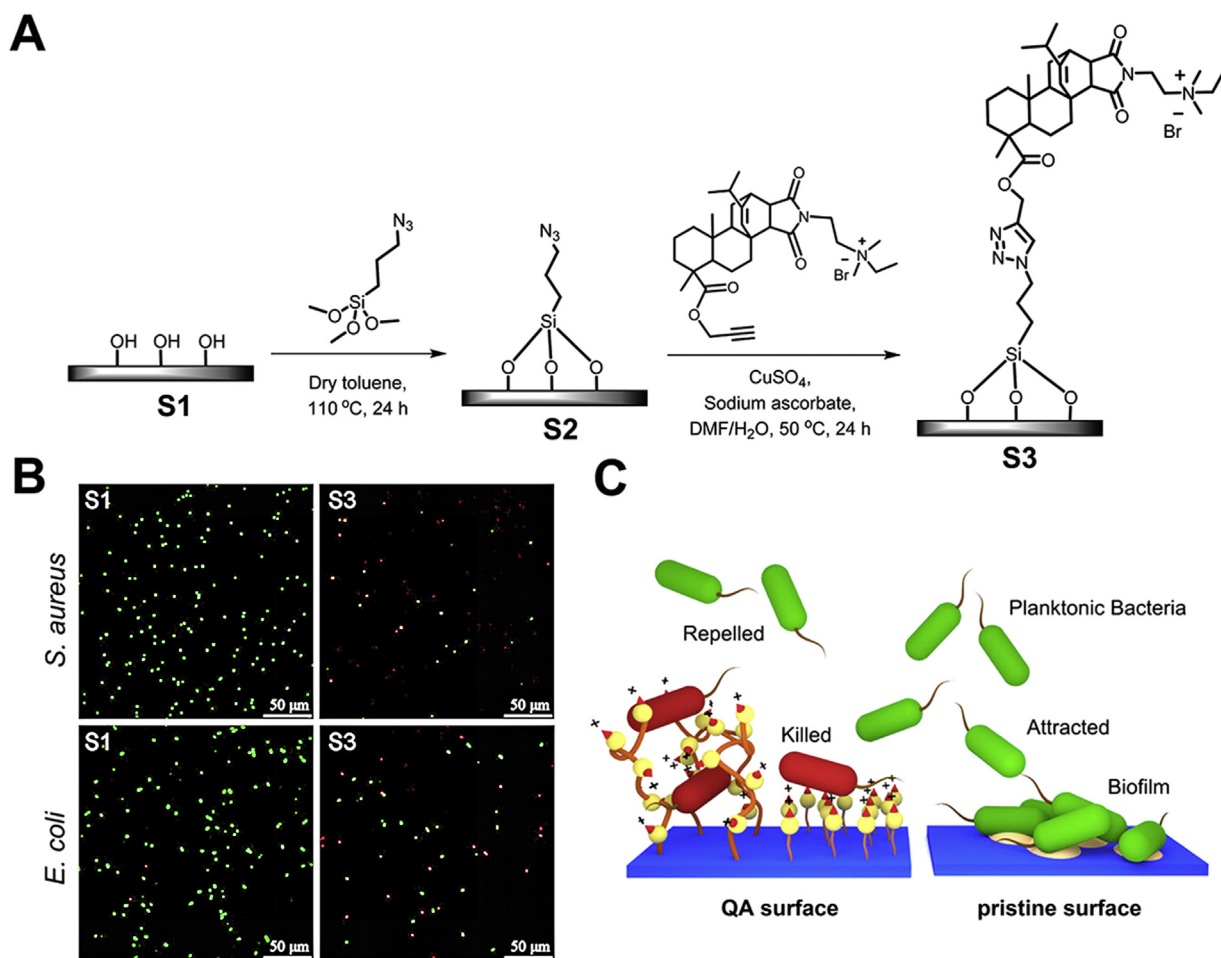

**Fig. 8.** Representative quaternary ammonium-based antimicrobial surfaces prepared by Cu-catalyzed azide–alkyne cycloaddition (CuAAC). A. Synthesis of antimicrobial surfaces. B. Stained (live/dead stain) surfaces after 24 h of incubation with *Staphylococcus aureus* and *Escherichia coli*. S1, pristine surface; S3, quaternary ammonium-based surfaces. Cells with green fluorescence indicate live bacteria colonizing the surface, while dead cells exhibit red fluorescence. C. Schematic representation of the antimicrobial activity of the QA surfaces. [188], Copyright 2015. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.) Reproduced with permission from American Chemical Society.

production of cations of p(DMAEMA), p(2-vinylpyridine) (2-VP) and p(4-VP).


An inherent limitation of CuAAC is the potential toxicity of catalyst Cu(I). To address this issue, Cu-free click chemistry has been developed [192]. Bertozzi et al. used strained alkynes (cyclooctynes) to facilitate strain-promoted cycloaddition of alkynes and azide (SPAAC) without a toxic catalyst [193], the reaction rate of which may be tuned by substituents on the cyclooctyne group. Copper-free click chemistry has attracted increasing interest in the fast-growing field of polymer and materials science because of its non-toxicity and biocompatibility. Applications of this strategy to QA surface modification have also been reported [194]. In that study, quantum dots were first modified with dibenzocyclooctynes (DBCO) to obtain DBCO-modified quantum dots. This was followed by SPAAC of the DBCO-modified quantum dots to azide-modified quaternized p(DMAEMA). Quaternary ammonium functionalized quantum dots possessed good antibacterial activity against *E. coli* and *S. aureus*, and exhibited no cytotoxicity on mammalian cells (Fig. 9).

Thiol-ene reaction has also been used for surface functionalization due to its efficiency, simplicity and high degree of conversion under mild conditions. Attachment of a molecule with a sterically accessible alkene or thiol group to a surface of interest enables surface functionalization via thiol-ene reaction. Tian et al. synthesized QA-functionalized antimicrobial wool fabric through

thiol-ene reaction. The wool fabric was first treated with tris(2-carboxyethyl)phosphine to produce thiol groups for subsequent reaction with the C=C groups of a QA salt [195]. The antimicrobial efficiency of the modified fabric against *E. coli* and *S. aureus* was 86.3% and 90.1%, respectively. In radical initiated polymerization, three distinct processes including initiation, polymerization and termination are involved in thiol-ene reaction [196]. In an ideal thiol-ene reaction, the combined propagation and chain transfer reaction proceed at equivalent rates and one thiol reacts with one-ene to produce an addition product. This inherent nature of the reaction results in homogenous and uniform end products. Photochemistry may also be used to initiate the thiol-ene reaction. For example, Wen et al. synthesized a series of QA-functionalized hyperbranched polyglycerols via ultraviolet light-initiated thiol-ene click chemistry [197] (Fig. 10). Compared with other methodologies such as thermal and redox initiation, the use of photoinitiation is particularly attractive because it allows both spatial and temporal control over the progress of the reaction.


#### 4. Orthopedics-related materials

Despite the adoption of stringent sterilization and aseptic procedures, biomedical material-associated infections remain a critical challenge in orthopedics. The incidence of peri-prosthetic infection is 0.5–5%, depending on the surgical site and the procedure

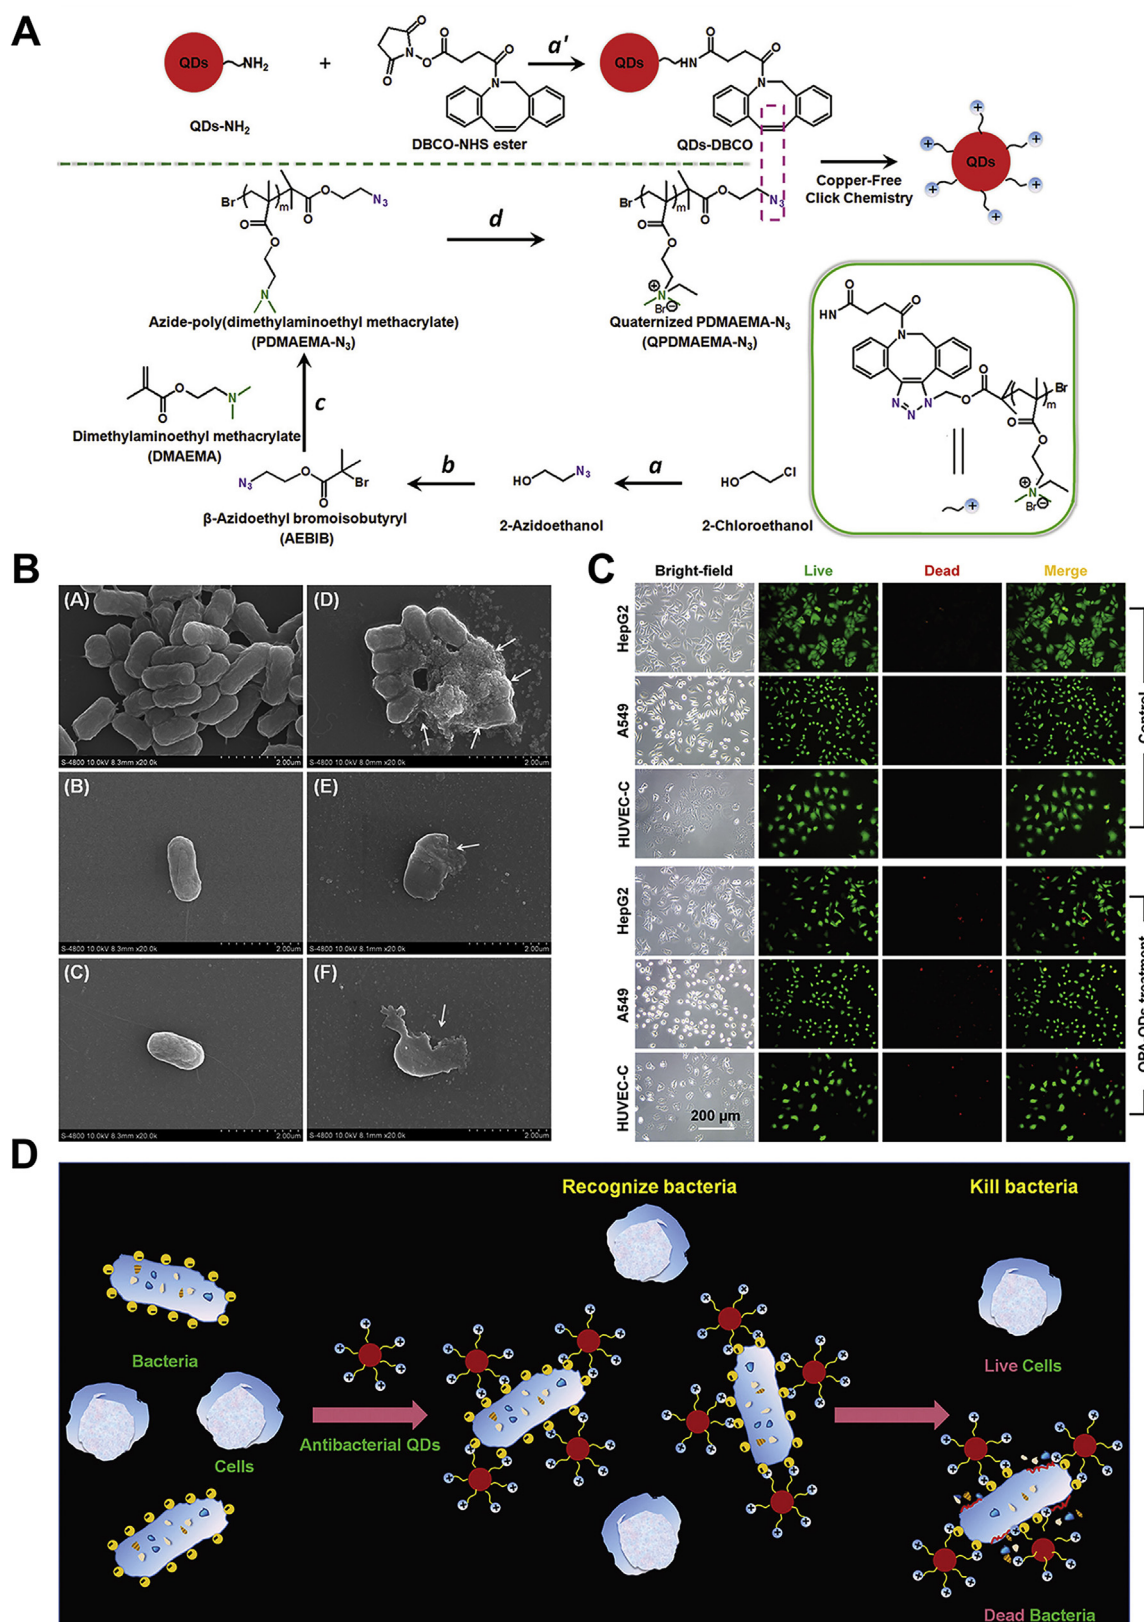

**Fig. 9.** Representative quaternary ammonium-based antimicrobial surfaces prepared by Cu-free click cycloaddition. A. Schematic of the synthesis of quaternary ammonium-functionalized quantum dots (QA-QDs). B. Representative scanning electron microscopy images of *Escherichia coli* incubated without (A–C) and with QPA-QDs for 20 min (D–F). C. Optical phase contrast images of cells double-stained with acridine orange and propidium iodide (AO/PI), after culturing with HepG2, A549, and HUVEC–C cells for 20 min with QPA-QDs (400 $\times$  magnification). Cells with green fluorescence indicate live cells, while dead cells displayed red fluorescence. [194], Copyright 2016. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

Reproduced with permission from The Royal Society of Chemistry.

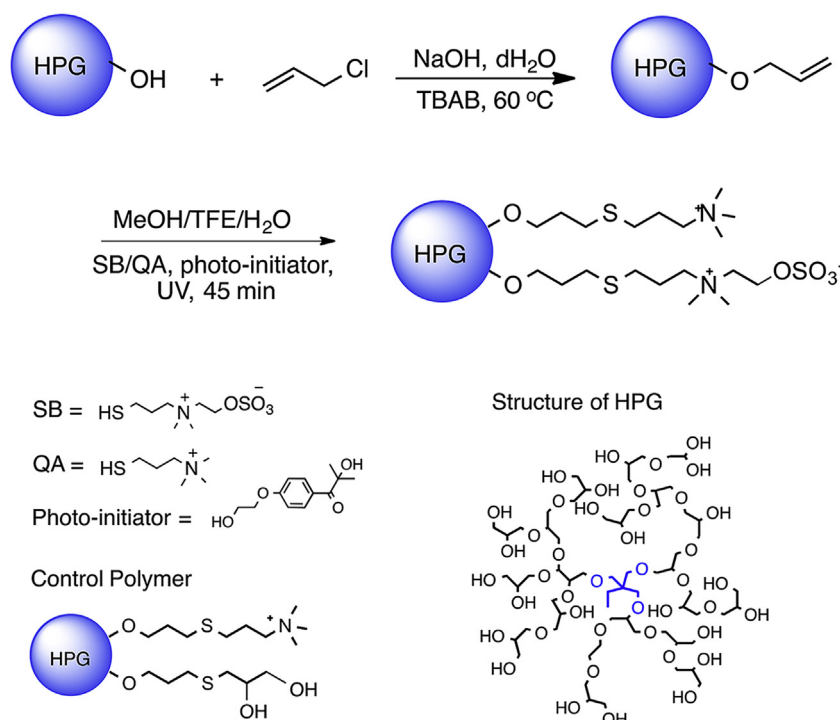

**Fig. 10.** Synthesis of sulfobetaine/quaternary ammonium modified, hyperbranched polyglycerols (HPGs) via ultraviolet light-initiated thiol-ene “click” chemistry. [197], Copyright 2016.

Reproduced with permission from The Royal Society of Chemistry.

undertaken [198]. Among the diverse microorganisms present, gram-positive pathogens are predominant in deep infections, predisposing individuals to pain, high treatment cost and reduced treatment success. Hence, biomedical materials with anti-infective properties are highly desirable in orthopedics to prevent potential infections, and to serve as local delivery systems for antimicrobial agents to treat deep bone infections (osteomyelitis). Controlled release of antibiotics such as gentamicin from bone cements and beads represent the current gold standard for local antibiotic delivery, for preventing infections after total joint replacement and for treating osteomyelitis [199–201]. Non-degradable poly(methyl methacrylate) (PMMA) bone cements and spacer beads loaded with antibiotics can release drugs from the cement over time with a high initial release rate followed by sustained release. Nevertheless, their use is also associated with drawbacks such as unpredictable long-term efficacy, potential antibiotic resistance and local tissue toxicity. These issues may compromise cell and bone regeneration and implant osseointegration [202,203]. The effectiveness of such devices is strongly dependent on the release rate of the loaded drugs [204]. In addition, long-term low-level release below the minimum inhibitory concentration of antibiotics following the “initial burst release” may contribute to the development of antibiotic-resistant bacteria strains.

Several publications support that the use of QACs in providing stable and permanent antimicrobial properties to bone cements (Table 5). Punyani et al. developed QA-based PMMA bone cements using a free radical bulk polymerization technique [205]. The bone cements exhibit a broad spectrum of contact-killing antimicrobial properties against *E. coli* and *S. aureus*. The modified cements and their eluants elicited negligible immune response and chronic inflammation in the host tissues [206]. These materials effectively kill bacterial cells attached to the cement surface. Incorporation of less than 15 wt% of these QACs to the bone cements results in no alteration of mechanical properties; the methacryloxy functionality renders these QACs polymerizable

with methacrylate bone cements. Compared with linear polymers, dendrimers have many advantages as antimicrobial agents. The controlled synthetic process produces final molecules with well-defined architectures. The specific spherical-shaped structure provides high surface functional group concentration [295]. Hyperbranched QAC-functionalized tripropylene glycol diacrylate (TPGDA) dendrimers have been incorporated into bone cements due to their large number of QA functionalities [208]. The modified cement can kill up to  $10^8$  CFU/mL of common hospital-acquired bacteria such as *E. coli*, *S. aureus* and *P. aeruginosa* by contact-killing, with sustained bactericidal activity over a 30-day period. These antimicrobial properties render the modified bone cement promising for combating infections related with prostheses and surgeries.

Quaternary ammonium polyethylenimine (QPEI) nanoparticles and quaternized chitosan derivatives are two examples of QA-functionalized fillers incorporated into PMMA bone cements. The QPEI nanoparticles have been used in various dental materials (see Section 6) because of their excellent antibacterial activities, mechanical properties and biosafety. Bone cements loaded with the nanoparticles retain effective antibacterial activity after a 4-week aging period, without altering the biocompatibility or mechanical properties of PMMA [209]. From a clinical perspective, PMMA bone cements loaded with 26 wt% hydroxypropyltrimethyl ammonium chloride chitosan (HACC), a quaternized chitosan derivative, prevent bacterial biofilm formation of antibiotic-resistant bacteria strains (methicillin-resistant *S. aureus* standard strains and clinically-isolated methicillin-resistant *Staphylococcus epidermidis*) and down-regulate virulence-associated gene expressions on the cement surface [209]. The HACC-loaded PMMA was found to induce better stem cell proliferation, osteogenic differentiation and osteogenesis-associated genes expression when compared with gentamicin-loaded PMMA because local release of antibiotics in bone cements suppresses osseointegration [210] (Fig. 11).

**Table 5**  
Quaternary ammonium-based biomedical materials, QA-based nanoparticles, and the combination of QACs and nanomaterials.


Applications		QACs	Microorganisms tested	Antibacterial methodologies	Details	Refs.
Orthopedics-related materials	Bone cements	QADMA	<i>E. coli</i>	Agar diffusion test, bacteria viability (colony counts), SEM	QADMA-modified bone cement showed contact killing antimicrobial properties without releasing any bioactive agents.	[207]
		QAMA	<i>E. coli, S. aureus</i>	Agar diffusion test, bacteria viability (colony counts), SEM	Inclusion of QAMA produced bone cements with antibacterial properties, lowered polymerization exotherm and comparable mechanical properties without evoking any cytotoxic response.	[205,206]
		TPGDA	<i>E. coli, S. aureus, P. aeruginosa</i>	Bacteria viability (colony counts), agar diffusion test	The novel dendritic structures showed promise for clinical antimicrobial activity while retaining the mechanical properties of bone cements.	[208]
		HACC	Clinical isolate <i>S. aureus</i> , clinical isolate <i>S. epidermidis</i> , <i>S. epidermidis</i> , methicillin-resistant <i>S. aureus</i> , methicillin-resistant <i>S. epidermidis</i>	Biofilm inhibition test, bacteria viability (colony counts) fluores, SEM, Real-time PCR, rabbit model, bacteria viability (colony counts)	PMMA bone cements loaded with HACC exhibited improved surface roughness and wettability, increased porosity and better attachment and spreading of human-marrow-derived mesenchymal stem cells on the cement surface. These cements also prevented bacterial biofilm formation and exhibited improved physical properties and better osteogenic activity than gentamicin-loaded PMMA. In a rabbit model, HACC-loaded PMMA inhibits <i>in vivo</i> bone infections induced by methicillin-resistant <i>S. epidermidis</i> , with no bone lysis, periosteal reactions, cyst formation and sequestral bone formation.	[65,209–212]
		QCS NPs	<i>S. aureus, S. epidermidis</i>	Bacteria viability (colony counts), biofilm inhibition test	Incorporation of the NPs in bone cements resulted in effective antibacterial action, and enhanced the antibacterial efficacy of gentamicin-loaded bone cements without compromising mechanical properties or causing cytotoxicity.	[213]
		QPEI NPs	<i>S. aureus, E. faecalis</i>	Direct contact test, agar diffusion test	Incorporation of QPEI nanoparticles in bone cements had a long-lasting antibacterial effect without compromising the cement's biocompatibility and physical properties.	[214]
Wound dressing materials	Titanium implant coatings	HACC	<i>S. epidermidis</i>	Bacterial viability (colony counts), rat model, SEM, CLSM	The antibacterial implant coating decreased infection rates associated with orthopedic implantation and promotes implant osseointegration.	[215]
	Sutures	2AE	<i>E. coli</i>	Bacterial viability (colony counts), agar diffusion test	The modified keratin substrate exhibited a multifunctional effect including antibacterial and antistatic properties, improved liquid moisture management property, improved dyeing ability and a non-leaching characteristic of the treated substrate.	[216]
		K21	<i>P. gingivalis, E. faecalis</i>	Agar diffusion test	K21-coated surgical sutures exhibited antimicrobial activity for bacterial species of direct relevance to postoperative infection and bacteremia.	[217]
		IDMA	<i>E. coli, S. aureus</i>	Agar diffusion test	The modified wool fabric showed good antibacterial and antistatic properties. Its mechanical properties were improved by the chemical bonds of the modification.	[195]
	Cotton fibers	SPH, SPODA	<i>S. aureus, E. coli</i>	Agar diffusion test	The cotton fabric coated with both SPH and SPODA exhibited antibacterial activity.	[218]
		GTAC, GTAC + AgNPs	<i>E. coli</i> , methicillin-resistant <i>S. aureus, P. aeruginosa, S. typhimurium</i>	Bacterial viability (colony counts), agar diffusion test	Cotton fibers treated chemically with GTAC and coated with AgNPs exhibited increased antibacterial efficacy, enhanced hydrophilicity but lower heat stability.	[219]
	Wound dressings and hydrogels	pDADMAC	<i>A. baumannii, P. aeruginosa, S. aureus</i>	Bacterial viability (colony counts), CLSM, SEM, bacterial migration test	The modified dressing inhibited growth and migration of bacteria.	[220]
		GTEACI	<i>S. aureus, E. coli</i>	Agar diffusion test, shaking flask test	The polyurethane membranes with appropriate loading of GTEACI showed biocompatibility, antibacterial activity, and possessed appropriate hydrophilicity and water vapor transmission rate.	[221]
		EPSiQA	<i>A. niger, B. subtilis, E. coli, S. aureus</i>	MIC determination	EPSiQA-gelatin had excellent antibacterial property.	[63]

Dental materials	Resin composites	Monomer 1	<i>S. aureus</i> , <i>E. coli</i> , <i>P. aeruginosa</i> , <i>C. albicans</i>	Bacterial viability (colony counts), FE-SEM	The quaternized hydrogels showed fast degradation at room temperature, with broad-spectrum antimicrobial activity. These properties made the modified hydrogels ideal candidates for wound healing and implantable biomaterials.	[176]
		GTMAC	<i>E. coli</i> , <i>S. epidermidis</i>	Shaking flask test, bacterial viability (colony counts), rat wound model	The efficiency in wound healing of the gel rendered it a promising material for treatment of full-thickness open wound.	[222,223]
		MDPB	<i>S. mutans</i> , <i>S. sobrinus</i> , <i>S. oralis</i> , <i>S. mitis</i> , <i>S. sanguis</i> , <i>S. gordonii</i> , <i>S. salicarius</i>	Agar diffusion test, bacteria viability (colony counts)	Resin composites with MDPB after curing possessed antibacterial activity on contact against bacteria, with no adverse effects on mechanical properties and curing performance.	[66,224–228]
		QPEI NPs	<i>E. coli</i> , <i>E. faecalis</i> , <i>P. aeruginosa</i> , <i>S. epidermidis</i> , <i>S. mutans</i> , <i>S. aureus</i> , human saliva	Direct contact test, agar diffusion test, <i>in vivo</i> model, SEM, bacteria viability (colony counts), CLSM	QPEI nanoparticles immobilized resin composite exhibited strong and long-lasting <i>in vitro</i> and <i>in vivo</i> antibacterial activity against a broad spectrum of bacteria, without leaching of the nanoparticles or compromising mechanical properties.	[229–231]
		QADM/ DMADDM/ DMAHDM + NACP	Human saliva, rat saliva	Dental plaque microcosm model, MIC and MBC determination, biofilm accumulation (MTT), bacteria viability (colony counts) flores, biofilm inhibition test, rat tooth cavity model	The nanocomposite exhibited antibacterial and remineralization potential <i>in vitro</i> without compromising load-bearing properties. Milder pulpal inflammation and more extensive tertiary dentin formation <i>in vivo</i> , indicating its potential to combat bulk tooth fracture, secondary caries, and facilitate the healing of the dentin–pulp complex.	[232–237]
		QADM + AgNPs + NACP	<i>S. mutans</i> , Human saliva	Biofilm accumulation (MTT), bacteria viability (colony counts)	The QADM + AgNPs + NACP composite possessed the double benefits of remineralization and antibacterial capabilities. The composite was found to be potentially useful for inhibiting dental caries with no adverse effects on mechanical properties. The anti-biofilm activity was maintained after 12 months of water-aging.	[238,239]
		QADM	<i>S. mutans</i>	CLSM	Incorporation of 10 wt% QADM reduced bacterial colonization, and increased the viscosity, degree of conversion and surface charge density.	[240]
		DDMAI	<i>S. mutans</i>	MIC determination, bacteria viability (colony counts), SEM	Incorporation of 5% DDMAI had no adverse effect on the conversion and flexural strength of the resin composite and provided radio-opaque and antibacterial effects.	[69,241,242]
		QADMAIs	<i>S. mutans</i>	Agar diffusion test, biofilm inhibition test	QADMAIs had no adverse impact on the degree of conversion and flexural strength. However, antibacterial activity, flexural strength, flexural modulus and radio-opacity were affected by the alky chain length of QAC.	[243]
		MAE-DB	<i>S. mutans</i>	Bacteria viability (colony counts), biofilm inhibition, RT-PCR	MAE-DB-containing resin blends exhibited long-term antibacterial effects after polymerization by attenuating <i>gtfB</i> expression and impairing membrane integrity.	[57,244]
		IPhene	<i>S. mutans</i>	Biofilm inhibition test	Incorporation of 30 wt% IPhene endowed dental resins with both antibacterial and radio-opacity, with lower flexural strength and modulus, lower volumetric shrinkage and higher fracture energy.	[245]
		QAB	<i>S. mutans</i>	MIC determination, bacteria viability (colony counts)	QAB-modified composites showed significant antibacterial activity. However, mechanical strength was reduced.	[70]
Monomer II	<i>S. mutans</i>	Biofilm inhibition test, FE-SEM	Resin composite containing 3% of monomer II significantly reduced against <i>S. mutans</i> biofilm formation without major adverse effects on its physical and mechanical properties.	[246]		

Table 5 (Continued)

Applications	QACs	Microorganisms tested	Antibacterial methodologies	Details	Refs.
Dental adhesives	QASM	<i>S. aureus</i> , <i>E. coli</i> , <i>S. mutans</i>	Agar diffusion test, direct contact test	Thiol–ene rich resins produced low shrinkage, homogeneous networks with adequate water uptake. Bactericidal activity was present on the matrix surface without sacrificing the physico-mechanical properties of the cured resin.	[247]
	IMQ-16	<i>S. mutans</i>	Biofilm Inhibition test, agar diffusion test, direct contact test	Incorporation of IMQ-16 into resin provided significant antibacterial activity and equivalent physicochemical properties.	[248,249]
	MDPB	<i>P. acnes</i> , <i>E. alactolyticum</i> , <i>B. bifidum</i> , <i>P. asaccharolyticus</i> , <i>L. acidophilus</i> , <i>L. arcasei</i> ssp, <i>L. plantarum</i> , <i>L. salivarius</i> ssp, <i>L. brevis</i> , <i>L. fermentum</i> , <i>L. casei</i> , <i>S. mutans</i> , dog saliva, human saliva	Agar diffusion test, bacterial viability (colony counts), MIC and MBC determination, biofilm accumulation, direct contact test, microcosm biofilm model, dog model, <i>in situ</i>	Antibacterial adhesive or primer containing MDPB before curing acted as effective cavity disinfectants to directly kill bacteria. After polymerization, the adhesive or primer exhibited long-lasting contact inhibition effects on bacteria contacting the cured surface, without diffusion of soluble components, or significant decline in bond strength or curing performance.	[62,224,250–258]
	DMAE-CB	<i>S. mutans</i> , <i>A. viscosus</i> , <i>S. aureus</i> , <i>L. casei</i>	Bacteria viability (colony counts), biofilm accumulation, RT-PCR, MIC and MBC determination, SEM	The modified dental adhesive had strong and long-lasting contact antibacterial activity after polymerization without negatively influencing bonding ability.	[58,59,259–261]
	DMAHDM, DMADDM	<i>S. mutans</i>	Bacteria viability (colony counts), biofilm inhibition test, SEM, EPS Staining, pH Measurement, RT-PCR	Increasing the alkyl chain length and quaternary amine charge density of dentin bonding agent resin greatly enhanced antibacterial and anti-biofilm activity without compromising dentin bond strength.	[68,262–265]
	QAMP	<i>S. mutans</i> , <i>L. casei</i> , <i>A. naeslundii</i>	MIC and MBC determination, bacteria viability (colony counts), agar diffusion test	The use of QAMP in an adhesive system demonstrated effective bond strength, acceptable degree of conversion, and long-lasting antibacterial effects.	[54,55]
	MDPB + AgNPs	Human saliva	Dental plaque microcosm model, bacteria viability (colony counts), agar diffusion test	Dual agents (MDPB + AgNPs) method yielded potent antibacterial properties without reducing dentin bond strength.	[266,267]
	QADM + AgNPs	<i>S. mutans</i> , human saliva	Bacteria viability (colony counts) fluores, biofilm inhibition test, RT-PCR, dental plaque microcosm model, agar diffusion test and inhibitory effects, TEM	Adhesive containing QADM and AgNPs had long-distance killing capability and inhibited bacteria on contact and away from its surface, without adversely affecting bond strength. Potential to inhibit secondary caries.	[268–271]
GICs and resin modified GICs	DMADDM + NACP	Human saliva	Dental plaque microcosm model, bacteria viability (colony counts), biofilm inhibition test	Bonding agent containing DMADDM and NACP inhibited biofilms and dramatically increased the Ca and P ion release at cariogenic pH 4, without affecting dentin bond strength.	[272]
	PQAS	<i>S. mutans</i> , human saliva	MIC determination, bacteria viability (colony counts)	The cement exhibited long-lasting antibacterial activity and high mechanical strength, indicating its clinical potential.	[44,273–275]
	DMADDM	Human saliva, <i>S. mutans</i>	<i>In situ</i> dental biofilm model, biofilm inhibition test, fluoride releasing, atomic force microscope, live/dead bacteria and EPS staining, lactic acid measurement, RT-PCR	The cement strongly inhibited <i>in situ S. mutans</i> biofilms and had the potential to improve the management of secondary caries.	[276,277]

	QPEI NPs	<i>S. mutans, L. casei</i>	Direct contact test, agar diffusion test	QPEI nanoparticles when incorporated in GICs at a low concentration (1%) exhibited strong antibacterial effect that lasted for at least one month.	[214]
Root canal sealers	MDPB	<i>E. faecalis, F. nucleatum, P. nigrescens</i>	Root canal infection model, bacteria viability (colony counts), bacterial adherence, MIC and MBC determination, agar diffusion test	The root canal filling system had the ability to effectively disinfect infected root canals and achieved good sealing.	[50,278,279]
	QAES NPs	<i>A. naeslundii, C. albicans, E. faecalis, S. mutans</i>	Direct contact test, biofilm inhibition test, bacteria viability (colony counts)	The root canal sealer possessed long-lasting antibacterial activity for both planktonic bacteria and biofilms.	[280,281]
	QPEI NPs	<i>E. faecalis</i> , clinical isolate <i>E. faecalis</i>	Direct contact test, membrane-restricted experiments, biofilm inhibition test, agar diffusion test, SEM	Addition of QPEI NPs improved the long-term antibacterial activity of root canal sealers without relevant changes in physicochemical and mechanical properties.	[282–284]
Pit-and-fissure sealants	DMAE-CB	<i>S. mutans</i>	Bacteria viability (colony counts)	Incorporation of DMAE-CB provided the sealant with contact-like antibacterial activity without negatively influencing physicochemical and mechanical properties.	[285]
	MAE-DB	<i>S. mutans</i>	Bacteria viability (colony counts), CLSM	Incorporation of MAE-DB rendered the sealant with contact antibacterial activity after polymerization by influencing the growth, adherence and membrane integrity of <i>S. mutans</i> .	[286]
Pulp capping materials	MAE-DB	<i>S. mutans</i>	Bacteria viability (colony counts), biofilm accumulation	Pulp capping materials with strong and long-lasting contact-killing antibacterial activity <i>in vitro</i> .	[287]
Acrylic resin	QAMS	<i>S. mutans, A. naeslundii, C. albicans</i>	Bacterial viability (colony counts), CLSM, RCT	QAMS-containing acrylic resins exhibited long-lasting antimicrobial activities, decreased water wettability and improved toughness, without adversely affecting the flexural strength and modulus, water sorption and solubility. The acrylic resin had the potential for preventing bacteria- and fungus-induced stomatitis.	[288–291]
	MUPB	<i>C. albicans, C. dubliniensis, C. glabrata, L. casei, S. aureus, S. mutans</i>	MIC and MBC determination, bacterial viability (colony counts), bacterial adherence	Antimicrobial activity of MUPB after incorporation in a denture base acrylic resin was not dependent on elution of the antimicrobial monomer. Incorporation of MUPB slightly reduced the mechanical properties of denture base acrylic resin.	[64,292]
	QCS	<i>S. mutans, C. albicans</i>	Bacterial viability (colony counts)	Chitosan quaternary ammonium salt-modified resin denture base materials showed antimicrobial properties, without significant reduction in their tensile strength and cytotoxicity.	[293]
Dental implants	DCAMA	<i>S. aureus</i>	Bacterial adherence, CLSM	The coatings demonstrated antibacterial activity against bacteria adherent to the surface but exhibited poor cyto-compatibility.	[294]

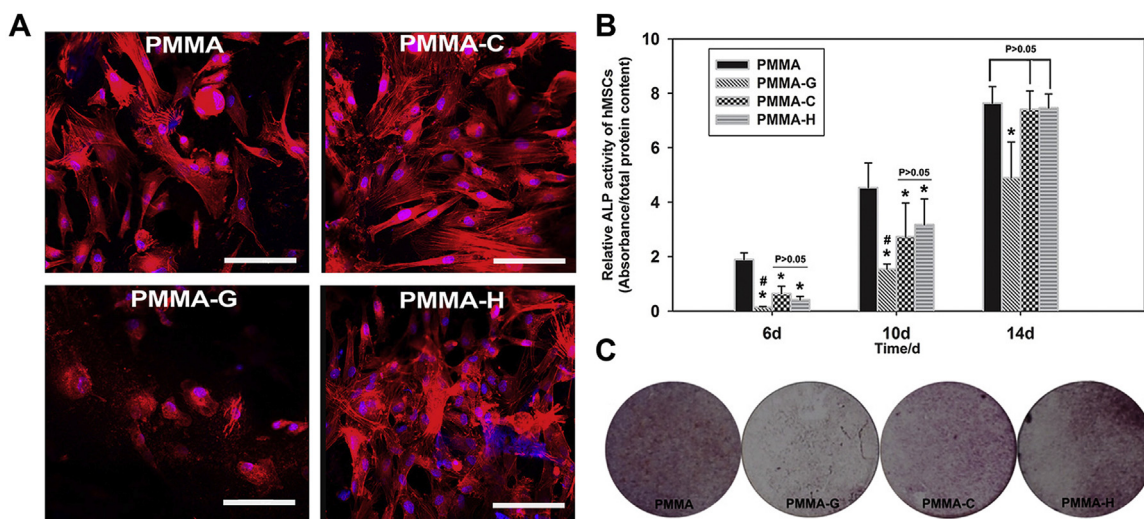

**Fig. 11.** A. Cytoskeletal morphology of human mesenchymal stem cells (hMSCs) exposed to different polymethyl methacrylate (PMMA)-based bone cements. B. Relative alkaline phosphatase activity (indicative of bone forming potential) of hMSCs after 6, 10, and 14 days of culture. For each time period, columns connected with a horizontal bar are not significantly different ( $P > 0.05$ ). C. Representative images showing hMSCs with positive alkaline phosphatase staining on the four PMMA-based bone cements at day 14. PMMA-C: chitosan-loaded PMMA; PMMA-G: gentamicin-loaded PMMA; PMMA-H: hydroxypropyltrimethyl ammonium chloride chitosan (HACC)-loaded PMMA. [210]. Copyright 2012.

Reproduced with permission from Elsevier Science Ltd.


The favorable results achieved by HACC-loaded PMMA may be attributed to improved surface roughness and wettability, increased porosity and better attachment and spreading of human-marrow-derived mesenchymal stem cells on the cement surface. In a rabbit model, HACC-loaded PMMA inhibits *in vivo* bone infections induced by methicillin-resistant *S. epidermidis*, with no bone lysis, periosteal reactions, cyst formation and sequestration of non-vital bone [211,212]. The quaternized chitosan derivative may also be immobilized on titanium implant surfaces via silanization with aminopropyltriethoxysilane [215]. Incorporation of silyl groups enables covalent attachment of the quaternized chitosan derivative on the metal or hydroxylated surfaces, while the QA group exerts long-term antibacterial activity. Titanium surfaces modified with HACC prevent bacteria attachment *in vitro* and reduce infection *in vivo*. The coated titanium implants are well-integrated with the surrounding bone without bacterial growth. Nevertheless, clinical trials and FDA approval are required before clinical translation and commercialization of this technology can be successfully achieved.

Incorporation of both contact-based biocides such as QACs, and release-based biocides such as AgNPs [296,297] or silver bromide (AgBr) NPs [298] produces surfaces with dual-functional antibacterial activities. This strategy is of particular interest in orthopedic operations because of its unique antibacterial characteristics. Dual-functional coatings exhibit potent initial antibacterial properties due to the release of bioactive biocides and maintain long-term antibacterial activities via the immobilized QA groups. The first 6 h after surgical implantation is highly susceptible to bacterial invasion and surface colonization, and has been coined the “decisive period” [299]. A high initial burst release offers protection against the initial elevated risk of infection, while sustained contact-killing provides surveillance against subsequent latent infections.

## 5. Sutures and wound dressings

Wound management is a critical healthcare component that has attracted much global concerns. Sutures are used to approximate tissues to facilitate closure and healing of wounds [300]. Bacteria attachment and proliferation on suture materials are significant risk factors for wound infections [301]. Wound dressings generally

consist of bilayer structures, including an upper dense “skin” layer and a lower spongy layer. Although dressings are designed to protect the wound against microorganisms [302], the wounded site in the vicinity of the dressing provides a favorable environment for bacterial growth. Intensive research has been conducted on antibacterial modification of wound dressings to prevent infections and provide an optimal milieu for tissue regeneration [303,304]. These antibacterial materials are produced predominantly by electrospinning [305]. Sustained broad-spectrum antimicrobial activity is desirable for optimal wound healing because complex tissue interactions between cells, extracellular matrix molecules and soluble mediators are involved in the regeneration of damaged skin or other tissues. Previous studies reported addition of small molecule QACs such as benzalkonium chloride, *N,N,N,N*-didecyl-*N,N*-dimethylammonium chloride to polymer solutions for electrospinning of antibacterial nanofibers [306,307]. Such methods suffer from drawbacks such as reduction in fiber diameter and a burst release of QACs. Compared with the attachment of QACs to a wound dressing through ionic absorption, immobilization of QA moieties on the dressing surface via covalent bonding provides long-term antibacterial protection and eradication of bacteria by contact-killing (Table 5). Various polymerization techniques including layer-by-layer assembly, click chemistry, FRP and CRP have been employed [308–310]. For example, Dan et al. reported the preparation of antimicrobial keratin fibers for medical applications through thiol-ene click chemistry [216]. The presence of QA moieties on keratin structures was confirmed with Raman and infrared spectroscopy. The modified sutures exhibit excellent antimicrobial activity, antistatic property and significantly improved moisture management capability. Sutures and dental floss that were coated with the QA compound “K21” demonstrated dose-dependent antibacterial activities against the periodontal pathogen *P. gingivalis* and the endodontic pathogen *Enterococcus faecalis* [217]. Liu et al. found that compared with traditional pad-dry-cure process, QA-functionalized cotton fabric prepared using a pad-dry process showed a relatively higher antibacterial efficacy [218]. The phenomenon may be attributed to increased hydrophobicity of the coated samples under high coating temperature in the pad-dry-cure process. Recently, Kang et al. reported improved

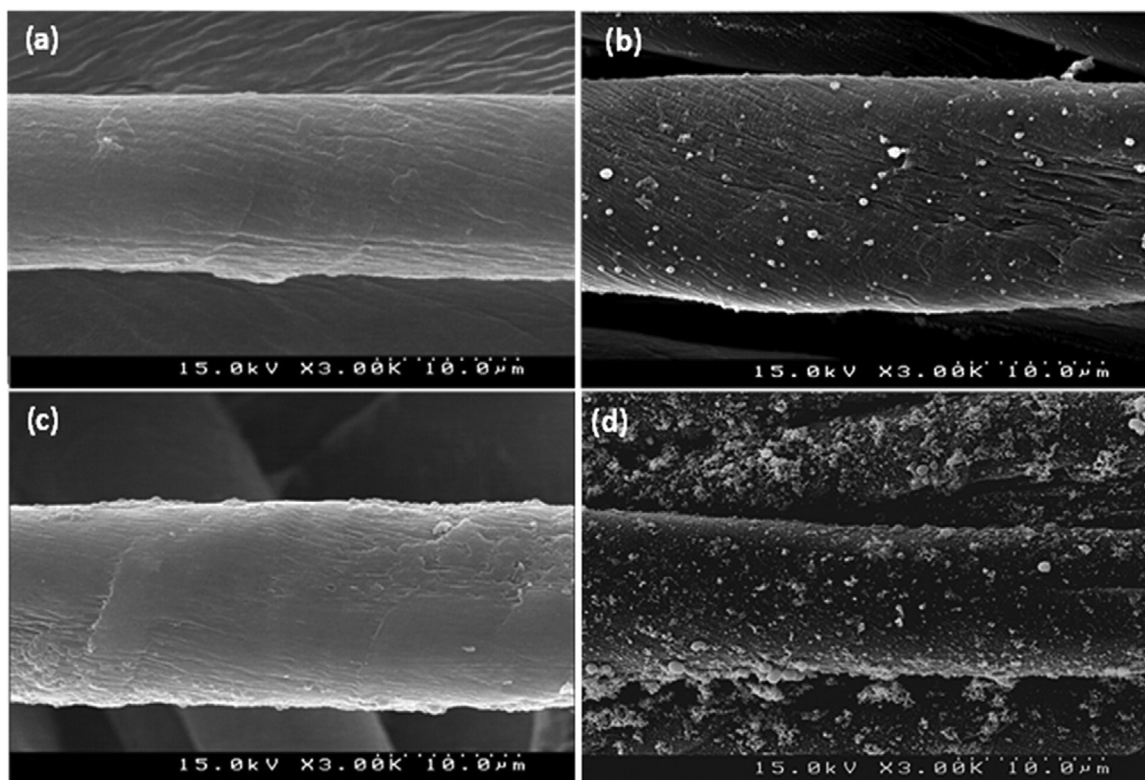

**Fig. 12.** Representative scanning electron microscopy images of A. Untreated cotton; B. Cotton treated with silver nanoparticles (AgNPs). C. Cotton treated cotton with quaternary ammonium compound. D. Cotton treated with quaternary ammonium compound and AgNPs. [219], Copyright 2016. Reproduced with permission from Elsevier Science Ltd.

antibacterial efficacy in antimicrobial cotton fibers that are chemically treated with glycidyltrimethylammonium chloride and AgNPs [219] (Fig. 12). In addition, the coated fibers exhibit increased moisture regain as a result of the enhanced hydrophilicity.


Attempts have also been made to incorporate QA groups into wound dressing materials. Attachment of QA groups to a polyurethane foam wound dressing [220] resulted in inhibition of biofilm development of three major wound pathogens (*S. aureus*, *P. aeruginosa* and *Acinetobacter baumannii*) both within the wound and in the wound dressing. Wound healing requires a moist and warm environment, and dressing materials with good air permeability and moisture absorption are desirable. Novel QA-containing polyurethane membranes used as wound dressings exhibit antibacterial activity against *S. aureus* and *E. coli* [221]. The modified antibacterial dressings exhibit good biocompatibility for fibroblasts and epidermal keratinocytes. More importantly, the modified dressings possess excellent water vapor transmission to prevent accumulation of exudates and decrease surface inflammation within the wounded area. Hydrogels based on synthetic or natural polymers may be used as wound dressings to locally deliver a wide range of bioactive agents in a controlled and sustained manner to regulate stem cells that are encapsulated within the three-dimensional polymer network [311]. Because of their biocompatibility, low immunogenicity and rapid hydrolysis under physiologic conditions, some hydrogels have been commercialized for clinical use [312]. Recently, a gelatin hydrogel grafted with an epoxy silicone QA salt exhibits excellent antibacterial property against Gram-positive and Gram-negative bacteria, including *S. aureus*, *E. coli* and *Bacillus subtilis* [63]. The quaternized polycarbonate hydrogels have been successfully synthesized via ROP [176]. In addition to their broad-spectrum antimicrobial activity, the gels showed fast degradation at room temperature (4–6 days). This makes them promising for incorporation into wound healing and

implantable biomaterials. Pilakasiri et al. found that QA-modified chitin gels are promising candidates for treatment of full-thickness open wounds, with better wound healing than a clinically available dressing [223].

## 6. Dental materials

Dental caries is one of the most prevalent bacteria-related human infectious diseases [313]. During the development of dental caries, acidogenic and aciduric bacteria such as *Streptococcus mutans* accumulate on teeth and/or dental fillings and cause demineralization of enamel and dentin via acid generation [314]. Following demineralization, salivary proteases or endogenous peptidases such as MMPs and cysteine cathepsins induce degradation of the demineralized collagen matrix [315]. To address the growing need for antibacterial dental materials, a useful approach is to permanently copolymerize QACs with resin materials by forming covalent bonds with the polymer network. Such stable non-leaching antibacterial materials can provide long-term protection via contact of the microorganisms with the biocidal surface, without sacrificing the mechanical properties and polymerization behavior of the original non-antibacterial resin formulations [70,226]. In particular, QA-based resin materials exhibit good biocompatibility that is evidenced by minimal toxicity, allergenicity and tissue irritability [51]. Based on the aforementioned advantages, QACs are considered highly desirable for managing and combating dental caries.

The first synthetic QAC to be incorporated in antibacterial dental materials is 12-methacryloyloxy dodecyl pyridinium bromide (MDPB) [66]. Polymerized dental adhesives containing MDPB significantly exhibit contact-killing effects on *S. mutans* when these bacteria come into contact with the specimens' surface [253]. Composites incorporated with MDPB exhibit long-term

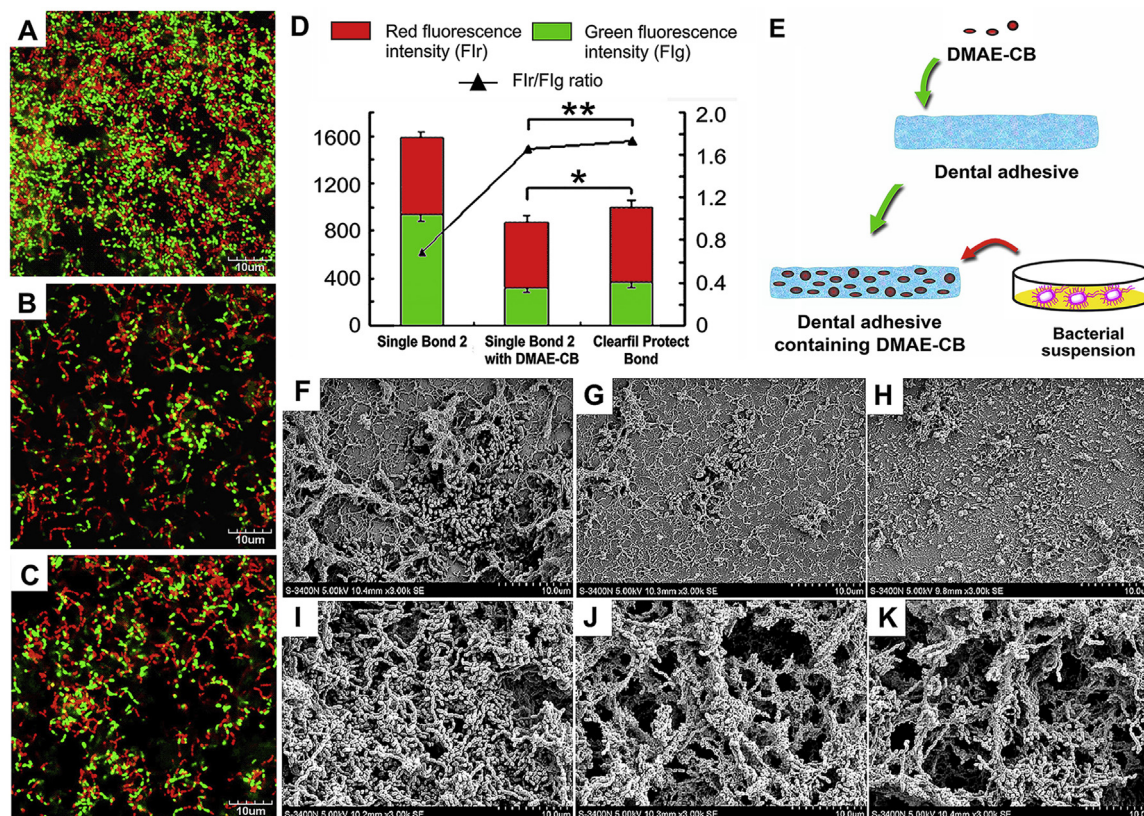

**Fig. 13.** Antibacterial activity of polymerized dental adhesives containing MDPB or DMAE-CB. A–C. Representative confocal laser scanning microscopy images of *Streptococcus mutans* adhered on the control adhesive (A), adhesive containing MDPB (B) and adhesive containing DMAE-CB (C) after 24-h incubation. Bacteria with integral membranes were stained with green fluorescence and those with compromised membranes were stained with red fluorescence. D. Fluorescence intensity values of the two channels for adhesives derived from the three groups. E. Schematic representation of polymerized adhesive containing DMAE-CB. F–H. Representative scanning electron microscopy images of *Streptococcus mutans* biofilms on the control adhesive (F), adhesive containing MDPB (G) and adhesive containing DMAE-CB (H) after 4-h incubation. I–K. Representative scanning electron microscopy images of *Streptococcus mutans* biofilms on the control adhesive (I), adhesive containing MDPB (J) and adhesive containing DMAE-CB (K) after 24-h incubation. [260], Copyright 2009. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.) Reproduced with permission from Elsevier Science Ltd. [259], Copyright 2009, Reproduced with permission from International & American Associations for Dental Research.

antibacterial activity without eluting antibacterial components. Dental materials containing methacryloxyethyl cetyl ammonium chloride (DMAE-CB) exhibit strong, fast and long-term killing effects [58,261] (Fig. 13). Adhesives incorporating DMAE-CB suppress the expression of glucosyltransferase genes which contribute to plaque biofilm accumulation [259,260]. The application of QACs in dental materials has been published in several reviews [316,317]. These discoveries led to the development of various kinds of non-releasing antibacterial dental materials including resin composites, adhesives, glass ionomer cements and resin-modified glass ionomer cements, root canal sealers, pit-and-fissure sealants, pulp capping materials, acrylic resin dentures, orthodontic retainers, denture lining materials and dental implants (Table 5).

Over the last decade, researches on QACs have benefited from ground breaking advancements in organic and inorganic chemistry as well as materials science. These improvements have contributed to the introduction of strategies to develop innovative QACs with improved properties. Theoretically, antibacterial materials incorporated with more QACs provide better antimicrobial activities. However, the capability of a resin polymer network to copolymerize with QACs is limited (e.g. only 5 wt% MDPB and 3 wt% DMAE-CB are employed in adhesives). Incorporating too high concentrations of these mono-methacrylates (i.e. QACs with one methacrylate group) beyond the polymerizable capability of the resin polymer network may adversely affect its structural and mechanical properties. To address these problems, QACs with two methacrylate

groups have been developed for incorporation in antibacterial dental materials [57,240,244,287,318].

In the investigation of the structure-property relationship of QACs [67,68], those with a chain length of 12 or 16 were found to possess higher antibacterial potency. Due to the high electron density of iodine, substitution of the halogen anions in QACs with iodine as the counter ion results in radiopaque antibacterial monomers [69,241–243,245].

Most of the reported QACs have only antibacterial effects. Apart from bacteria, fungi play an important role in oral cavity infections such as denture-related stomatitis. Co-colonization of *S. mutans* and *Candida albicans* in the form of mixed dental plaque biofilms can occur on the surface of removable orthodontic appliances or removable dentures [319,320]. Recently, quaternary ammonium methacryloxy silicate (QAMS) has been developed with both antibacterial and anti-fungal properties for incorporation into dental removable appliances fabricated from acrylic resin (i.e. PMMA) [288–290]. In those *in vitro* studies, acrylic resin containing 5 wt% QAMS exhibits contact-killing microbiocidal activities on *S. mutans*, *Actinomyces naeslundii* and *C. albicans* single species biofilms. Thus, QAMS has the potential for fabrication of antibacterial/anti-fungal partial/full denture bases, as well as for preparation of removable orthodontic appliances and retainers.

Polymerization shrinkage stresses and strains are generally considered the most pertinent issues associated with the clinical use of resin-based dental filling materials. These stresses and

resulting strains may contribute to crack propagation in the filling material, leakage along the tooth-filling interface, bacterial invasion and secondary caries [321,322]. Burujeny and colleagues fabricated thiol-ene-methacrylate containing quaternary amine moieties with reduced polymerization shrinkage stress and strain and improved antibacterial effectiveness [247]. Reduction in polymerization shrinkage has been attributed to the nature of thiol-ene polymerization; delayed gelation produces more homogeneous structure with narrow glass transition temperature ranges and reduced brittleness in comparison with classic methacrylate resin systems [323,324]. In addition, the presence of flexible thiol-ether linkages provide a better opportunity for exposure of reactive quaternary amine groups on the surface of the polymerized resin matrix, which, in turn, provides better bactericidal function.


Biomedical materials have evolved with the advent of nanotechnology, making it possible to develop antibacterial dental materials with QAC-functionalized nano-fillers. Quaternary ammonium polyethylenimine (QPEI) nanoparticles are effective against a variety of Gram-positive and Gram-negative bacteria, including clinical isolates of pathogenic bacteria and bacteria in contaminated water [325,326]. The antimicrobial potency of these nanoparticles is attributed to the abundance of QA groups along its backbone. The QPEI is a synthetic, non-biodegradable, cationic polymer with primary, secondary and tertiary amine functionalities, which may be subjected to a wide range of chemical modifications to produce desirable physicochemical properties [16]. Because of the small size and large surface area of the nanoparticles, as well as their capability to release high concentrations of ions with low filler content, only a small amount is required for incorporation into dental materials. Incorporation of low concentration of these nanoparticles (1–2 wt%) into dental materials [229,230,282,284,327] provides potent and broad-spectrum antimicrobial effects. Silane-quaternary amine-based antimicrobials, generally consisting of an organic shell with antimicrobial functionality and a silica core with high colloidal stability, have been shown to be effective antimicrobial fillers for more than 40 years [328]. Reactive silane functionalized antimicrobial agents are resistant to microbial growth and biofilm formation. These antimicrobial agents also possess other benefits, including tunable surface functionality, low cytotoxicity and easily controllable size. Hence, they are widely used in the field of antimicrobials [329–331]. Silica-quaternary ammonium QPEI nanoparticles, prepared by surface modification of silica particles with QA groups, distribute more homogeneously in the polymeric coatings, with less nanoparticle aggregation when compared with QPEI nanoparticles [332]. For example, quaternary ammonium epoxy silicate nanoparticles applied as QA compounds conjugated to organosilanes and silica nanoparticles, and also to epoxy silicates, were synthesized by a silane-based sol-gel reaction and incorporated into an epoxy resin-based root canal sealer. The sealer exhibited antimicrobial activities against *E. faecalis* biofilms [281]. Resins incorporating functionalized silica nanoparticles possess sufficient antimicrobial activity as well as high strength and modulus of elasticity values even at low filler concentrations [333].

Dental materials with both QACs and nano-sized antibacterial agents incorporated into one system operate with dual functions [334]. For example, incorporation of both QACs and AgNPs can effectively kill bacterial both on (contact-based killing) and away from the surface of the materials (release-based killing) [268,269]. The AgNPs are small enough (mean diameter 40 nm) to infiltrate dentinal tubules to kill residual intratubular bacteria [270]. Incorporation of nanoparticles of amorphous calcium phosphate (NACPs) into QAC-based dental materials bestows those materials with remineralization capabilities for reversing the tooth decay process [335]. The QAC-based nanocomposites and adhesives containing NACPs possess “smart” properties by increasing Ca and P

ion release at low cariogenic pH values, when these ions are most needed for inhibiting caries, neutralizing the demineralization of enamel and dentin by lactic acid, and preventing caries formation [332]. However, one should be careful in balancing the antibacterial effects of those nano-fillers with their cytotoxicity due to latent nanoparticles-related toxicity.

Although *in vitro* models have been adopted by researchers for initial screening of new materials and techniques for developing QACs and to justify their potential for clinical applications, there are other *in vivo* factors that cannot be duplicated in *in vitro* studies. To date, the majority of the work performed on the antimicrobial properties of QACs is *in vitro* nature. Although the recent use of multi-species oral biofilm models has contributed to the understanding of intraoral microbial adhesion and biofilm formation, these models are unlikely to simulate the variability and *in vivo* dynamics of dental plaque biofilms. For example, the antibacterial and immunoregulatory effects of antimicrobial peptides such as  $\alpha$ - and  $\beta$ -defensins, and the cathelicidin LL-37 in the oral cavity, as well as histatins derived from the saliva cannot be neglected [336,337]. Other factors include the role of saliva in slowing down tooth decay by neutralizing plaque acids [338]. In addition, saliva-derived protein films can be adsorbed on dental restoration surfaces and provide anchoring sites for bacteria [339], block functional antibacterial groups on the material surfaces, thereby reducing the antibacterial activity of QA-based materials. Indeed, several publications show that the presence of a saliva-derived protein film (i.e. pellicle) on the surface of QA-based materials reduce their bactericidal effects [224,340]. Because pre-coating of salivary pellicles on resin surfaces significantly decreases the antibacterial effects of polymerized antibacterial resins, *in vivo* and *in-situ* models are highly desirable for evaluating treatment outcomes, which, unfortunately, are desperately lacking. Animal models have been developed for comparing the functional efficacy of QA-based dental materials. Generally, those animal models were designed to examine: a) the biocompatibility of the materials (pulp response and reparative dentin formation) [341]; b) the presence of bacteria within the intraradicular dentin [254]; c) bonding ability using QA-based dental adhesives [256] and restorative materials. Using a rat tooth cavity model, QA-based NACP-containing nanocomposites and adhesives were found to combat oral pathogens and biofilms effectively and facilitate healing of the dentin-pulp complex [234] (Fig. 14).

It must be pointed out that data derived from animal studies are somewhat different from the clinical effects experienced by humans. Apart from differences in structural characteristics between *in vitro* and *in vivo* biofilms, the presence of host defenses such as antimicrobial peptides derived from saliva is seldom taken into account in *in vitro* multi-species biofilm models [342]. Plaque biofilm profiles vary among individuals because they are modulated by different environmental factors as well as quorum sensing signals derived from adjacent microorganisms [343–345]. These confounding factors may temper the efficacy of antimicrobial polymers *in vivo*. In the contemporary world of evidence-based medicine and dentistry which demands the conscientious, explicit and judicious use of current best evidence in making decisions about the care of individual patients [346], it is crucial to ensure that QACs that have been tested *in vitro* have equivalent antimicrobial potential in *in vivo* settings before they are marketed commercially as “antimicrobial dental materials”. Moreover, clinically relevant *in-situ* models are required to validate the effects of novel antibacterial dental materials. Double-blind randomized control clinical trials remain the gold standard in evaluating treatment outcomes [347,348]. In a case-controlled observational mini-study (ClinicalTrials.gov: registration number NCT00299598), ten volunteers wore removable acrylic appliances with two control resin composite specimens and two resin composite specimens incorporating

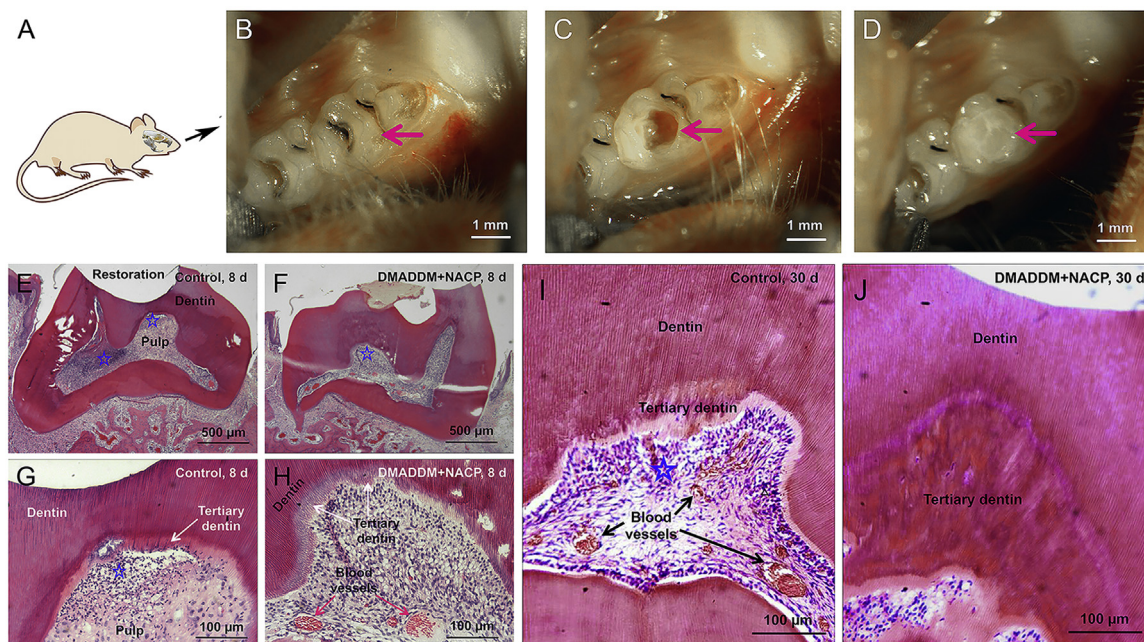

**Fig. 14.** Evaluation of antibacterial and remineralizing nanocomposite and adhesive containing nanoparticles of amorphous calcium phosphate (NACP) and dimethylaminododecyl methacrylate (DMADDM) in a rat tooth cavity model. A. Schematic representation of rat tooth cavity model. B. Rat right and left molar teeth were used. C. Occlusal cavity was prepared. D. Cavity was restored with adhesive and nanocomposite and light-cured. E–H. Histological analyses of rat tooth cavities at 8 days in the control group (E and F) and the DMADDM + NACP group (G and H). The same four groups at a higher magnification. The control group exhibited disruption of the odontoblast layer associated with a medium inflammatory response in the pulp. Blood vessels are observed and a thin layer of tertiary dentin can be identified. The DMADDM + NACP group has normal pulp tissues, with much thicker tertiary dentin (a type of reparative dentin) than the control. Stars indicate areas with inflammatory cell infiltration. I and J. Representative hematoxylin and eosin-stained images at 30 days in control group (I) and the DMADDM + NACP group (J). Stars indicate areas with inflammatory cells. Blood vessels are indicated by arrows. The control group exhibits slight inflammatory responses. The DMADDM + NACP group shows normal pulp tissue without inflammatory response, and greater tertiary dentin thickness. [234], Copyright 2014.

Reproduced with permission from Elsevier Science Ltd.


1 wt% QPEI nanoparticles for 4 h to develop intraoral biofilms [230]. The vitality of biofilms on QPEI-containing specimens was reduced by more than 50%, while those grown on the control resin composite discs were predominantly viable. No inflammation or allergic reaction developed after wearing of the appliances containing the experimental specimens. Recently, a double-blind, randomized clinical trial (RCT) was conducted to examine the *in vivo* antimicrobial efficacy of QAMS-containing orthodontic acrylic (ClinicalTrials.gov: registration number NCT02525458) [291]. The trial involved intraoral wearing of custom-made removable retainers by thirty-two human subjects to create 48-h multi-species plaque biofilms, using a split-mouth study design. Using confocal laser scanning microscopy, it was found that incorporation of 5 wt% QAMS in a PMMA-based orthodontic acrylic resin enables killing of microorganisms in the plaque biofilms without harm to the oral mucosa or systemic health (Fig. 15).

It was previously perceived that polymerized “contact killing” antibacterial resin polymers exhibit antimicrobial activities only via direct contact of bacteria, without antibacterial effects against planktonic (free-floating) bacteria [349]. However, recent studies of QA-containing materials conducted with confocal laser scanning microscopy and three-dimensional reconstruction of biofilms stained with live–dead fluorescent stains [350,351] indicate that those materials possess a reducing spectrum of biocidal activities from the substrate surface to the top of the biofilms [230,288,289,352,353]. That is, the presence of dead microorganisms is not limited to the bottom of the biofilms that is in contact with the antibacterial surface. This phenomenon may be explained by the ability of bacteria to undergo quorum-sensing signaling-induced programmed cell death in responses to environmental stresses [354,355]. Activation of altruistic cell death mechanisms stimulates the release of pheromones such as the toxin component

of toxin–antitoxin systems or bacteriocins (bacteriolytic molecules) [356,357]. This coordinated sacrificial lifestyle in the biofilm community enables elimination of non-competent members of the community to sustain survival of the remaining members or for re-colonization. For *S. mutans* biofilms, a quorum-sensing pathway is present for inducing bacteriocin production in response to environmental stresses. The pathway responds to the intracellular accumulation of competence-stimulating peptide pheromone [358]. The occurrence of apoptosis-like programmed cell death in bacteria provides a rational explanation for the observation of three-dimensional killing by QACs within *in vivo* plaque biofilms that mimic the process of diffusional-killing by leached antimicrobial agents incorporated into polymers (Video 1 in Supplementary material; <https://youtu.be/Iw5StFwE.FU>).

## 7. Toxicological aspects of QACs

Although QAC-based biomedical materials have seen exciting advances, there are public concerns and even frustrations regarding their potential harm to the ecosystem and human health due to recent toxicological reports on QACs. Detection of QACs and their degradation products have been reported in diverse environments such as surface water, sediment and sludge-amended soil. The toxicity of QACs has received considerable attention because in addition to microorganisms, QACs are toxic to aquatic organisms, soil organisms, animals and humans [359]. Toxicity data from laboratory studies are essential for evaluation of the possible biological risks of QACs. Sandbacka et al. reported that QACs exhibited acute toxicity on fish cells, daphnia magna and even white fish [360]. Other studies reported that QACs exhibited higher toxicity in algae than fish and crustaceans [359,361–363], due to their high affinity for negatively-charged algal cell walls. Sludge containing QACs also

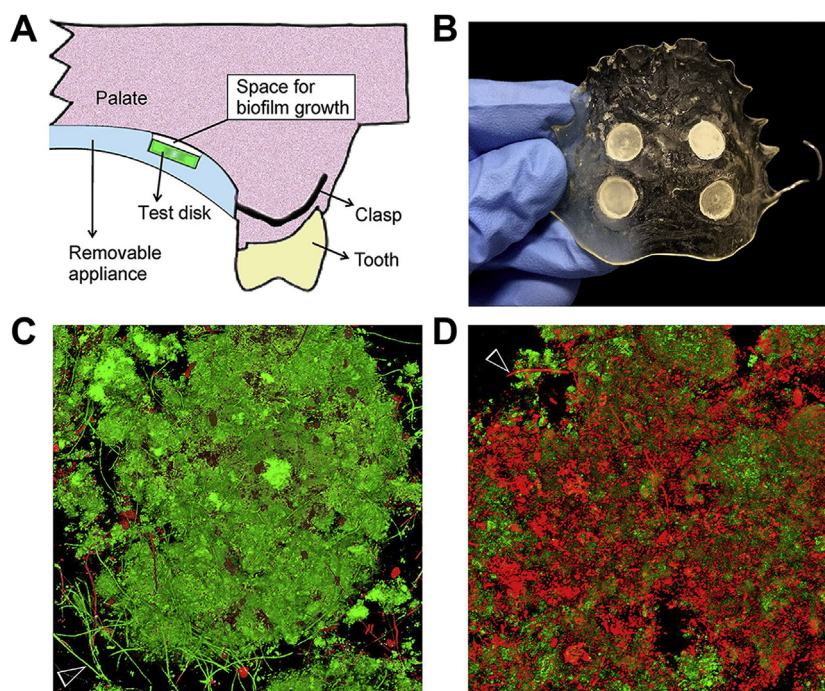

**Fig. 15.** Randomized clinical trial on the *in vivo* antimicrobial efficacy of quaternary ammonium methacryloxy siloxane (QAMS)-containing orthodontic acrylic. A. Schematic illustrating the relationship between a test disk and its fitting well within the retainer appliance. The disk surface to be examined was turned toward the palate but not in direct contact with the palate. Each well was protected from the oral cavity by orthodontic acrylic to prevent disturbance of the biofilm by the tongue. B. Each appliance contained 4 wells to house two 6-mm diameter retrievable control disks and 2 similar diameter retrievable experimental PMMA disks (containing 5 wt% QAMS). C. BacLight-stained confocal laser scanning microscopy merged image showing the presence of live (green) bacteria and fungal hyphae (open arrowhead) within the biovolume of a biofilm taken from a control disk of one subject. D. The corresponding BacLight-stained merged image showing the presence of dead (red) bacteria and fungal hyphae killed by the QAMS-containing acrylic from an experimental disk of the same subject. [291], Copyright 2016. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

Reproduced with permission from Scientific Reports, Nature Publishing Group.

exhibit toxicity towards soil organisms such as earthworms [364]. Accumulation of QACs, together with other contaminants in soil over time, may change the soil environment and lead to potential bioaccumulation in soil organisms, resulting in potential biological risks [365]. Hence, the toxicological effects of QACs after their long-term exposure to the environment warrant further investigation [366].

Special attention should be paid to the toxicity of QACs towards animals and humans. The common QAC surfactant benzalkonium chloride causes toxicity and genotoxicity in *Daphnia magna* and *Ceriodaphnia dubia* models [367]. Using a eukaryotic cell model, genotoxicity has been observed for two QACs, benzalkonium chloride and dimethyldioctadecyl-ammonium bromide, at concentrations commonly found in waste water [368] and in commercially available nasal preparations [369]. These data suggest that direct contact with QA-containing detergents and pharmaceuticals that contain substantially higher QAC concentrations may cause potential DNA-damaging effects in humans. Different cell types have dissimilar susceptibility to the same QAC. An *in vitro* study conducted by Sokolova and coworkers reported that QACs exhibit selective toxic action among different cell lines [85]. Such a phenomenon may be explained by the different cell culture conditions and selective toxicity of QACs against lymphoblastoid cells compared with cells of epithelial origin. Melin et al. reported that QACs significantly reduced reproductive function in both male and female mice [370,371]. Larsen et al. also found that inhalation of QAC aerosols results in acute airway irritation and inflammation in mice [372]. Theoretically, the QACs cannot be released from QA-based biomedical materials. Thus, a better understanding of the mechanisms of QAC-related toxicity should promote the innocuous use of these technologies.


The antimicrobial activity of QACs has generally been attributed to their ability to destroy cell membrane structure. To investigate the mechanisms responsible for the toxicity of QACs, Vieira's group compared the toxicity of QACs to cells cultured *in vitro* with their ability to kill pathogens [373]. The authors also evaluated the cytotoxicity of QACs toward several mammalian cell lines [374]. Unexpectedly, they found that cytotoxicity is intracellular in origin at low QAC concentrations; abnormality or damage of intracellular biochemical processes are involved in lieu of membrane disintegration or cell lysis. It has been shown that QACs at low concentrations induce oxidative stresses, trigger apoptotic signals and destroy cells by apoptosis [375,376]. Similarly, DMAE-CB monomers cause overproduction of reactive oxygen species, cell cycle arrest, reduction in mitochondrial membrane potential and enhanced caspase-3 activity [61]. Mitochondria are believed to be a core component of the cell death machinery. Mitochondria act as sensors and amplifiers in determining the execution of cell death or apoptosis through regulation of cellular energy metabolism (mitochondrial respiration and oxidative phosphorylation) [377]. Mitochondrial dysfunction and perturbation of cellular energetic mechanisms are involved in QAC-induced toxicity [367,378–380]. At very low concentrations, QACs inhibit mitochondrial respiration and oxidative phosphorylation. Apoptosis occurs when the cellular energy charge is reduced by more than 50%. An *in vitro* study showed that QACs alter DNA structure and compromise vital cellular processes [381]. Recently, DMAE-CB monomers were found to induce intracellular oxidative stress, oxidative DNA damage and induction of intrinsic mitochondrial apoptosis [382]. Taking together, oxidative stress and oxidative damage are involved in QAC-induced cytotoxicity.

Based on the finding that oxidative stresses are involved in the cytotoxic effects of QACs, antioxidants such as N-acetyl


cysteine (NAC) have been used for scavenging ROS and antioxidants to reduce the cytotoxicity of QACs [53,60]. Modification of the molecular structures of QACs (e.g. preparation of pegylated-polymers) is an alternative strategy for combating their toxicity. It has been demonstrated that incorporation of poly(ethylene glycol) in QACs completely suppresses hemolysis of human red blood cells [383,384]. Well-defined pegylated-polymers have been synthesized via RAFT polymerization [385]. By modifying the content of hydrophobic groups and molecular weights, the antimicrobial and

hemolytic activities of amphiphilic polymethacrylate derivatives can be tailored. Compared with pegylated-polymers consisting of longer alkyl spacers, polymers with a shorter alkyl or hydroxyl group exhibit minimal hemolysis of red blood cells while retaining potent antimicrobial activities.

Quaternary ammonium-based nanomaterials may cause latent nanoparticle-related toxicity. Nano-sized particles have unique bio-distribution due to their highly different pharmacokinetic properties. Although existing drugs or materials are safe in the

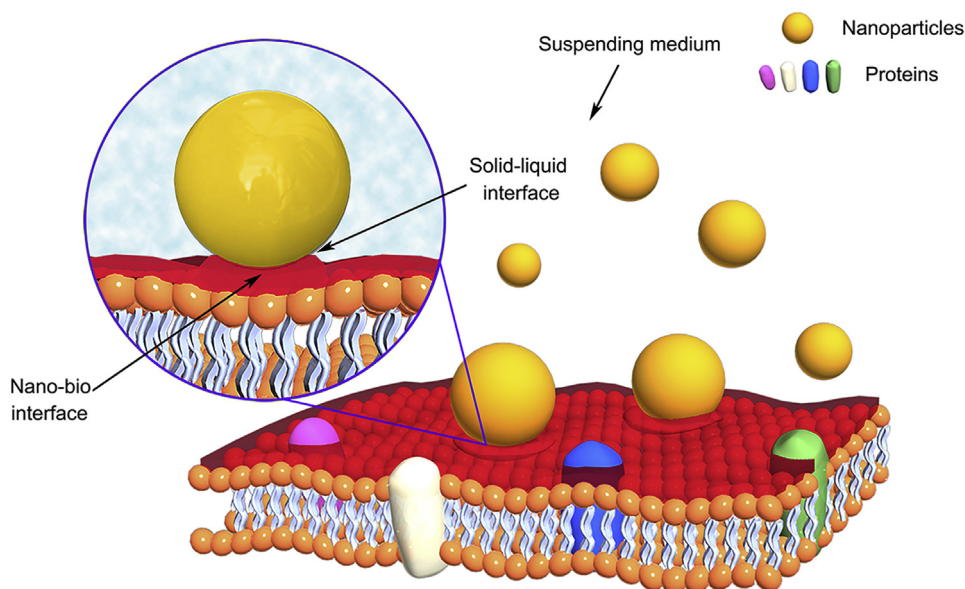

**Fig. 16.** Schematic representation of the interface between a nanoparticle and the lipid bilayer of a cell membrane. The nano-bio interface comprises the surface of the nanoparticle; the solid-liquid interface and the effects of the surrounding medium; and the interface's contact zone with biological substrates.

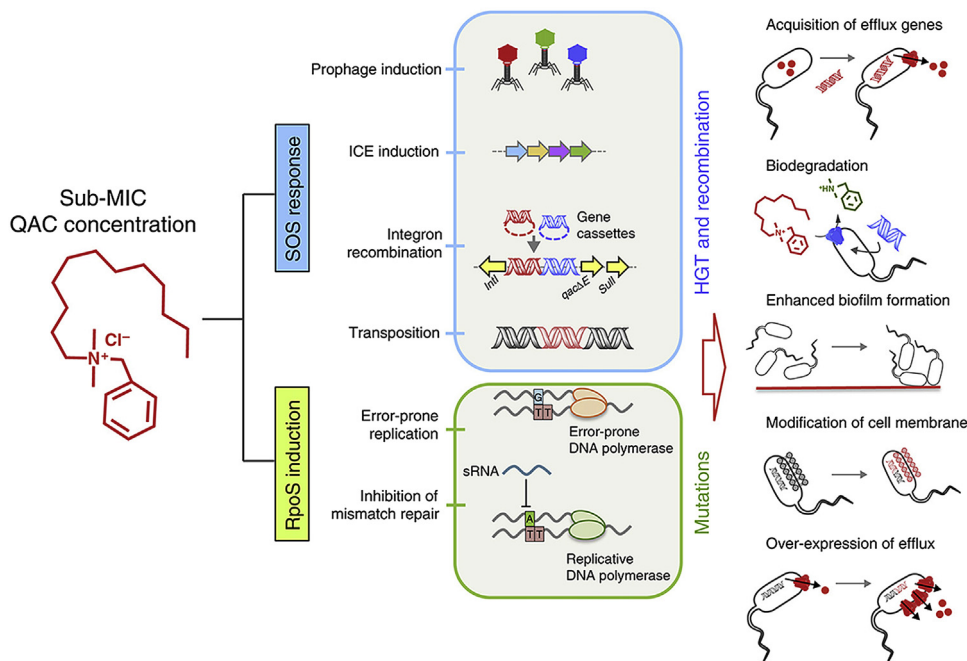

micrometer dimensions, unpredictable adverse and toxicological effects may emerge when they are formulated at the nanoscale. Nanoparticles are small enough to penetrate blood-brain barrier in the body, causing neurotoxicity [386]. Several approaches have been suggested and identified to achieve safe design of nanomaterials, based on the understanding of the bio-nanointerface [387] (Fig. 16). These approaches include: (1) changing the surface characteristics (such as size, surface charge, and dispersibility, particularly the effect of hydrophobicity) and the ability of nanoparticles to aggregate, (2) coating nanoparticles with protective shells, and (3) designing nanoparticles with different oxidative states.

## 8. QACs and antimicrobial resistance

Antimicrobial resistance of pathogens is rapidly becoming the most serious concern in contemporary infection control [388]. A new post-antibiotic era has instigated since the discovery of untreatable strains of Enterobacteriaceae that are resistant to the carbapenem class of antibiotics, considered the “drug of last resort” for such infections [389]. Until recently, QACs were thought to be invulnerable to the development of antimicrobial resistance [390]. However, recently acquired data has shown this to be far from the truth. Therefore, comprehending the contributory conditions and underlying mechanisms that result in antimicrobial resistance of QACs are still required.

At concentrations above the minimum inhibitory concentration, it is well accepted that QACs interact with cell membranes of microorganisms, disrupt their membrane integrity and cause leakage of cellular contents [47]. However, QACs are biodegradable under aerobic conditions. As a result, microorganisms are dynamically exposed to QACs over a wide range of concentrations (i.e., non-inhibitory, sub-inhibitory, over-inhibitory concentrations). In general, environmental concentrations of QACs, including those that are found in sewage, biological wastewater treatment units, surface water and sediments, are well below minimum inhibitory concentration values. Thus, it is possible to prolong the contact between QACs and microorganisms at sub-inhibitory concentrations. Such environments with QACs at low chemical reactivity become selective and favorable for the survival of clones with lower susceptibility, ultimately leading to evolution and selection of QAC-resistant bacteria [391]. Many excellent reviews indicate that QAC-related antimicrobial resistance occurs at sub-inhibitory concentrations through both intrinsic and acquired resistance mechanisms [392,393] (Fig. 17). Bacteria compensate for the oxidative stresses created by exposure to QACs at sub-inhibitory concentrations via SOS-response and induction of stress-response sigma factors rpoS inducing modification of cell membrane structure and composition, enhanced biofilm formation, hyper-expression of efflux pumps and acquisition of efflux pump genes through mobile recombination elements [394]. Mutations in QAC-resistant bacterial strains cause modifications in cell membrane, resulting in reduction in cell permeability and a more anionic and hydrophobic cell surface. Such modifications help reduce or restrict QAC-induced contact killing [395]. Exposure to QACs at sub-inhibitory concentrations may enhance biofilm formation [396,397] through augmentation of certain gene expression, such as stress response sigma factor HrcA. The latter encodes a transcriptional regulator of the class I heat-shock response [398], and DnaK which encodes a class I heat-shock response chaperone protein [399]. The reduced expression of porins, which results in the changes of membrane protein composition, is also attributed to QAC resistance [400,401]. Efflux pumps, which are generally chromosomally-encoded, help remove antimicrobial agents from the inside of bacterial cell [402]. Efflux-mediated QAC resistance may involve two mechanisms. First, QAC resistance is achieved

by hyper-expression of efflux pumps or increase in their extrusion efficiency, including regulatory modifications or mutations of efflux determinants [403]. For instance, a study by Guo et al. showed that over-expression of efflux-related genes in a variant of *Salmonella typhimurium* increases their tolerance to benzalkonium chloride [404]. Another study by Buffet-Bataillon et al. demonstrated that clinical *E. coli* strains, variants of which are pathogenic, exhibit higher minimum inhibitory concentrations of QACs and ciprofloxacin. Their antibiotic resistance depends on the AcrAB-TolC efflux pump and its regulatory genes [405]. The second mechanism of QAC resistance is through acquisition of genes for specialized QAC efflux pumps through mobile recombination elements, such as plasmids, transposon or integrons. Acquisition of genetic elements, which can be collaterally transferred between bacteria of the same or different genera via quorum sensing, may result in co-resistance (two or more resistance mechanisms in one organism) or cross-resistance (one resistance mechanism that counteracts two or more antibacterial agents). The emergence of “small multidrug resistance” includes expressions of both multidrug efflux pumps [406] and QAC-specific efflux determinants [407]. Accordingly, antibiotic efflux mechanism is likely to be a potential therapeutic target to counteract antimicrobial resistance. There is limited *in vitro* evidence showing that efflux inhibitors such as verapamil and reserpine can block efflux pumps [408]. Further research is required to enhance the pharmacokinetics of these drugs and improve their biocompatibility to target QAC resistance by bacteria.

Regarding QAC-based biomedical materials, there is an urgent need to evaluate whether the long-term use of such technologies results in reduced microbial susceptibility to the QAC and the emergence of QAC-resistant strains. A recent study investigated whether *S. mutans* and *E. faecalis* could develop resistance to the cationic biocides [409]. There were no changes in the minimum inhibitory concentration of MDPB to *S. mutans* and *E. faecalis* even after ten passages, suggesting that no antimicrobial resistance has been developed. Although experimental and clinical evidence on the causal link between QAC-based biomedical materials and antimicrobial resistance are rare, it is important to bear in mind that the use of QACs at sub-inhibitory concentrations helps develop QAC-resistant strains. Caution would be required in the use of QAC-based biomedical materials.

## 9. Concluding remarks and future perspectives

In addition to their broad-spectrum antimicrobial activity, biomaterials with QA functionalities possess potent and long-term biocidal efficacy with non-leachable active species, better biocompatibility and no adverse effects on the mechanical properties of the carrier materials. The advent of new technologies and biomaterials design, especially the emergence of nanotechnology, brings unique opportunities and hope to the formulation of novel biomedical materials that contain QA-functionalized fillers/nanofillers, to address the difficulties and drawbacks of incorporating antibacterial agents that exist in their conventional dimensions into those materials. Nevertheless, there is an ever-growing need to develop antimicrobial materials aiming at multi-species pathogenic microbes, since many microorganisms including bacteria, fungi, protozoa, prions and viruses are involved in microbial infections. Over the past two decades, the advent of various polymerization techniques and post-modification strategies has made it possible to produce QA-based antimicrobial surfaces with an unprecedented level of control over composition, structure, and properties. Despite phenomenal advances in the variety of polymerization techniques, the ongoing progress in each of these arenas indicates that there is still plenty of room for future development.

There are also growing concerns regarding the biocompatibility QACs. Considerable evidence points to their potential toxicological side-effects which may hamper their safe and population-wide applications. Along with the efforts to enhance their antimicrobial properties, lower cytotoxicity also needs to be achieved to expand their clinical use. Currently, many research studies are engaged in investigating structure-bioactivity relationship of QA-based biomedical materials to balance their antimicrobial activity and cytotoxicity. Although the exact and detailed mechanism is still largely unknown, prior reports suggest that oxidative stress plays an important role in their cytotoxicity. Experimental evidence suggests that the use of antioxidants helps reduce their cytotoxicity [53,60,410]. Some QACs may induce differential changes in expression of antioxidant enzymes such as superoxide dismutase, glutathione peroxidase, and catalase [382]. The expression of these antioxidant enzymes is under the control of nuclear factor E2-related factor 2 (Nrf2), a transcription factor that plays a key role in the intracellular anti-oxidative defense system to maintain redox homeostasis [411]. The aforementioned pathway also plays a protective role in nanomaterial-induced oxidative DNA damage and cell death [412,413]. Accordingly, modulation of the Nrf2-mediated cellular defense response may help control QAC-induced cytotoxicity, an important issue that requires further investigation.

Sub-inhibitory concentrations of QACs may be involved in the evolution and selection of QAC-resistant bacteria through intrinsic or acquired resistance mechanisms. To date, there are no relevant studies that examine whether QA-based biomedical materials cause antimicrobial resistance. Nevertheless, one has to be careful with the use of QA-based biomedical materials. The biological environment within the human body is complex, and different fields of application require antimicrobial biomaterials with additional specific properties (e.g. remineralization or protein-repellent properties). Some research groups have incorporated additional components such as AgNPs [268–270], NO-releasing agents [173,174], fluoride [414], NACPs [232–237,335] and 2-methacryloyloxyethyl phosphorylcholine [415–417] into QA-based biomedical materials to achieve augmented antimicrobial or multifunctional applications.

Biofilms are made up of a diverse community of interacting microorganisms with complex three-dimensional structures, including channels, micro-colonies and mushroom-like protrusions [418]. The properties of biofilms are distinct from those exhibited by planktonic species. Biofilms are more tolerant of adverse growth conditions such as antimicrobial agents, stress and host defense peptides. Thus, a better understanding of every aspect of the biofilm, especially with fluorescence microscopy coupled with functionalized nano-probes which allow *in-situ* investigations of the three-dimensional structure of biofilms, may help manage and eradicate biofilms. Recently, luminescent silica nanoparticles with QA functionality have been designed and synthesized [419]. Using confocal laser scanning microscopy, narrow diffusion paths of these luminescent nanoparticles were identified in *P. aeruginosa* biofilms. In addition, pH-sensitive luminescent silica nanoparticles have also been used to investigate pH microenvironment of biofilms of *E. coli* [420]. Future investigations with these functionalized nano-probes may render it possible to create a luminescent adhesive or resin composite with self-diagnostic capability using this technology. To expand the clinical use and commercialization of more QA-based biomedical materials, appropriately designed and well-structured multicenter clinical trials are critically needed to obtain reliable comparative data. Acquisition of these important information should help identify the most effective antibacterial solutions and the optimal circumstances for the use of these materials.

## Acknowledgements

This work was supported by grant 81470773, grant 81130078 and grant 81400555 from National Nature Science Foundation of China, grant 2015AA020942 from National High Technology Research and Development Program of China and Program No. IRT13051 for Changjiang Scholars and Innovative Research Team in University.

## Appendix A. Supplementary data

Supplementary data associated with this article can be found, in the online version, at <http://dx.doi.org/10.1016/j.progpolymsci.2017.03.001>.

## References

- [1] Avila M, Said N, Ojcius DM. The book reopened on infectious diseases. *Microbes Infect* 2008;10:942–7.
- [2] GBD 2013 Mortality and Causes of Death Collaborators. Global, regional, and national age-sex specific all-cause and cause-specific mortality for 240 causes of death, 1990–2013: a systematic analysis for the global burden of disease study 2013. *Lancet* 2015;385:117–71.
- [3] Salwiczek M, Qu Y, Gardiner J, Strugnell RA, Lithgow T, McLean KM, et al. Emerging rules for effective antimicrobial coatings. *Trends Biotechnol* 2014;32:82–90.
- [4] Oyston PC, Fox MA, Richards SJ, Clark GC. Novel peptide therapeutics for treatment of infections. *J Med Microbiol* 2009;58:977–87.
- [5] Lakshmaiah Narayana J, Chen JY. Antimicrobial peptides: possible anti-infective agents. *Peptides* 2015;72:88–94.
- [6] Campoccia D, Montanaro L, Speziale P, Arciola CR. Antibiotic-loaded biomaterials and the risks for the spread of antibiotic resistance following their prophylactic and therapeutic clinical use. *Biomaterials* 2010;31:6363–77.
- [7] Talbot GH, Bradley J, Edwards Jr JE, Gilbert D, Scheld M, Bartlett JG. Antimicrobial availability task force of the Infectious Diseases Society of America: bad bugs need drugs: an update on the development pipeline from the antimicrobial availability task force of the Infectious Diseases Society of America. *Clin Infect Dis* 2006;42:657–68.
- [8] Organization WH. Antimicrobial resistance: global report on surveillance. *Australas Med J* 2014;7:695–704.
- [9] Isquith A, Abbott E, Walters P. Surface-bonded antimicrobial activity of an organosilicon quaternary ammonium chloride. *Appl Microbiol* 1972;24:859–63.
- [10] Tuladhar E, de Koning MC, Fundeanu I, Beumer R, Duizer E. Different virucidal activities of hyperbranched quaternary ammonium coatings on poliovirus and influenza virus. *Appl Environ Microbiol* 2012;78:2456–8.
- [11] Deka SR, Sharma AK, Kumar P. Cationic polymers and their self-assembly for antibacterial applications. *Curr Top Med Chem* 2015;15:1179–95.
- [12] Campoccia D, Montanaro L, Arciola CR. A review of the biomaterials technologies for infection-resistant surfaces. *Biomaterials* 2013;34:8533–54.
- [13] Cloutier M, Mantovani D, Rosei F. Antibacterial coatings: challenges, perspectives, and opportunities. *Trends Biotechnol* 2015;33:637–52.
- [14] Mai S, Mauger MT, Niu LN, Barnes JB, Kao S, Bergeron BE, et al. Potential applications of antimicrobial peptides and their mimics in combating caries and pulpal infections. *Acta Biomater* 2016;49:16–35.
- [15] Lima SM, de Pádua GM, Sousa MG, Freire de MS, Franco OL, Rezende TM. Antimicrobial peptide-based treatment for endodontic infections—biotechnological innovation in endodontics. *Biotechnol Adv* 2015;33:203–13.
- [16] Jain A, Duvvuri LS, Farah S, Beyth N, Domb AJ, Khan W. Antimicrobial polymers. *Adv Healthc Mater* 2014;3:1969–85.
- [17] Padovani GC, Feitosa VP, Sauro S, Tay FR, Durán G, Paula AJ, et al. Advances in dental materials through nanotechnology: facts, perspectives and toxicological aspects. *Trends Biotechnol* 2015;33:621–36.
- [18] Paladini F, Pollini M, Sannino A, Ambrosio L. Metal-based antibacterial substrates for biomedical applications. *Biomacromolecules* 2015;16:1873–85.
- [19] Seabra AB, Justo GZ, Haddad PS. State of the art challenges and perspectives in the design of nitric oxide-releasing polymeric nanomaterials for biomedical applications. *Biotechnol Adv* 2015;33:1370–9.
- [20] Michl TD, Coad BR, Doran M, Osiecki M, Kafshgari MH, Voelcker NH, et al. Nitric oxide releasing plasma polymer coating with bacteriostatic properties and no cytotoxic side effects. *Chem Commun* 2015;51:7058–60.
- [21] Weber DJ, Rutala WA. Self-disinfecting surfaces: review of current methodologies and future prospects. *Am J Infect Control* 2013;41:S31–5.
- [22] Yueh MF, Tukey RH. Triclosan: a widespread environmental toxicant with many biological effects. *Annu Rev Pharmacol Toxicol* 2016;56:251–72.
- [23] Domagk G. A new class of disinfectants. *Dtsch Med Wochenscher* 1935;61:829–32.

- [24] Jennings MC, Buttaro BA, Minbiole KPC, Wuest WM. Bioorganic investigation of multicationic antimicrobials to combat QAC-resistant *Staphylococcus aureus*. *ACS Infect Dis* 2015;1:304–9.
- [25] Xue Y, Xiao H, Zhang Y. Antimicrobial polymeric materials with quaternary ammonium and phosphonium salts. *Int J Mol Sci* 2015;16:3626–55.
- [26] Carmona-Ribeiro AM, de Melo Carrasco LD. Cationic antimicrobial polymers and their assemblies. *Int J Mol Sci* 2013;14:9906–46.
- [27] Muñoz-Bonilla A, Fernández-García M. Polymeric materials with antimicrobial activity. *Prog Polym Sci* 2012;37:281–339.
- [28] Jaeger W, Bohrisch J, Laschewsky A. Synthetic polymers with quaternary nitrogen atoms—synthesis and structure of the most used type of cationic polyelectrolytes. *Prog Polym Sci* 2010;35:511–77.
- [29] Marcotte L, Barbeau J, Lafleur M. Permeability and thermodynamics study of quaternary ammonium surfactants-phosphocholine vesicle system. *J Colloid Interface Sci* 2005;292:219–27.
- [30] Haldar J, An D, de Cienfuegos LÁ, Chen J, Klibanov AM. Polymeric coatings that inactivate both influenza virus and pathogenic bacteria. *Proc Natl Acad Sci USA* 2006;103:17667–71.
- [31] Kenawy el R, Worley SD, Broughton R. The chemistry and applications of antimicrobial polymers: a state-of-the-art review. *Biomacromolecules* 2007;8:1359–84.
- [32] Oblak E, Piecuch A, Krasowska A, Luczynski J. Antifungal activity of gemini quaternary ammonium salts. *Microbiol Res* 2013;168:630–8.
- [33] Wessels S, Ingmer H. Modes of action of three disinfectant active substances: a review. *Regul Toxicol Pharmacol* 2013;67:456–67.
- [34] Ikeda T, Hirayama H, Yamaguchi H, Tazuke S, Watanabe M. Polycationic biocides with pendant active groups: molecular weight dependence of antibacterial activity. *Antimicrob Agents Chemother* 1986;30:132–6.
- [35] Chen CZ, Beck-Tan NC, Dhurjati P, van Dyk TK, LaRossa RA, Cooper SL. Quaternary ammonium functionalized poly(propylene imine) dendrimers as effective antimicrobials: structure-activity studies. *Biomacromolecules* 2000;1:473–80.
- [36] Gilbert P, Al-Taae A. Antimicrobial activity of some alkyltrimethylammonium bromides. *Lett Appl Microbiol* 1985;1:101–4.
- [37] Caillier L, de Givenchy ET, Levy R, Vandenberghe Y, Geribaldi S, Guittard F. Synthesis and antimicrobial properties of polymerizable quaternary ammoniums. *Eur J Med Chem* 2009;44:3201–8.
- [38] He J, Soderling E, Vallittu PK, Lassila LV. Investigation of double bond conversion, mechanical properties, and antibacterial activity of dental resins with different alkyl chain length quaternary ammonium methacrylate monomers (QAM). *J Biomater Sci Polym Ed* 2013;24:565–73.
- [39] Kong M, Chen XG, Xing K, Park HJ. Antimicrobial properties of chitosan and mode of action: a state of the art review. *Int J Food Microbiol* 2010;144:51–63.
- [40] Gilbert P, Moore LE. Cationic antiseptics: diversity of action under a common epithet. *J Appl Microbiol* 2005;99:703–15.
- [41] Garg G, Chauhan GS, Gupta R, Ahn JH. Anion effects on anti-microbial activity of poly[1-vinyl-3-(2-sulfoethyl imidazolium betaine)]. *J Colloid Interface Sci* 2010;344:90–6.
- [42] Ingalsbe ML, Denis JD, McGahan ME, Steiner WW, Priefer R. Development of a novel expression, ZI MAX/K ZI, for determination of the counter-anion effect on the antimicrobial activity of tetrabutylammonium salts. *Bioorg Med Chem Lett* 2009;19:4984–7.
- [43] Sharma SK, Chauhan GS, Gupta R, Ahn JH. Tuning anti-microbial activity of poly(4-vinyl 2-hydroxyethyl pyridinium) chloride by anion exchange reactions. *J Mater Sci Mater Med* 2010;21:717–24.
- [44] Xie D, Weng Y, Guo X, Zhao J, Gregory RL, Zheng C. Preparation and evaluation of a novel glass-ionomer cement with antibacterial functions. *Dent Mater* 2011;27:487–96.
- [45] Panarin EF, Solovskii MV, Zaikina NA, Afinogenov GE. Biological activity of cationic polyelectrolytes. *Makromol Chem* 1985;9:25–33.
- [46] Mizerska U, Fortuniak W, Chojnowski J, Halasa R, Konopačka A, Werel W. Polysiloxane cationic biocides with imidazolium salt (ImS) groups, synthesis and antibacterial properties. *Eur Polym J* 2009;45:779–87.
- [47] Tischer M, Pradel G, Ohlson K, Holzgrabe U. Quaternary ammonium salts and their antimicrobial potential: targets or nonspecific interactions. *ChemMedChem* 2012;7:22–31.
- [48] Gottenbos B, Grijpma DW, van der Mei HC, Feijen J, Busscher HJ. Antimicrobial effects of positively charged surfaces on adhering Gram-positive and Gram-negative bacteria. *J Antimicrob Chemother* 2001;48:7–13.
- [49] Cavallaro A, Mierczynska A, Barton M, Majewski P, Vasilev K. Influence of immobilized quaternary ammonium group surface density on antimicrobial efficacy and cytotoxicity. *Biofouling* 2016;32:13–24.
- [50] Yoshikawa K, Clark DT, Brailsford SR, Beighton D, Watson TF, Imazato S, et al. The effect of antibacterial monomer MDPB on the growth of organisms associated with root caries. *Dent Mater J* 2007;26:388–92.
- [51] Imazato S, Ebi N, Tarumi H, Russell RR, Kaneko T, Ebiu S. Bactericidal activity and cytotoxicity of antibacterial monomer MDPB. *Biomaterials* 1999;20:899–903.
- [52] Nishida M, Imazato S, Takahashi Y, Ebiu S, Ishimoto T, Nakano T, et al. The influence of the antibacterial monomer 12-methacryloyloxydodecylpyridinium bromide on the proliferation, differentiation and mineralization of odontoblast-like cells. *Biomaterials* 2010;31:1518–32.
- [53] Ma S, Imazato S, Takahashi Y, Kiba W, Takeda K, Izutani N, et al. Mechanism of detoxification of the cationic antibacterial monomer 12-methacryloyloxydodecylpyridinium bromide (MDPB) by *N*-acetyl cysteine. *Dent Mater* 2013;29:1219–27.
- [54] Pupo YM, Farago PV, Nadal JM, Simao LC, Esmerino LA, Gomes OM, et al. Effect of a novel quaternary ammonium methacrylate polymer (QAMP) on adhesion and antibacterial properties of dental adhesives. *Int J Mol Sci* 2014;15:8998–9015.
- [55] Pupo YM, Farago PV, Nadal JM, Esmerino LA, Maluf DF, Zawadzki SF, et al. An innovative quaternary ammonium methacrylate polymer can provide improved antimicrobial properties for a dental adhesive system. *J Biomater Sci Polym Ed* 2013;24:1443–58.
- [56] Li F, Weir MD, Fouad AF, Xu HH. Time-kill behaviour against eight bacterial species and cytotoxicity of antibacterial monomers. *J Dent* 2013;41:881–91.
- [57] Huang L, Xiao YH, Xing XD, Li F, Ma S, Qi LL, et al. Antibacterial activity and cytotoxicity of two novel cross-linking antibacterial monomers on oral pathogens. *Arch Oral Biol* 2011;56:367–73.
- [58] Xiao YH, Chen JH, Fang M, Xing XD, Wang H, Wang YJ, et al. Antibacterial effects of three experimental quaternary ammonium salt (QAS) monomers on bacteria associated with oral infections. *J Oral Sci* 2008;50:323–7.
- [59] Chai Z, Li F, Fang M, Wang Y, Ma S, Xiao Y, et al. The bonding property and cytotoxicity of a dental adhesive incorporating a new antibacterial monomer. *J Oral Rehabil* 2011;38:849–56.
- [60] Jiao Y, Ma S, Li J, Shan L, Wang Y, Tian M, et al. *N*-acetyl cysteine (NAC)-directed detoxification of methacryloyloxyethyl cetyl ammonium chloride (DMAE-CB). *PLoS One* 2015;10, e0135815/1–15.
- [61] Ma S, Shan LQ, Xiao YH, Li F, Huang L, Shen L, et al. The cytotoxicity of methacryloyloxyethyl cetyl ammonium chloride, a cationic antibacterial monomer, is related to oxidative stress and the intrinsic mitochondrial apoptotic pathway. *Braz J Med Biol Res* 2011;44:1125–33.
- [62] Imazato S, Torii Y, Takatsuka T, Inoue K, Ebi N, Ebiu S. Bactericidal effect of dentin primer containing antibacterial monomer methacryloyloxydodecylpyridinium bromide (MDPB) against bacteria in human carious dentin. *J Oral Rehabil* 2001;28:314–9.
- [63] Li J, Sha Z, Zhang W, Tao F, Yang P. Preparation and antibacterial properties of gelatin grafted with an epoxy silicone quaternary ammonium salt. *J Biomater Sci Polym Ed* 2016;27:1017–28.
- [64] Regis RR, Vecchia MPD, Pizzolitto AC, Compagnoni MA, Souza PPC, Souza RFD. Antimicrobial properties and cytotoxicity of an antimicrobial monomer for application in prosthodontics. *J Prosthodont* 2012;21:283–90.
- [65] Peng ZX, Wang L, Du L, Guo SR, Wang XQ, Tang TT. Adjustment of the antibacterial activity and biocompatibility of hydroxypropyltrimethyl ammonium chloride chitosan by varying the degree of substitution of quaternary ammonium. *Carbohydr Polym* 2010;81:275–83.
- [66] Imazato S, Torii M, Tsuchitani Y, McCabe JF, Russell RR. Incorporation of bacterial inhibitor into resin composite. *J Dent Res* 1994;73:1437–43.
- [67] Cheng L, Weir MD, Zhang K, Arola DD, Zhou X, Xu HH. Dental primer and adhesive containing a new antibacterial quaternary ammonium monomer dimethylaminododecyl methacrylate. *J Dent* 2013;41:345–55.
- [68] Li F, Weir MD, Xu HH. Effects of quaternary ammonium chain length on antibacterial bonding agents. *J Dent Res* 2013;92:932–8.
- [69] He J, Söderling E, Österblad M, Vallittu PK, Lassila LV. Synthesis of methacrylate monomers with antibacterial effects against *S. mutans*. *Molecules* 2011;16:9755–63.
- [70] Weng Y, Guo X, Chong VJ, Howard L, Gregory RL, Xie D. Synthesis and evaluation of a novel antibacterial dental resin composite with quaternary ammonium salts. *J Biomed Sci Eng* 2011;4:147–57.
- [71] Lewis K. In search of natural substrates and inhibitors of MDR pumps. *J Mol Microbiol Biotechnol* 2001;3:247–54.
- [72] Leclercq L, Lubart Q, Dewilde A, Aubry JM, Nardello-Rataj V. Supramolecular effects on the antifungal activity of cyclodextrin/di-*n*-decyldimethylammonium chloride mixtures. *Eur J Pharm Sci* 2012;46:336–45.
- [73] Nurdin N, Helary G, Sauvet G. Biocidal polymers active by contact: III. Ageing of biocidal polyurethane coatings in water. *J Appl Polym Sci* 1993;50:671–8.
- [74] Oblak E, Lachowicz TM, Luczyński J, Witek S. Comparative studies of the biological activities of lysosomotropic aminoesters and quaternary ammonium salts on the yeast *Saccharomyces cerevisiae*. *Cell Mol Biol Lett* 2001;6:871–80.
- [75] Oosterhof JJ, Buijssen KJ, Busscher HJ, van der Laan BF, van der Mei HC. Effects of quaternary ammonium silane coatings on mixed fungal and bacterial biofilms on tracheoesophageal shunt prostheses. *Appl Environ Microbiol* 2006;72:3673–7.
- [76] Vieira DB, Carmona-Ribeiro AM. Cationic lipids and surfactants as antifungal agents: mode of action. *J Antimicrob Chemother* 2006;58:760–7.
- [77] Carmona-Ribeiro AM, Vieira DB, Lincopan N. Cationic surfactants and lipids as anti-infective agents. *Anti-Infe Agents Med Chem* 2006;5:33–51.
- [78] Reboiras MD, Miller MJ, Jones MN. Liposome adsorption to *Candida albicans*. *Colloids Surf B* 1997;9:101–7.
- [79] Campanhã M, Mamizuka E, Carmona-Ribeiro A. Interactions between cationic vesicles and *Candida albicans*. *J Phys Chem B* 2001;105:8230–6.
- [80] Shirai A, Sumitomo T, Kurimoto M, Maseda H, Kourai H. The mode of the antifungal activity of gemini-pyridinium salt against yeast. *Biocontrol Sci* 2009;14:13–20.

- [81] Shirai A, Ueta S, Maseda H, Kourai H, Omasa T. Action of reactive oxygen species in the antifungal mechanism of gemini-pyridinium salts against yeast. *Biocontrol Sci* 2012;17:77–82.
- [82] Muhizi T, Coma V, Grelier S. Synthesis of D glucosamine quaternary ammonium derivatives and evaluation of their antifungal activity together with aminodeoxyglucose derivatives against two wood fungi *Corioli* versicolor and *Por*ia placenta: structure-activity relationships. *Pest Manag Sci* 2011;67:287–93.
- [83] Tsoo IF, Wang HY, Shipman Jr C. Interaction of infectious viral particles with a quaternary ammonium chlorid (QAC) surface. *Biotechnol Bioeng* 1989;34:639–46.
- [84] Walters PA, Abbott EA, Isquith AJ. Algicidal activity of a surface-bonded organosilicon quaternary ammonium chloride. *Appl Microbiol* 1973;25:253–6.
- [85] Sokolova AS, Yarovaya CO, Shernyukov CA, Pokrovsky CE, Pokrovsky CA, Lavrinenko VA, et al. New quaternary ammonium camphor derivatives and their antiviral activity, genotoxic effects and cytotoxicity. *Bioorgan Med Chem* 2013;21:6690–8.
- [86] Sokolova AS, Yarovaya OI, Shernyukov AV, Gatilov YV, Razumova YV, Zarubaev VV, et al. Discovery of a new class of antiviral compounds: camphor imine derivatives. *Eur J Med Chem* 2015;105:263–73.
- [87] Sokolova AS, Yarovaya OC, Korchagina DV, Zarubaev VV, Tretiak TS, Anfimov PM, et al. Camphor-based symmetric diimines as inhibitors of influenza virus reproduction. *Bioorgan Med Chem* 2014;22:2141–8.
- [88] Zarubaev VV, Garshina AV, Tretiak TS, Fedorova VA, Shtro AA, Sokolova AS, et al. Broad range of inhibiting action of novel camphor-based compound with anti-hemagglutinin activity against influenza viruses in vitro and in vivo. *Antiviral Res* 2015;120:126–33.
- [89] Shiraiishi M, Aramaki Y, Seto M, Imoto H, Nishikawa Y, Kanzaki N, et al. Discovery of novel, potent, and selective small-molecule CCR5 antagonists as anti-HIV-1 agents: synthesis and biological evaluation of anilide derivatives with a quaternary ammonium moiety. *J Med Chem* 2000;43:2049–63.
- [90] Scott FW. Virucidal disinfectants and feline viruses. *Am J Vet Res* 1980;41:410–4.
- [91] Kennedy MA, Mellon VS, Caldwell G, Potgieter L. Virucidal efficacy of the newer quaternary ammonium compounds. *J Am Anim Hosp Assoc* 1994;31:254–8.
- [92] Eleraky NZ, Potgieter LN, Kennedy MA. Virucidal efficacy of four new disinfectants. *J Am Anim Hosp Assoc* 2002;38:231–4.
- [93] Harada Y, Lekcharoensuk P, Furuta T, Taniguchi T. Inactivation of foot-and-mouth disease virus by commercially available disinfectants and cleaners. *Biocontrol Sci* 2015;20:205–8.
- [94] Tung G, Macinga D, Arbogast J, Jaykus LA. Efficacy of commonly used disinfectants for inactivation of human noroviruses and their surrogates. *J Food Prot* 2013;76:1210–7.
- [95] Shirai J, Kanno T, Tsuchiya Y, Mitsubayashi S, Seki R. Effects of chlorine, iodine, and quaternary ammonium compound disinfectants on several exotic disease viruses. *J Vet Med Sci* 2000;62:85–92.
- [96] Hoelzer K, Fanaselle W, Pouillot R, Van Doren JM, Dennis S. Virus inactivation on hard surfaces or in suspension by chemical disinfectants: systematic review and meta-analysis of norovirus surrogates. *J Food Prot* 2013;76:1006–16.
- [97] Gulve N, Kimmerling K, Johnston AD, Krueger GR, Ablashi DV, Prusty BK. Anti-herpesviral effects of a novel broad range anti-microbial quaternary ammonium silane, K21. *Antiviral Res* 2016;131:166–73.
- [98] Mazzoni A, Tjäderhane L, Checchi V, Di Lenarda R, Salo T, Tay FR, et al. Role of dentin MMPs in caries progression and bond stability. *J Dent Res* 2015;94:241–51.
- [99] Chaussain-Miller C, Fioretti F, Goldberg M, Menashi S. The role of matrix metalloproteinases (MMPs) in human caries. *J Dent Res* 2006;85:22–32.
- [100] Palosaari H, Pennington CJ, Larmas M, Edwards DR, Tjäderhane L, Salo T. Expression profile of matrix metalloproteinases (MMPs) and tissue inhibitors of MMPs in mature human odontoblasts and pulp tissue. *Eur J Oral Sci* 2003;111:117–27.
- [101] Sulkala M, Wahlgren J, Larmas M, Sorsa T, Teronen O, Salo T, et al. The effects of MMP inhibitors on human salivary MMP activity and caries progression in rats. *J Dent Res* 2001;80:1545–9.
- [102] Menezes-Silva R, Khaliq S, Deeley K, Letra A, Vieira AR. Genetic susceptibility to periapical disease: conditional contribution of MMP2 and MMP3 genes to the development of periapical lesions and healing response. *J Endod* 2012;38:604–7.
- [103] Karayasha D, Glushkova M, Boteva E, Mitev V, Kadiyska T. Association study for the role of matrix metalloproteinases 2 and 3 gene polymorphisms in dental caries susceptibility. *Arch Oral Biol* 2016;68:9–12.
- [104] Tezvergil-Mutluay A, Agee KA, Uchiyama T, Imazato S, Mutluay MM, Cadenaro M, et al. The inhibitory effects of quaternary ammonium methacrylates on soluble and matrix-bound MMPs. *J Dent Res* 2011;90:535–40.
- [105] Tezvergil-Mutluay A, Agee KA, Mazzoni A, Carvalho RM, Carrilho M, Tersariol IL, et al. Can quaternary ammonium methacrylates inhibit matrix MMPs and cathepsins. *Dent Mater* 2015;31:e25–32.
- [106] Liu Y, Tjäderhane L, Breschi L, Mazzoni A, Li N, Mao J, et al. Limitations in bonding to dentin and experimental strategies to prevent bond degradation. *J Dent Res* 2011;90:953–68.
- [107] Carrilho MR. Can exogenous protease inhibitors control dentin matrix degradation. *J Dent Res* 2012;91:1099–102.
- [108] Jain A, Bahuguna R. Role of matrix metalloproteinases in dental caries, pulp and periapical inflammation: an overview. *J Oral Biol Craniofac Res* 2015;5:212–8.
- [109] Chang YC, Yang SF, Hsieh YS. Regulation of matrix metalloproteinase-2 production by cytokines and pharmacological agents in human pulp cell cultures. *J Endod* 2001;27:679–82.
- [110] Lin SK, Wang CC, Huang S, Lee JJ, Chiang CP, Lan WH, et al. Induction of dental pulp fibroblast matrix metalloproteinase-1 and tissue inhibitor of metalloproteinase-1 gene expression by interleukin-1 $\alpha$  and tumor necrosis factor- $\alpha$  through a prostaglandin-dependent pathway. *J Endod* 2001;27:185–9.
- [111] Goda S, Kato Y, Domae E, Hayashi H, Tani-Ishii N, Iida J, et al. Effects of JNK1/2 on the inflammation cytokine TNF- $\alpha$ -enhanced production of MMP-3 in human dental pulp fibroblast-like cells. *Int Endod J* 2015;48:1122–8.
- [112] de Paula-Silva FW, D'Silva NJ, da Silva LA, Kapila YL. High matrix metalloproteinase activity is a hallmark of periapical granulomas. *J Endod* 2009;35:1234–42.
- [113] Leonardi R, Caltabiano R, Loreto C. Collagenase-3 (MMP-13) is expressed in periapical lesions: an immunohistochemical study. *Int Endod J* 2005;38:297–301.
- [114] Wahlgren J, Salo T, Teronen O, Luoto H, Sorsa T, Tjäderhane L. Matrix metalloproteinase-8 (MMP-8) in pulpal and periapical inflammation and periapical root-canal exudates. *Int Endod J* 2002;35:897–904.
- [115] Martinho FC, Teixeira FF, Cardoso FG, Ferreira NS, Nascimento GG, Carvalho CA, et al. Clinical investigation of matrix metalloproteinases, tissue inhibitors of matrix metalloproteinases, and matrix metalloproteinase/tissue inhibitors of matrix metalloproteinase complexes and their networks in apical periodontitis. *J Endod* 2016;42:1082–8.
- [116] Zhao B, Brittain WJ. Polymer brushes: surface-immobilized macromolecules. *Prog Polym Sci* 2000;25:677–710.
- [117] Zhou T, Zhu Y, Li X, Liu X, Yeung KWK, Wu S, et al. Surface functionalization of biomaterials by radical polymerization. *Prog Mater Sci* 2016;83:191–235.
- [118] Barbey R, Lavanant L, Paripovic D, Schüwer N, Sugnaux C, Tugulu S, et al. Polymer brushes via surface-initiated controlled radical polymerization: synthesis, characterization, properties, and applications. *Chem Rev* 2009;109:5437–527.
- [119] Huang J, Koepsel RR, Murata H, Wu W, Lee SB, Kowalewski T, et al. Nonleaching antibacterial glass surfaces via grafting onto: the effect of the number of quaternary ammonium groups on biocidal activity. *Langmuir* 2008;24:6785–95.
- [120] Davies ML, Hamilton CJ, Murphy SM, Tighe BJ. Polymer membranes in clinical sensor applications: I. An overview of membrane function. *Biomaterials* 1992;13:971–8.
- [121] Qiu J, Charleux B, Matyjaszewski K. Controlled/living radical polymerization in aqueous media: homogeneous and heterogeneous systems. *Prog Polym Sci* 2001;26:2083–134.
- [122] Mastan E, Li X, Zhu S. Modeling and theoretical development in controlled radical polymerization. *Prog Polym Sci* 2015;45:71–101.
- [123] Lee SB, Koepsel RR, Morley SW, Matyjaszewski K, Sun Y, Russell AJ. Permanent, nonleaching antibacterial surfaces: 1. Synthesis by atom transfer radical polymerization. *Biomacromolecules* 2004;5:877–82.
- [124] Murata H, Koepsel RR, Matyjaszewski K, Russell AJ. Permanent, non-leaching antibacterial surfaces. 2: How high density cationic surfaces kill bacterial cells. *Biomaterials* 2007;28:4870–9.
- [125] Ravikumar T, Murata H, Koepsel RR, Russell AJ. Surface-active antifungal polyquaternary amine. *Biomacromolecules* 2006;7:2762–9.
- [126] Wang B, Xu Q, Ye Z, Liu H, Lin Q, Nan K, et al. Copolymer brushes with temperature-triggered, reversibly switchable bactericidal and antifouling properties for biomaterial surfaces. *ACS Appl Mater Interfaces* 2016;8:27207–17.
- [127] Wang B, Ye Z, Xu Q, Liu H, Lin Q, Chen H, et al. Construction of a temperature-responsive terpolymer coating with recyclable bactericidal and self-cleaning antimicrobial properties. *Biomater Sci* 2016;4:1731–41.
- [128] Roy D, Knapp JS, Guthrie JT, Perrier S. Antibacterial cellulose fiber via RAFT surface graft polymerization. *Biomacromolecules* 2008;9:91–9.
- [129] Ignatova M, Voccia S, Gilbert B, Markova N, Mercuri PS, Galleni M, et al. Synthesis of copolymer brushes endowed with adhesion to stainless steel surfaces and antibacterial properties by controlled nitroxide-mediated radical polymerization. *Langmuir* 2004;20:10718–26.
- [130] Voccia S, Ignatova M, Jérôme R, Jérôme C. Design of antibacterial surfaces by a combination of electrochemistry and controlled radical polymerization. *Langmuir* 2006;22:8607–13.
- [131] Yuan SJ, Pehkonen SO, Ting YP, Neoh KG, Kang ET. Inorganic-organic hybrid coatings on stainless steel by layer-by-layer deposition and surface-initiated atom-transfer-radical polymerization for combating biocorrosion. *ACS Appl Mater Interfaces* 2009;1:640–52.
- [132] Yuan SJ, Pehkonen SO, Ting YP, Neoh KG, Kang ET. Antibacterial inorganic-organic hybrid coatings on stainless steel via consecutive surface-initiated atom transfer radical polymerization for biocorrosion prevention. *Langmuir* 2010;26:6728–36.
- [133] Ignatova M, Voccia S, Gabriel S, Gilbert B, Cossement D, Jerome R, et al. Stainless steel grafting of hyperbranched polymer brushes with an antibacterial activity: synthesis, characterization, and properties. *Langmuir* 2009;25:891–902.

- [134] Yuan SJ, Xu FJ, Pehkonen SO, Ting YP, Neoh KG, Kang ET. Grafting of antibacterial polymers on stainless steel via surface-initiated atom transfer radical polymerization for inhibiting biocorrosion by *Desulfovibrio desulfuricans*. *Biotechnol Bioeng* 2009;103:268–81.
- [135] Dong H, Huang J, Koepsel RR, Ye P, Russell AJ, Matyjaszewski K. Recyclable antibacterial magnetic nanoparticles grafted with quaternized poly(2-(dimethylamino)ethyl methacrylate) brushes. *Biomacromolecules* 2011;12:1305–11.
- [136] Rutnakornpituk B, Wichai U, Vilaivan T, Rutnakornpituk M. Surface-initiated atom transfer radical polymerization of poly(4-vinylpyridine) from magnetite nanoparticle. *J Nanopart Res* 2011;13:6847–57.
- [137] Zhang F, Shi ZL, Chua PH, Kang ET, Neoh KG. Functionalization of titanium surfaces via controlled living radical polymerization: from antibacterial surface to surface for osteoblast adhesion. *Ind Eng Chem Res* 2007;46:9077–86.
- [138] Ramstedt M, Cheng N, Azzaroni O, Mossialos D, Mathieu HJ, Huck WT. Synthesis and characterization of poly(3-sulfopropylmethacrylate) brushes for potential antibacterial applications. *Langmuir* 2007;23:3314–21.
- [139] Xu FJ, Yuan SJ, Pehkonen SO, Kang ET, Neoh KG. Antimicrobial surfaces of viologen-quaternized poly((2-dimethyl amino)ethyl methacrylate)-Si(100) hybrids from surface-initiated atom transfer radical polymerization. *Nanobiotechnology* 2006;2:123–34.
- [140] Wei T, Zhan W, Cao L, Hu C, Qu Y, Yu Q, et al. Multifunctional and regenerable antibacterial surfaces fabricated by a universal strategy. *ACS Appl Mater Interfaces* 2016;8:30048–57.
- [141] Fundeanu I, Klee D, Schouten AJ, Busscher HJ, van der Mei HC. Solvent-free functionalization of silicone rubber and efficacy of PAAm brushes grafted from an amino-PPX layer against bacterial adhesion. *Acta Biomater* 2010;6:4271–6.
- [142] Fundeanu I, van der Mei HC, Schouten AJ, Busscher HJ. Polyacrylamide brush coatings preventing microbial adhesion to silicone rubber. *Colloids Surf B* 2008;64:297–301.
- [143] Wang H, Wang L, Zhang P, Yuan L, Yu Q, Chen H. High antibacterial efficiency of pDMAEMA modified silicon nanowire arrays. *Colloids Surf B* 2011;83:355–9.
- [144] Vaterrodt A, Thallinger B, Daumann K, Koch D, Guebitz GM, Ulbricht M. Antifouling and antibacterial multi-functional polyzwitterion/enzyme coating on silicone catheter material prepared by electrostatic layer-by-layer assembly. *Langmuir* 2016;32:1347–59.
- [145] Peng Q, Lu S, Chen D, Wu X, Fan P, Zhong R, et al. Poly(vinylidene fluoride)-graft-poly(*N*-vinyl-2-pyrrolidone) copolymers prepared via a RAFT-mediated process and their use in antifouling and antibacterial membranes. *Macromol Biosci* 2007;7:1149–59.
- [146] Zhai G, Shi ZL, Kang ET, Neoh KG. Surface-initiated atom transfer radical polymerization on poly(vinylidene fluoride) membrane for antibacterial ability. *Macromol Biosci* 2005;5:974–82.
- [147] Cheng Z, Zhu X, Shi ZL, Neoh KG, Kang ET. Polymer microspheres with permanent antibacterial surface from surface-initiated atom transfer radical polymerization. *Ind Eng Chem Res* 2005;44:7098–104.
- [148] Lenoir S, Pagnouille C, Galleni M, Compere P, Jerome R, Detrembleur C. Polyolefin matrixes with permanent antibacterial activity: preparation, antibacterial activity, and action mode of the active species. *Biomacromolecules* 2006;7:2291–6.
- [149] Jo TS, Yang ML, Brownell LV, Bae C. Synthesis of quaternary ammonium ion-grafted polyolefins via activation of inert C–H bonds and nitroxide mediated radical polymerization. *J Polym Sci Part A Polym Chem* 2009;47:4519–31.
- [150] Huang J, Murata H, Koepsel RR, Russell AJ, Matyjaszewski K. Antibacterial polypropylene via surface-initiated atom transfer radical polymerization. *Biomacromolecules* 2007;8:1396–9.
- [151] Thomassin JM, Lenoir S, Riga J, Jerome R, Detrembleur C. Grafting of poly[2-(tert-butylamino)ethyl methacrylate] onto polypropylene by reactive blending and antibacterial activity of the copolymer. *Biomacromolecules* 2007;8:1171–7.
- [152] Fang Y, Fu GD, Zhao J, Kang ET, Neoh KG. Antibacterial effect of surface-functionalized polypropylene hollow fiber membrane from surface-initiated atom transfer radical polymerization. *J Membrane Sci* 2008;319:149–57.
- [153] Fu GD, Yao F, Li ZG, Li XS. Solvent-resistant antibacterial microfibers of self-quaternized block copolymers from atom transfer radical polymerization and electrospinning. *J Mater Chem* 2008;18:859–67.
- [154] Konn C, Morel F, Beyou E, Chaumont P, Bourgeat-Lami E. Nitroxide-mediated polymerization of styrene initiated from the surface of laponite clay platelets. *Macromolecules* 2007;40:7464–72.
- [155] Wang JS, Matyjaszewski K. Controlled/living radical polymerization: atom transfer radical polymerization in the presence of transition-metal complexes. *J Am Chem Soc* 1995;117:5614–5.
- [156] Kato M, Kamigaito M, Sawamoto M, Higashimura T. Polymerization of methyl methacrylate with the carbon tetrachloride/dichlorotris-(triphenylphosphine)ruthenium(II)/methylaluminum bis(2,6-di-tert-butylphenoxide) initiating system: possibility of living radical polymerization. *Macromolecules* 1995;28:1721–3.
- [157] Matyjaszewski K, Tsarevsky NV. Macromolecular engineering by atom transfer radical polymerization. *J Am Chem Soc* 2014;136:6513–33.
- [158] Matyjaszewski K. Atom transfer radical polymerization (ATRP): Current status and future perspectives. *Macromolecules* 2012;45:4015–39.
- [159] Ran J, Wu L, Zhang Z, Xu T. Atom transfer radical polymerization (ATRP): a versatile and forceful tool for functional membranes. *Prog Polym Sci* 2013;39:124–44.
- [160] Siegwart DJ, Oh JK, Matyjaszewski K. ATRP in the design of functional materials for biomedical applications. *Prog Polym Sci* 2012;37:18–37.
- [161] Mayadunne RT, Rizzardo E, Chiefari J, Chong YK, Moad G, Thang SH. Living radical polymerization with reversible addition-fragmentation chain transfer (RAFT polymerization) using dithiocarbamates as chain transfer agents. *Macromolecules* 1999;32:6977–80.
- [162] Chong Y, Le TP, Moad G, Rizzardo E, Thang SH. A more versatile route to block copolymers and other polymers of complex architecture by living radical polymerization: the RAFT process. *Macromolecules* 1999;32:2071–4.
- [163] Barner Kowolik C, Perrier S. The future of reversible addition fragmentation chain transfer polymerization. *J Polym Sci Part A Polym Chem* 2008;46:5715–23.
- [164] Zhang H. Controlled/living radical precipitation polymerization: a versatile polymerization technique for advanced functional polymers. *Eur Polym J* 2013;49:579–600.
- [165] Gregory A, Stenzel MH. Complex polymer architectures via RAFT polymerization: from fundamental process to extending the scope using click chemistry and nature's building blocks. *Prog Polym Sci* 2012;37:38–105.
- [166] Benaglia M, Chiefari J, Chong YK, Moad G, Rizzardo E, Thang SH. Universal (switchable) RAFT agents. *J Am Chem Soc* 2009;131:6914–5.
- [167] Nicolas J, Guillaneuf Y, Lefay C, Bertin D, Gignes B, Charleux B. Nitroxide-mediated polymerization. *Prog Polym Sci* 2013;38:63–235.
- [168] Zhao L, Li N, Wang K, Shi C, Zhang L, Luan Y. A review of polypeptide-based polymersomes. *Biomaterials* 2014;35:1284–301.
- [169] Nuyken O, Pask SD. Ring-opening polymerization – an introductory review. *Polymers* 2013;5:361–403.
- [170] Penczek S, Cypryk M, Duda A, Kubisa P, Slomkowski S. Living ring-opening polymerizations of heterocyclic monomers. *Prog Polym Sci* 2007;32:247–82.
- [171] King A, Chakraborty S, Zhang W, Zeng X, Ohman DE, Wood LF, et al. High antimicrobial effectiveness with low hemolytic and cytotoxic activity for PEG/quaternary copolyoxetanes. *Biomacromolecules* 2014;15:456–67.
- [172] Chakraborty S, King A, Kurt P, Zhang W, Ohman DE, Wood LF, et al. Highly effective, water-soluble, hemocompatible 1,3-propylene oxide-based antimicrobials: poly[(3,3-quaternary)/PEG]-copolyoxetanes]. *Biomacromolecules* 2011;12:757–69.
- [173] Worley BV, Slomberg DL, Schoenfisch MH. Nitric oxide-releasing quaternary ammonium-modified poly(amidoamine) dendrimers as dual action antibacterial agents. *Bioconjug Chem* 2014;25:918–27.
- [174] Carpenter AW, Worley BV, Slomberg DL, Schoenfisch MH. Dual action antimicrobials: nitric oxide release from quaternary ammonium-functionalized silica nanoparticles. *Biomacromolecules* 2012;13:3334–42.
- [175] Leng M, Hu S, Lu A, Cai M, Luo X. The anti-bacterial poly(caprolactone)-poly(quaternary ammonium salt) as drug delivery carriers. *Appl Microbiol Biotechnol* 2015;100:3049–59.
- [176] Pascual A, Tan JP, Yuen A, Chan JM, Coody DJ, Mecerreyes D, et al. Broad-spectrum antimicrobial polycarbonate hydrogels with fast degradability. *Biomacromolecules* 2015;16:1169–78.
- [177] Liang Z, Zhu M, Yang YW, Gao H. Antimicrobial activities of polymeric quaternary ammonium salts from poly(glycidyl methacrylate)s. *Polym Adv Technol* 2014;25:117–22.
- [178] Kolb HC, Finn MG, Sharpless KB. Click chemistry: diverse chemical function from a few good reactions. *Angew Chem Int Ed* 2001;40:2004–21.
- [179] Golas PL, Matyjaszewski K. Marrying click chemistry with polymerization: expanding the scope of polymeric materials. *Chem Soc Rev* 2010;41:1338–54.
- [180] Galvin CJ, Genzer J. Applications of surface-grafted macromolecules derived from post-polymerization modification reactions. *Prog Polym Sci* 2012;37:871–906.
- [181] Moses JE, Moorhouse AD. The growing applications of click chemistry. *Chem Soc Rev* 2007;36:1249–62.
- [182] Sheiko SS, Sumerlin BS, Matyjaszewski K. Cylindrical molecular brushes: synthesis, characterization, and properties. *Prog Polym Sci* 2008;33:759–85.
- [183] Such GK, Johnston APR, Liang K, Caruso F. Synthesis and functionalization of nanoengineered materials using click chemistry. *Prog Polym Sci* 2012;37:985–1003.
- [184] Tasdelen MA, Kiskan B, Yagci Y. Externally stimulated click reactions for macromolecular syntheses. *Prog Polym Sci* 2015;52:19–78.
- [185] Rostovtsev VV, Green LG, Fokin VV, Sharpless KB. A stepwise huisgen cycloaddition process: copper(I)-catalyzed regioselective ligation of azides and terminal alkynes. *Angew Chem Int Ed* 2002;41:2596–9.
- [186] Tornøe CW, Christensen C, Meldal M. Peptidotriazoles on solid phase: [1,2,3]-triazoles by regioselective copper(I)-catalyzed 1,3-dipolar cycloadditions of terminal alkynes to azides. *J Org Chem* 2002;67:3057–64.
- [187] Bock VD, Hiemstra H, Van Maarseveen JH. Cu-catalyzed alkyne-azide click cycloadditions from a mechanistic and synthetic perspective. *Eur J Org Chem* 2006;37:51–68.
- [188] Ganewatta MS, Miller KP, Singleton SP, Mehrpouya-Bahrani P, Chen YP, Yan Y, et al. Antibacterial and biofilm-disrupting coatings from resin acid-derived materials. *Biomacromolecules* 2015;16:3336–44.

- [189] Qin T, Chang T, Ma T, Long P, Wang J. Click synthesis of quaternized poly(dimethylaminoethyl methacrylate) functionalized graphene oxide with improved antibacterial and antifouling ability. *Colloids Surf B* 2016;141:196–205.
- [190] Riva R, Lussis P, Lenoir S, Jérôme C, Jérôme R, Lecomte P. Contribution of click chemistry to the synthesis of antimicrobial aliphatic copolyester. *Polymer* 2008;49:2023–8.
- [191] Yao K, Chen Y, Zhang J, Clay B, Tang C. Cationic salt-responsive bottle-brush polymers. *Macromol Rapid Comm* 2013;34:645–51.
- [192] Jewett JC, Bertozzi CR. Cu-free click cycloaddition reactions in chemical biology. *Chem Soc Rev* 2010;39:1272–9.
- [193] Jewett JC, Sletten EM, Bertozzi CR. Rapid Cu-free click chemistry with readily synthesized biarylazacyclooctynes. *J Am Chem Soc* 2010;132:3688–90.
- [194] Tu Q, Ma C, Tian C, Yuan M, Han X, Wang DE, et al. Quantum dots modified with quaternized poly(dimethylaminoethyl methacrylate) for selective recognition and killing of bacteria over mammalian cells. *Analyst* 2016;141:3328–36.
- [195] Tian W, Hu Y, Wang W, Yu D. Synthesis of a gemini quaternary ammonium salt and its reaction with wool fabric using click chemistry. *RSC Adv* 2015;5:91932–6.
- [196] Hoyle CE, Lowe AB, Bowman CN. Thiol-click chemistry: a multifaceted toolbox for small molecule and polymer synthesis. *Chem Soc Rev* 2010;39:1355–87.
- [197] Wen J, Weinhart M, Lai B, Kizhakkedathu J, Brooks DE. Reversible homeostatic properties of sulfobetaine/quaternary ammonium modified hyperbranched polyglycerol. *Biomaterials* 2016;86:42–55.
- [198] Zilberman M, Elsnor JJ. Antibiotic-eluting medical devices for various applications. *J Control Release* 2008;130:202–15.
- [199] Buchholz H, Engelbrecht H. Über die Depotwirkung einiger Antibiotika bei Vermischung mit dem kunstharz Palacos. *Chirurg* 1970;41:511–5.
- [200] Vecsei V, Barquet A. Treatment of chronic osteomyelitis by necrectomy and gentamicin-PMMA beads. *Clin Orthop Relat Res* 1981;159:201–7.
- [201] Hendriks JG, van Horn JR, van der Mei HC, Busscher HJ. Backgrounds of antibiotic-loaded bone cement and prosthesis-related infection. *Biomaterials* 2004;25:545–56.
- [202] van de Belt H, Neut D, van Horn JR, van der Mei HC, Schenk W, Busscher HJ. Antibiotic resistance—to treat or not to treat. *Nat Med* 1999;5:358–9.
- [203] Bunetel L, Segui A, Cormier M, Percheron E, Langlais F. Release of gentamicin from acrylic bone cement. *Clin Pharmacokinet* 1989;17:291–7.
- [204] Wu P, Grainger DW. Drug/device combinations for local drug therapies and infection prophylaxis. *Biomaterials* 2006;27:2450–67.
- [205] Punyani S, Singh H. Preparation of iodine containing quaternary amine methacrylate copolymers and their contact killing antimicrobial properties. *J Appl Polym Sci* 2006;102:1038–44.
- [206] Deb S, Doiron R, Disilvio L, Punyani S, Singh H. PMMA bone cement containing a quaternary amine comonomer with potential antibacterial properties. *J Biomed Mater Res B* 2008;85:130–9.
- [207] Punyani S, Deb S, Singh H. Contact killing antimicrobial acrylic bone cements: preparation and characterization. *J Biomater Sci Polym Ed* 2007;18:131–45.
- [208] Abid K, Jain S, Jackeray R, Chattopadhyay S, Singh H. Formulation and characterization of antimicrobial quaternary ammonium dendrimer in poly(methyl methacrylate) bone cement. *J Biomed Mater Res B* 2015;10, <http://dx.doi.org/10.1002/jbm.b.33553>.
- [209] Tan H, Peng Z, Li Q, Xu X, Guo S, Tang T. The use of quaternized chitosan-loaded PMMA to inhibit biofilm formation and downregulate the virulence-associated gene expression of antibiotic-resistant staphylococcus. *Biomaterials* 2012;33:365–77.
- [210] Tan H, Guo S, Yang S, Xu X, Tang T. Physical characterization and osteogenic activity of the quaternized chitosan-loaded PMMA bone cement. *Acta Biomater* 2012;8:2166–74.
- [211] Tan H, Ao H, Ma R, Tang T. Quaternized chitosan-loaded polymethylmethacrylate bone cement: biomechanical and histological evaluations. *J Orthop Trans* 2013;1:57–66.
- [212] Tan HL, Ao HY, Ma R, Lin WT, Tang TT, Tan HL. In vivo effect of quaternized chitosan-loaded PMMA bone cement on methicillin-resistant staphylococcus infection of the tibial metaphysis in a rabbit model. *Antimicrob Agents Chemother* 2014;58:6016–23.
- [213] Shi Z, Neoh KG, Kang ET, Wang W. Antibacterial and mechanical properties of bone cement impregnated with chitosan nanoparticles. *Biomaterials* 2006;27:2440–9.
- [214] Beyth S, Polak D, Milgrom C, Weiss EI, Matanis S, Beyth N. Antibacterial activity of bone cement containing quaternary ammonium polyethyleneimine nanoparticles. *J Antimicrob Chemother* 2014;69:854–5.
- [215] Peng ZX, Ao HY, Wang L, Guo SR, Tang TT. Quaternized chitosan coating on titanium provides a self-protective surface that prevents bacterial colonisation and implant-associated infections. *RSC Adv* 2015;5:54304–11.
- [216] Dan Y, Cai JY, Xin L, Church JS, Wang L. Novel immobilization of a quaternary ammonium moiety on keratin fibers for medical applications. *Int J Biol Macromol* 2014;70:236–40.
- [217] Meghil MM, Rueggeberg F, El-Awady A, Miles B, Tay F, Pashley D, et al. Novel coating of surgical suture confers antimicrobial activity against *Porphyromonas gingivalis* and *Enterococcus faecalis*. *J Periodontol* 2015;86:788–94.
- [218] Liu Y, Ma K, Li R, Ren X, Huang TS. Antibacterial cotton treated with *N*-halamine and quaternary ammonium salt. *Cellulose* 2013;20:3123–30.
- [219] Kang CK, Kim SS, Kim S, Lee J, Lee JH, Roh C, et al. Antibacterial cotton fibers treated with silver nanoparticles and quaternary ammonium salts. *Carbohydr Polym* 2016;151:1012–8.
- [220] Tran PL, Hamood AN, de Souza A, Schultz G, Liesenfeld B, Mehta D, et al. A study on the ability of quaternary ammonium groups attached to a polyurethane foam wound dressing to inhibit bacterial attachment and biofilm formation. *Wound Repair Regen* 2015;23:74–81.
- [221] Yari A, Yeganeh H, Bakhshi H. Synthesis and evaluation of novel absorptive and antibacterial polyurethane membranes as wound dressing. *J Mater Sci Mater Med* 2012;23:2187–202.
- [222] Uppanar P, Channananon S, Veeranondh S, Tanodekaew S. Synthesis of GTMAC modified chitin-PAA gel and evaluation of its biological properties. *J Biomed Mater Res A* 2011;98:185–91.
- [223] Pilakasis K, Molee P, Sringeriyuang D, Sangjun N, Channananon S, Tanodekaew S. Efficacy of chitin-PAA-GTMAC gel in promoting wound healing: animal study. *J Mater Sci Mater Med* 2011;22:2497–504.
- [224] Imazato S, Ebi N, Takahashi Y, Kaneko T, Ebisu S, Russell RR. Antibacterial activity of bactericide-immobilized filler for resin-based restoratives. *Biomaterials* 2003;24:3605–9.
- [225] Imazato S, Imai T, Russell RR, Torii M, Ebisu S. Antibacterial activity of cured dental resin incorporating the antibacterial monomer MDPB and an adhesion-promoting monomer. *J Biomed Mater Res* 1998;39:511–5.
- [226] Imazato S, McCabe JF. Influence of incorporation of antibacterial monomer on curing behavior of a dental composite. *J Dent Res* 1994;73:1641–5.
- [227] Imazato S, Russell RR, McCabe JF. Antibacterial activity of MDPB polymer incorporated in dental resin. *J Dent* 1995;23:177–81.
- [228] Imazato S, Tarumi H, Kato S, Ebisu S. Water sorption and colour stability of composites containing the antibacterial monomer MDPB. *J Dent* 1999;27:279–83.
- [229] Beyth N, Yudovin-Farber I, Bahir R, Domb AJ, Weiss EI. Antibacterial activity of dental composites containing quaternary ammonium polyethyleneimine nanoparticles against *Streptococcus mutans*. *Biomaterials* 2006;27:3995–4002.
- [230] Beyth N, Yudovin-Farber I, Perez-Davidi M, Domb AJ, Weiss EI. Polyethyleneimine nanoparticles incorporated into resin composite cause cell death and trigger biofilm stress in vivo. *Proc Natl Acad Sci USA* 2010;107:22038–43.
- [231] Yudovin-Farber I, Beyth N, Nyska A, Weiss EI, Golenser J, Domb AJ. Surface characterization and biocompatibility of restorative resin containing nanoparticles. *Biomacromolecules* 2008;9:3044–50.
- [232] Cheng L, Weir MD, Zhang K, Wu EJ, Xu SM, Zhou X, et al. Dental plaque microcosm biofilm behavior on calcium phosphate nanocomposite with quaternary ammonium. *Dent Mater* 2012;28:853–62.
- [233] Cheng L, Weir MD, Zhang K, Xu SM, Chen Q, Zhou X, et al. Antibacterial nanocomposite with calcium phosphate and quaternary ammonium. *J Dent Res* 2012;91:460–6.
- [234] Li F, Wang P, Weir MD, Fouad AF, Xu HH. Evaluation of antibacterial and remineralizing nanocomposite and adhesive in rat tooth cavity model. *Acta Biomater* 2014;10:2804–13.
- [235] Wu J, Weir MD, Melo MA, Xu HH. Development of novel self-healing and antibacterial dental composite containing calcium phosphate nanoparticles. *J Dent* 2015;43:317–26.
- [236] Wu J, Zhou H, Weir MD, Melo MA, Levine ED, Xu HH. Effect of dimethylaminohexadecyl methacrylate mass fraction on fracture toughness and antibacterial properties of CaP nanocomposite. *J Dent* 2015;43:1539–46.
- [237] Zhou C, Weir MD, Zhang K, Deng D, Cheng L, Xu HH. Synthesis of new antibacterial quaternary ammonium monomer for incorporation into CaP nanocomposite. *Dent Mater* 2013;29:859–70.
- [238] Cheng L, Weir MD, Xu HH, Antonucci JM, Kraigsley AM, Lin NJ, et al. Antibacterial amorphous calcium phosphate nanocomposites with a quaternary ammonium dimethacrylate and silver nanoparticles. *Dent Mater* 2012;28:561–72.
- [239] Cheng L, Zhang K, Zhou CC, Weir MD, Zhou XD, Xu HHK. One-year water-aging of calcium phosphate composite containing nano-silver and quaternary ammonium to inhibit biofilms. *Int J Oral Sci* 2016;8:172–81.
- [240] Antonucci JM, Zeiger DN, Tang K, Lin-Gibson S, Fowler BO, Lin NJ. Synthesis and characterization of dimethacrylates containing quaternary ammonium functionalities for dental applications. *Dent Mater* 2012;28:219–28.
- [241] He J, Soderling E, Lassila LV, Vallittu PK. Incorporation of an antibacterial and radiopaque monomer in to dental resin system. *Dent Mater* 2012;28:e110–7.
- [242] He J, Soderling E, Vallittu PK, Lassila LV. Preparation and evaluation of dental resin with antibacterial and radio-opaque functions. *Int J Mol Sci* 2013;14:5445–60.
- [243] He J, Soderling E, Lassila LV, Vallittu PK. Synthesis of antibacterial and radio-opaque dimethacrylate monomers and their potential application in dental resin. *Dent Mater* 2014;30:968–76.
- [244] Huang L, Sun X, Xiao YH, Dong Y, Tong ZC, Xing XD, et al. Antibacterial effect of a resin incorporating a novel polymerizable quaternary ammonium salt MAE-DB against *Streptococcus mutans*. *J Biomed Mater Res B* 2012;100:1353–8.

- [245] He J, Soderling E, Lassila LV, Vallittu PK. Preparation of antibacterial and radio-opaque dental resin with new polymerizable quaternary ammonium monomer. *Dent Mater* 2015;31:575–82.
- [246] Xu X, Wang Y, Liao S, Wen ZT, Fan Y. Synthesis and characterization of antibacterial dental monomers and composites. *J Biomed Mater Res B* 2012;100:1151–62.
- [247] Burujeny SB, Atai M, Yeganeh H. Assessments of antibacterial and physico-mechanical properties for dental materials with chemically anchored quaternary ammonium moieties: thiol-ene-methacrylate vs. conventional methacrylate system. *Dent Mater* 2015;31:244–61.
- [248] Liang X, Soderling E, Liu F, He J, Lassila LV, Vallittu PK. Optimizing the concentration of quaternary ammonium dimethacrylate monomer in bis-GMA/TEGDMA dental resin system for antibacterial activity and mechanical properties. *J Mater Sci Mater Med* 2014;25:1387–93.
- [249] Huang QT, He JW, Lin ZM, Liu F, Lassila LV, Vallittu PK. Physical and chemical properties of an antimicrobial Bis-GMA free dental resin with quaternary ammonium dimethacrylate monomer. *J Mech Behav Biomed Mater* 2016;56:68–76.
- [250] Banzi EC, Costa AR, Puppini-Rontani RM, Babu J, Garcia-Godoy F. Inhibitory effects of a cured antibacterial bonding system on viability and metabolic activity of oral bacteria. *Dent Mater* 2014;30:e238–44.
- [251] da Silva BM, Franca FM, Florio FM, Basting RT. In situ anticariogenic effect of adhesive systems containing fluoride and MDPB. *Am J Dent* 2010;23:75–80.
- [252] Gondim JO, Duque C, Hebling J, Giro EM. Influence of human dentine on the antibacterial activity of self-etching adhesive systems against cariogenic bacteria. *J Dent* 2008;36:241–8.
- [253] Imazato S, Ehara A, Torii M, Ebisu S. Antibacterial activity of dentine primer containing MDPB after curing. *J Dent* 1998;26:267–71.
- [254] Imazato S, Kaneko T, Takahashi Y, Noiri Y, Ebisu S. In vivo antibacterial effects of dentin primer incorporating MDPB. *Oper Dent* 2004;29:369–75.
- [255] Imazato S, Kinomoto Y, Tarumi H, Torii M, Russell R, McCabe J. Incorporation of antibacterial monomer MDPB into dentin primer. *J Dent Res* 1997;76:768–72.
- [256] Imazato S, Tay FR, Kaneshiro AV, Takahashi Y, Ebisu S. An in vivo evaluation of bonding ability of comprehensive antibacterial adhesive system incorporating MDPB. *Dent Mater* 2007;23:170–6.
- [257] Turkun M, Turkun L, Ergucu Z, Ates M. Is an antibacterial adhesive system more effective than cavity disinfectants. *Am J Dent* 2006;19:166–70.
- [258] Uysal T, Amasyali M, Ozcan S, Koyuturk AE, Sagdic D. Effect of antibacterial monomer-containing adhesive on enamel demineralization around orthodontic brackets: an in-vivo study. *Am J Orthod Dentofacial Orthop* 2011;139:650–6.
- [259] Li F, Chai ZG, Sun MN, Wang F, Ma S, Zhang L, et al. Anti-biofilm effect of dental adhesive with cationic monomer. *J Dent Res* 2009;88:372–6.
- [260] Li F, Chen J, Chai Z, Zhang L, Xiao Y, Fang M, et al. Effects of a dental adhesive incorporating antibacterial monomer on the growth, adherence and membrane integrity of *Streptococcus mutans*. *J Dent* 2009;37:289–96.
- [261] Xiao YH, Ma S, Chen JH, Chai ZG, Li F, Wang YJ. Antibacterial activity and bonding ability of an adhesive incorporating an antibacterial monomer DMAE-CB. *J Biomed Mater Res B* 2009;90:813–7.
- [262] Li F, Weir MD, Chen J, Xu HH. Effect of charge density of bonding agent containing a new quaternary ammonium methacrylate on antibacterial and bonding properties. *Dent Mater* 2014;30:433–41.
- [263] Wang S, Zhang K, Zhou X, Xu N, Xu HH, Weir MD, et al. Antibacterial effect of dental adhesive containing dimethylaminododecyl methacrylate on the development of *Streptococcus mutans* biofilm. *Int J Mol Sci* 2014;15:12791–806.
- [264] Zhang K, Wang S, Zhou X, Xu HH, Weir MD, Ge Y, et al. Effect of antibacterial dental adhesive on multispecies biofilms formation. *J Dent Res* 2015;94:622–9.
- [265] Zhou H, Li F, Weir MD, Xu HH. Dental plaque microcosm response to bonding agents containing quaternary ammonium methacrylates with different chain lengths and charge densities. *J Dent* 2013;41:1122–31.
- [266] Zhang K, Cheng L, Imazato S, Antonucci JM, Lin NJ, Lin-Gibson S, et al. Effects of dual antibacterial agents MDPB and nano-silver in primer on microcosm biofilm, cytotoxicity and dentine bond properties. *J Dent* 2013;41:464–74.
- [267] Zhang K, Li F, Imazato S, Cheng L, Liu H, Arola DD, et al. Dual antibacterial agents of nano-silver and 12-methacryloyloxydodecylpyridinium bromide in dental adhesive to inhibit caries. *J Biomed Mater Res B* 2013;101:929–38.
- [268] Cheng L, Zhang K, Weir MD, Liu H, Zhou X, Xu HH. Effects of antibacterial primers with quaternary ammonium and nano-silver on *Streptococcus mutans* impregnated in human dentin blocks. *Dent Mater* 2013;29:462–72.
- [269] Zhang K, Melo MA, Cheng L, Weir MD, Bai Y, Xu HH. Effect of quaternary ammonium and silver nanoparticle-containing adhesives on dentin bond strength and dental plaque microcosm biofilms. *Dent Mater* 2012;28:842–52.
- [270] Cheng L, Zhang K, Melo MA, Weir MD, Zhou X, Xu HH. Anti-biofilm dentin primer with quaternary ammonium and silver nanoparticles. *J Dent Res* 2012;91:598–604.
- [271] Li F, Weir MD, Chen J, Xu HH. Comparison of quaternary ammonium-containing with nano-silver-containing adhesive in antibacterial properties and cytotoxicity. *Dent Mater* 2013;29:450–61.
- [272] Chen C, Weir MD, Cheng L, Lin NJ, Lin-Gibson S, Chow LC, et al. Antibacterial activity and ion release of bonding agent containing amorphous calcium phosphate nanoparticles. *Dent Mater* 2014;30:891–901.
- [273] Weng Y, Guo X, Gregory R, Xie D. A novel antibacterial dental glass-ionomer cement. *Eur J Oral Sci* 2010;118:531–4.
- [274] Weng Y, Howard L, Chong VJ, Sun J, Gregory RL, Xie D. A novel furanone-modified antibacterial dental glass ionomer cement. *Acta Biomater* 2012;8:3153–60.
- [275] Weng Y, Guo X, Gregory RL, Xie D. Preparation and evaluation of an antibacterial dental cement containing quaternary ammonium salts. *J Appl Polym Sci* 2011;122:2542–51.
- [276] Feng J, Cheng L, Zhou X, Xu HH, Weir MD, Meyer M, et al. In situ antibiofilm effect of glass-ionomer cement containing dimethylaminododecyl methacrylate. *Dent Mater* 2015;31:992–1002.
- [277] Wang SP, Ge Y, Zhou XD, Xu HH, Weir MD, Zhang KK, et al. Effect of anti-biofilm glass-ionomer cement on *Streptococcus mutans* biofilms. *Int J Oral Sci* 2016;8:76–83.
- [278] Izutani N, Imazato S, Noiri Y, Ebisu S. Antibacterial effects of MDPB against anaerobes associated with endodontic infections. *Int Endod J* 2010;43:637–45.
- [279] Kitagawa R, Kitagawa H, Izutani N, Hirose N, Hayashi M, Imazato S. Development of an antibacterial root canal filling system containing MDPB. *J Dent Res* 2014;93:1277–82.
- [280] Gong SQ, Epasinghe DJ, Zhang W, Zhou B, Niu LN, Ryou H, et al. Synthesis of antimicrobial silsesquioxane-silica hybrids by hydrolytic co-condensation of alkoxy silanes. *Polym Chem* 2014;5:454–62.
- [281] Gong SQ, Huang ZB, Shi W, Ma B, Tay FR, Zhou B. In vitro evaluation of antibacterial effect of AH Plus incorporated with quaternary ammonium epoxy silicate against *Enterococcus faecalis*. *J Endod* 2014;40:1611–5.
- [282] Barros J, Silva MG, Rocas IN, Gonçalves LS, Alves FF, Lopes MA, et al. Antibiofilm effects of endodontic sealers containing quaternary ammonium polyethyleneimine nanoparticles. *J Endod* 2014;40:1167–71.
- [283] Barros J, Silva MG, Rodrigues MA, Alves FR, Lopes MA, Pina-Vaz I, et al. Antibacterial, physicochemical and mechanical properties of endodontic sealers containing quaternary ammonium polyethyleneimine nanoparticles. *Int Endod J* 2014;47:725–34.
- [284] Kesler Shvero D, Abramovitz I, Zaltsman N, Perez Davidi M, Weiss E, Beyth N. Towards antibacterial endodontic sealers using quaternary ammonium nanoparticles. *Int Endod J* 2013;46:747–54.
- [285] Li F, Li F, Wu D, Ma S, Gao J, Li Y, et al. The effect of an antibacterial monomer on the antibacterial activity and mechanical properties of a pit-and-fissure sealant. *J Am Dent Assoc* 2011;142:184–93.
- [286] Yu F, Yu H, Lin P, Dong Y, Zhang L, Sun X, et al. Effect of an antibacterial monomer on the antibacterial activity of a pit-and-fissure sealant. *PLoS One* 2016;11:e0162281/1–12.
- [287] Yang Y, Huang L, Dong Y, Zhang H, Zhou W, Ban J, et al. In vitro antibacterial activity of a novel resin-based pulp capping material containing the quaternary ammonium salt MAE-DB and Portland cement. *PLoS One* 2014;9:e112549/1–8.
- [288] Gong SQ, Epasinghe DJ, Zhou B, Niu LN, Kimmerling KA, Rueggeberg FA, et al. Effect of water-aging on the antimicrobial activities of an ORMOSIL-containing orthodontic acrylic resin. *Acta Biomater* 2013;9:6964–73.
- [289] Gong SQ, Epasinghe J, Rueggeberg FA, Niu LN, Mettenberg D, Yiu CK, et al. An ORMOSIL-containing orthodontic acrylic resin with concomitant improvements in antimicrobial and fracture toughness properties. *PLoS One* 2012;7:e42355/1–15.
- [290] Gong SQ, Niu LN, Kemp LK, Yiu CK, Ryou H, Qi YP, et al. Quaternary ammonium silane-functionalized, methacrylate resin composition with antimicrobial activities and self-repair potential. *Acta Biomater* 2012;8:3270–82.
- [291] Liu SY, Tonggu L, Niu LN, Gong SQ, Fan B, Wang L, et al. Antimicrobial activity of a quaternary ammonium methacryloxy silicate-containing acrylic resin: a randomised clinical trial. *Sci Rep* 2016;6:21882/1–14.
- [292] Regis RR, Zanini AP, Della Vecchia MP, Silva-Lovato CH, Oliveira Paranhos HF, deSouza RF. Physical properties of an acrylic resin after incorporation of an antimicrobial monomer. *J Prosthodont* 2011;20:372–9.
- [293] Song R, Zhong Z, Lin L. Evaluation of chitosan quaternary ammonium salt-modified resin denture base material. *Int J Biol Macromol* 2016;85:102–10.
- [294] Wassmann M, Winkel A, Haak K, Dempwolf W, Stiesch M, Menzel H. Influence of quaternization of ammonium on antibacterial activity and cytocompatibility of thin copolymer layers on titanium. *J Biomater Sci Polym Ed* 2016;27:1507–19.
- [295] Kalomiraki M, Thermos K, Chaniotakis NA. Dendrimers as tunable vectors of drug delivery systems and biomedical and ocular applications. *Int J Nanomed* 2015;11:1–12.
- [296] Li Z, Lee D, Sheng X, Cohen RE, Rubner MF. Two-level antibacterial coating with both release-killing and contact-killing capabilities. *Langmuir* 2006;22:9820–3.
- [297] Eby DM, Luckarift HR, Johnson GR. Hybrid antimicrobial enzyme and silver nanoparticle coatings for medical instruments. *ACS Appl Mater Interfaces* 2009;1:1553–60.
- [298] Varun S, Macbride MM, Peterson BR, Ayusman S. Silver bromide nanoparticle/polymer composites: dual action tunable antimicrobial materials. *J Am Chem Soc* 2006;128:9798–808.

- [299] Hetrick EM, Schoenfish MH. Reducing implant-related infections: active release strategies. *Chem Soc Rev* 2006;35:780–9.
- [300] Mackenzie D. The history of sutures. *Med Hist* 1973;17:158–68.
- [301] Masini BD, Stinner DJ, Waterman SM, Wenke JC. Bacterial adherence to suture materials. *J Surg Educ* 2011;68:101–4.
- [302] Mogosanu GD, Grumezescu AM. Natural and synthetic polymers for wounds and burns dressing. *Int J Pharm* 2014;463:127–36.
- [303] Windler L, Height M, Nowack B. Comparative evaluation of antimicrobials for textile applications. *Environ Int* 2013;53:62–73.
- [304] Dastjerdi R, Montazer M. A review on the application of inorganic nano-structured materials in the modification of textiles: focus on anti-microbial properties. *Colloids Surf B* 2010;79:5–18.
- [305] Supaphol P, Suwanto O, Sangsanoh P, Srinivasan S, Jayakumar R, Nair SV. Electrospinning of biocompatible polymers and their potentials in biomedical applications. *Adv Polym Sci* 2011;246:213–39.
- [306] Gliścińska E, Gutarowska B, Brycki B, Krucińska I. Electrospun polyacrylonitrile nanofibers modified by quaternary ammonium salts. *J Appl Polym Sci* 2013;128:767–75.
- [307] Uykun N, Ergal I, Kurt H, Gokceoren AT, Gocek I, Kayaoglu BK, et al. Electrospun antibacterial nanofibrous polyvinylpyrrolidone/cetyltrimethylammonium bromide membranes for biomedical applications. *J Bioact Compat Polym* 2014;29:382–97.
- [308] Cerkez I, Kocer HB, Worley SD, Broughton RM, Huang TS. N-halamine biocidal coatings via a layer-by-layer assembly technique. *Langmuir* 2011;27:4091–7.
- [309] Liu Y, Liu Y, Ren X, Huang TS. Antimicrobial cotton containing N-halamine and quaternary ammonium groups by grafting copolymerization. *Appl Surf Sci* 2014;296:231–6.
- [310] Duque Sanchez L, Brack N, Postma A, Pigram PJ, Meagher L. Surface modification of electrospun fibres for biomedical applications: a focus on radical polymerization methods. *Biomaterials* 2016;106:24–45.
- [311] DeForest CA, Anseth KS. Advances in bioactive hydrogels to probe and direct cell fate. *Annu Rev Chem Biomol Eng* 2012;3:421–44.
- [312] Malda J, Visser J, Melchels FP, Jüngst T, Hennink WE, Dhert WJ, et al. 25th anniversary article: engineering hydrogels for biofabrication. *Adv Mater* 2013;25:5011–28.
- [313] Bagramian RA, Garcia-Godoy F, Volpe AR. The global increase in dental caries: impending public health crisis. *Am J Dent* 2009;22:3–8.
- [314] Totiam P, Gonzalez-Cabezas C, Fontana MR, Zero DT. A new in vitro model to study the relationship of gap size and secondary caries. *Caries Res* 2007;41:467–73.
- [315] Tjäderhane L, Buzalaf MAR, Carrilho M, Chaussain C. Matrix metalloproteinases and other matrix proteases in relation to cariology: the era of dentin degradomics. *Caries Res* 2015;49:193–208.
- [316] Imazato S, Ma S, Chen JH, Xu HH. Therapeutic polymers for dental adhesives: loading resins with bio-active components. *Dent Mater* 2014;30:97–104.
- [317] Ge Y, Wang S, Zhou X, Wang H, Xu HH, Cheng L. The use of quaternary ammonium to combat dental caries. *Materials* 2015;8:3532–49.
- [318] Zhou W, Niu LN, Huang L, Fang M, Chang G, Shen LJ, et al. Improved secondary caries resistance via augmented pressure displacement of antibacterial adhesive. *Sci Rep* 2016;6:22269/1–10.
- [319] Batoni G, Pardini M, Giannotti A, Ota F, Giuca MR, Gabriele M, et al. Effect of removable orthodontic appliances on oral colonisation by mutans streptococci in children. *Eur J Oral Sci* 2001;109:388–92.
- [320] Arendorf T, Addy M. Candidal carriage and plaque distribution before, during and after removable orthodontic appliance therapy. *J Clin Periodontol* 1985;12:360–8.
- [321] Ferracane JL, Hilton TJ. Polymerization stress-is it clinically meaningful. *Dent Mater* 2016;32:1–10.
- [322] Kleverlaan CJ, Feilzer AJ. Polymerization shrinkage and contraction stress of dental resin composites. *Dent Mater* 2005;21:1150–7.
- [323] Lee TY, Caroscia J, Smith Z, Bowman CN. Thiol-allyl ether-methacrylate ternary systems: evolution mechanism of polymerization-induced shrinkage stress and mechanical properties. *Macromolecules* 2007;40:1473–9.
- [324] Boulden JE, Cramer NB, Schreck KM, Couch CL, Bracho-Troconis C, Stansbury JW, et al. Thiol-ene-methacrylate composites as dental restorative materials. *Dent Mater* 2011;27:267–72.
- [325] Ortega A, Farah S, Tranque P, Ocana AV, Nam-Cha SH, Beyth N, et al. Antimicrobial evaluation of quaternary ammonium polyethyleneimine nanoparticles against clinical isolates of pathogenic bacteria. *IET Nanobiotechnol* 2015;9:342–8.
- [326] Farah S, Aviv O, Laout N, Ratner S, Beyth N, Domb AJ. Quaternary ammonium polyethyleneimine nanoparticles for treating bacterial contaminated water. *Colloids Surf B* 2015;128:614–9.
- [327] Beyth N, Hourri-Haddad Y, Baraness-Hadar L, Yudovin-Farber I, Domb AJ, Weiss EI. Surface antimicrobial activity and biocompatibility of incorporated polyethyleneimine nanoparticles. *Biomaterials* 2008;29:4157–63.
- [328] Speier J. Development of an organosilicone antimicrobial agent for the treatment of surfaces. *J Ind Text* 1982;12:38–45.
- [329] Jang J, Kim Y. Fabrication of monodisperse silica-polymer core-shell nanoparticles with excellent antimicrobial efficacy. *Chem Commun* 2008:4016–8.
- [330] Song J, Kong H, Jang J. Enhanced antibacterial performance of cationic polymer modified silica nanoparticles. *Chem Commun* 2009;541:5418–20.
- [331] Song J, Kong H, Jang J. Bacterial adhesion inhibition of the quaternary ammonium functionalized silica nanoparticles. *Colloids Surf B* 2011;82:651–6.
- [332] Farah S, Aviv O, Laout N, Ratner S, Beyth N, Domb AJ. Antimicrobial silica particles loaded with quaternary ammonium polyethyleneimine network. *Polym Adv Technol* 2014;25:689–92.
- [333] Makvandi P, Ghaemy M, Ghadiri AA, Mohseni M. Photocurable antimicrobial quaternary ammonium-modified nanosilica. *J Dent Res* 2015;94:1401–7.
- [334] Yu Q, Wu Z, Chen H. Dual-function antibacterial surfaces for biomedical applications. *Acta Biomater* 2015;16:1–13.
- [335] Zhang K, Cheng L, Weir MD, Bai YX, Xu HH. Effects of quaternary ammonium chain length on the antibacterial and remineralizing effects of a calcium phosphate nanocomposite. *Int J Oral Sci* 2016;8:45–53.
- [336] Putsep K, Carlsson G, Boman HG, Andersson M. Deficiency of antibacterial peptides in patients with morbus Kostmann: an observation study. *Lancet* 2002;360:1144–9.
- [337] Zasloff M. Antimicrobial peptides of multicellular organisms. *Nature* 2002;415:389–95.
- [338] Hay DI. Salivary factors in caries models. *Adv Dent Res* 1995;9:239–43.
- [339] Lendenmann U, Grogan J, Oppenheim FG. Saliva and dental pellicle – a review. *Adv Dent Res* 2000;14:22–8.
- [340] Li F, Weir MD, Fouad AF, Xu HH. Effect of salivary pellicle on antibacterial activity of novel antibacterial dental adhesives using a dental plaque microcosm biofilm model. *Dent Mater* 2014;30:182–91.
- [341] Tziafas D, Koliniotou-Koumpia E, Tziafa C, Papadimitriou S. Effects of a new antibacterial adhesive on the repair capacity of the pulp-dentine complex in infected teeth. *Int Endod J* 2007;40:58–66.
- [342] Bjarnsholt T, Alhede M, Alhede M, Eickhardt-Sorensen SR, Moser C, Kühl M, et al. The in vivo biofilm. *Trends Microbiol* 2013;21:466–74.
- [343] Toyofuku M, Inaba T, Kiyokawa T, Obana N, Yawata Y, Nomura N. Environmental factors that shape biofilm formation. *Biosci Biotechnol Biochem* 2015;80:7–12.
- [344] Goo E, An JH, Kang Y, Hwang I. Control of bacterial metabolism by quorum sensing. *Trends Microbiol* 2015;23:567–76.
- [345] Dixon EF, Hall RA. Noisy neighbourhoods: quorum sensing in fungal-polymicrobial infections. *Cell Microbiol* 2015;17:1431–41.
- [346] Metzdorff MT. Evidence-based medicine: what it is, what it isn't, and are we practicing it? *J Trauma Acute Care Surg* 2013;75:927–35.
- [347] Paik S, Sechrist C, Torabinejad M. Levels of evidence for the outcome of endodontic retreatment. *J Endod* 2004;30:745–50.
- [348] Torabinejad M, Kutsenko D, Machnick TK, Ismail A, Newton CW. Levels of evidence for the outcome of nonsurgical endodontic treatment. *J Endod* 2005;31:637–46.
- [349] Tiller JC, Liao CJ, Lewis K, Klibanov AM. V Designing surfaces that kill bacteria on contact. *Proc Natl Acad Sci USA* 2001;98:5981–5.
- [350] Netuschil L, Reich E, Unteregger G, Sculean A, Brex M. A pilot study of confocal laser scanning microscopy for the assessment of undisturbed dental plaque vitality and topography. *Arch Oral Biol* 1998;43:277–85.
- [351] Auschill TM, Arweiler NB, Netuschil L, Brex M, Reich E, Sculean A. Spatial distribution of vital and dead microorganisms in dental biofilms. *Arch Oral Biol* 2001;46:471–6.
- [352] Zhou H, Weir MD, Antonucci JM, Schumacher GE, Zhou XD, Xu HH. Evaluation of three-dimensional biofilms on antibacterial bonding agents containing novel quaternary ammonium methacrylates. *Int J Oral Sci* 2014;6:77–86.
- [353] Zhou H, Liu H, Weir MD, Reynolds MA, Zhang K, Xu HH. Three-dimensional biofilm properties on dental bonding agent with varying quaternary ammonium charge densities. *J Dent* 2016;26:30141–5.
- [354] Bayles KW. Bacterial programmed cell death: making sense of a paradox. *Nat Rev Microbiol* 2014;12:63–9.
- [355] Rice KC, Bayles KW. Molecular control of bacterial death and lysis. *Microbiol Mol Biol Rev* 2008;72:85–109.
- [356] Allocati N, Masulli M, Di Ilio C, De Laurenzi V. Die for the community: an overview of programmed cell death in bacteria. *Cell Death Dis* 2015;6:e1609/1–10.
- [357] Gerdes K, Christensen SK, Løbner-Olesen A. Prokaryotic toxin-antitoxin stress response loci. *Nat Rev Microbiol* 2005;3:371–82.
- [358] Senadheera DB, Cordova M, Ayala EA, Chavez de Paz LE, Singh K, Downey JS, et al. Regulation of bacteriocin production and cell death by the VicRK signaling system in *Streptococcus mutans*. *J Bacteriol* 2012;194:1307–16.
- [359] Zhang C, Cui F, Zeng GM, Jiang M, Yang ZZ, Yu ZG, et al. Quaternary ammonium compounds (QACs): a review on occurrence, fate and toxicity in the environment. *Sci Total Environ* 2015;518–9, 352–62.
- [360] Sandbacka M, Christianson I, Isomaa B. The acute toxicity of surfactants on fish cells, *Daphnia magna* and fish—a comparative study. *Toxicol In Vitro* 2000;14:61–8.
- [361] van Wijk D, Gyimesi-van den Bos M, Garttner-Arends I, Geurts M, Kamstra J, Thomas P. Bioavailability and detoxification of cationics: I. Algal toxicity of alkyltrimethyl ammonium salts in the presence of suspended sediment and humic acid. *Chemosphere* 2009;75:303–9.
- [362] Guohua J, Zuoming Z, Jing Z. Quantitative structure-activity relationship (QSAR) study of toxicity of quaternary ammonium compounds on *Chlorella pyrenoidosa* and *Scenedesmus quadricauda*. *Chemosphere* 2012;86:76–82.

- [363] Liang Z, Ge F, Zeng H, Xu Y, Peng F, Wong M. Influence of cetyltrimethyl ammoniumbromide on nutrient uptake and cell responses of *Chlorella vulgaris*. *Aquat Toxicol* 2013;138–139:81–7.
- [364] Sarkar B, Megharaj M, Shanmuganathan D, Naidu R. Toxicity of organoclays to microbial processes and earthworm survival in soils. *J Hazard Mater* 2013;261:793–800.
- [365] Sarkar B, Megharaj M, Xi Y, Krishnamurti GS, Naidu R. Sorption of quaternary ammonium compounds in soils: implications to the soil microbial activities. *J Hazard Mater* 2010;184:448–56.
- [366] Grabinska-Sota E. Genotoxicity and biodegradation of quaternary ammonium salts in aquatic environments. *J Hazard Mater* 2011;195:182–7.
- [367] Lavorgna M, Russo C, D'Abrosca B, Parrrella A, Isidori M. Toxicity and genotoxicity of the quaternary ammonium compound benzalkonium chloride (BAC) using *Daphnia magna* and *Ceriodaphnia dubia* as model systems. *Environ Pollut* 2016;210:34–9.
- [368] Ferik F, Misik M, Hoelzl C, Uhl M, Fuehracker M, Grillitsch B, et al. Benzalkonium chloride (BAC) and dimethyldioctadecyl-ammonium bromide (DDAB), two common quaternary ammonium compounds, cause genotoxic effects in mammalian and plant cells at environmentally relevant concentrations. *Mutagenesis* 2007;22:363–70.
- [369] Deuschle T, Porkert U, Reiter R, Keck T, Riechelmann H. In vitro genotoxicity and cytotoxicity of benzalkonium chloride. *Toxicol In Vitro* 2006;20:1472–7.
- [370] Melin VE, Potinini H, Hunt P, Griswold J, Siems B, Werre SR, et al. Exposure to common quaternary ammonium disinfectants decreases fertility in mice. *Reprod Toxicol* 2014;50:163–70.
- [371] Melin VE, Melin TE, Dessify BJ, Nguyen CT, Shea CS, Hrubec TC. Quaternary ammonium disinfectants cause subfertility in mice by targeting both male and female reproductive processes. *Reprod Toxicol* 2016;59:159–66.
- [372] Larsen ST, Verder H, Nielsen GD. Airway effects of inhaled quaternary ammonium compounds in mice. *Basic Clin Pharmacol Toxicol* 2012;110:537–43.
- [373] Vieira OV, Hartmann DO, Cardoso CM, Oberdoerfer D, Baptista M, Santos MA, et al. Surfactants as microbicides and contraceptive agents: a systematic in vitro study. *PLoS One* 2008;3, e2913/1–12.
- [374] Inácio AS, Mesquita KA, Baptista M, Ramalho-Santos J, Vaz WL, Vieira OV. In vitro surfactant structure-toxicity relationships: implications for surfactant use in sexually transmitted infection prophylaxis and contraception. *PLoS One* 2011;6:1851–64.
- [375] Debbasch C, Brignole F, Pisella PJ, Warnet JM, Rat P, Baudouin C. Quaternary ammoniums and other preservatives' contribution in oxidative stress and apoptosis on Chang conjunctival cells. *Invest Ophthalmol Vis Sci* 2001;42:642–52.
- [376] Perani A, Gerardin C, Stacey G, Infante MR, Vinardell P, Rodehuser L, et al. Interactions of surfactants with living cells: induction of apoptosis by detergents containing a beta-lactam moiety. *Amino Acids* 2001;21:185–94.
- [377] Green DR, Reed JC. mitochondria and apoptosis. *Science* 1998;281:1309–12.
- [378] Yip KW, Mao X, Au PY, Hedley DW, Chow S, Dalili S, et al. Benzethonium chloride: a novel anticancer agent identified by using a cell-based small-molecule screen. *Clin Cancer Res* 2006;12:5557–69.
- [379] Levine SL, Han Z, Liu J, Farmer DR, Papadopoulos V. Disrupting mitochondrial function with surfactants inhibits MA-10 Leydig cell steroidogenesis. *Cell Biol Toxicol* 2007;23:385–400.
- [380] Inacio AS, Costa GN, Domingues NS, Santos MS, Moreno AJ, Vaz WL, et al. Mitochondrial dysfunction is the focus of quaternary ammonium surfactant toxicity to mammalian epithelial cells. *Antimicrob Agents Chemother* 2013;57:2631–9.
- [381] Gaweda S, Moran MC, Pais AA, Dias RS, Schillen K, Lindman B, et al. Cationic agents for DNA compaction. *J Colloid Interface Sci* 2008;323:75–83.
- [382] Jiao Y, Ma S, Wang Y, Li J, Shan L, Sun J, et al. Methacryloxyethyl cetyl ammonium chloride induces DNA damage and apoptosis in human dental pulp cells via generation of oxidative stress. *Int J Biol Sci* 2016;12:580–93.
- [383] Allison BC, Applegate BM, Youngblood JP. Hemocompatibility of hydrophilic antimicrobial copolymers of alkylated 4-vinylpyridine. *Biomacromolecules* 2007;8:2995–9.
- [384] Sellenet PH, Allison B, Applegate BM, Youngblood JP. Synergistic activity of hydrophilic modification in antibiotic polymers. *Biomacromolecules* 2007;8:19–23.
- [385] Venkataraman S, Zhang Y, Liu L, Yang YY. Design, syntheses and evaluation of hemocompatible pegylated-antimicrobial polymers with well-controlled molecular structures. *Biomaterials* 2010;31:1751–6.
- [386] Feng X, Chen A, Zhang Y, Wang J, Shao L, Wei L. Application of dental nanomaterials: potential toxicity to the central nervous system. *Int J Nanomed* 2015;10:3547–65.
- [387] Nel AE, Madler L, Velegol D, Xia T, Hoek EM, Somasundaran P, et al. Understanding biophysicochemical interactions at the nano-bio interface. *Nat Mater* 2009;8:543–57.
- [388] Laxminarayan R, Duse A, Wattal C, Zaidi AK, Wertheim HF, Sumpradit N, et al. Antibiotic resistance—the need for global solutions. *Lancet Infect Dis* 2013;13:1057–98.
- [389] Centers for Disease Control and Prevention (CDC). Vital signs: carbapenem-resistant enterobacteriaceae. *MMWR Morb Mortal Wkly Rep* 2013;62:165–70.
- [390] Jennings MC, Minbiole KPC, Wuest WM. Quaternary ammonium compounds: an antimicrobial mainstay and platform for innovation to address bacterial resistance. *ACS Infect Dis* 2015;1:288–303.
- [391] McBain AJ, Rickard AH, Gilbert P. Possible implications of biocide accumulation in the environment on the prevalence of bacterial antibiotic resistance. *J Ind Microbiol Biotechnol* 2002;29:326–30.
- [392] Buffet-Bataillon S, Tattevin P, Bonnaure-Mallet M, Jolivet-Gougeon A. Emergence of resistance to antibacterial agents: the role of quaternary ammonium compounds? A critical review. *Int J Antimicrob Agents* 2012;39:381–9.
- [393] Hegstad K, Langsrud S, Lunestad BT, Scheie AA, Sunde M, Yazdankhah SP. Does the wide use of quaternary ammonium compounds enhance the selection and spread of antimicrobial resistance and thus threaten our health. *Microb Drug Resist* 2010;16:91–104.
- [394] Tezel U, Pavlostathis SG. Quaternary ammonium disinfectants: microbial adaptation, degradation and ecology. *Curr Opin Biotechnol* 2015;33:296–304.
- [395] Fox EM, Leonard N, Jordan K. Physiological and transcriptional characterization of persistent and nonpersistent *Listeria monocytogenes* isolates. *Appl Environ Microbiol* 2011;77:6559–69.
- [396] Pagedar A, Singh J, Batish VK. Adaptation to benzalkonium chloride and ciprofloxacin affects biofilm formation potential, efflux pump and haemolysin activity of *Escherichia coli* of dairy origin. *J Dairy Res* 2012;79:383–9.
- [397] Nakamura H, Takakura K, Sone Y, Itano Y, Nishikawa Y. Biofilm formation and resistance to benzalkonium chloride in *Listeria monocytogenes* isolated from a fish processing plant. *J Food Prot* 2013;76:1179–86.
- [398] Stijn VDV, Tjakko A. Importance of SigB for *Listeria monocytogenes* static and continuous-flow biofilm formation and disinfectant resistance. *Appl Environ Microbiol* 2010;76:7854–60.
- [399] van der Veen S, Abee T, HrcA and DnaK are important for static and continuous-flow biofilm formation and disinfectant resistance in *Listeria monocytogenes*. *Microbiology* 2010;156:3782–90.
- [400] Atsushi T, Hideaki N, Takuya M, Keiji M, Yoichiro M, Hiroki K. Correlation between resistance of *Pseudomonas aeruginosa* to quaternary ammonium compounds and expression of outer membrane protein OprR. *Antimicrob Agents Chemother* 2008;47:2093–9.
- [401] Karatzas KA, Randall LP, Webber M, Piddock LJ, Humphrey TJ, Woodward MJ, et al. Phenotypic and proteomic characterization of multiply antibiotic-resistant variants of *Salmonella enterica* serovar Typhimurium selected following exposure to disinfectants. *Appl Environ Microbiol* 2008;74:1508–16.
- [402] Swartjes JJ, Sharma PK, van Kooten TG, van der Mei HC, Mahmoudi M, Busscher HJ, et al. Current developments in antimicrobial surface coatings for biomedical applications. *Curr Med Chem* 2015;22:2116–29.
- [403] Grkovic S, Brown MH, Skurray RA. Regulation of bacterial drug export systems. *Microbiol Mol Biol Rev* 2002;66:671–701.
- [404] Guo W, Cui S, Xu X, Wang H. Resistant mechanism study of benzalkonium chloride selected *Salmonella Typhimurium* mutants. *Microb Drug Resist* 2014;20:11–6.
- [405] Buffet-Bataillon S, Le Jeune A, Le Gall- David S, Bonnaure-Mallet M, Jolivet-Gougeon A. Molecular mechanisms of higher MICs of antibiotics and quaternary ammonium compounds for *Escherichia coli* isolated from bacteraemia. *J Antimicrob Chemother* 2012;67:2837–42.
- [406] He GX, Zhang C, Crow RR, Thorpe C, Chen H, Kumar S, et al. SugE, a new member of the SMR family of transporters, contributes to antimicrobial resistance in *Enterobacter cloacae*. *Antimicrob Agents Chemother* 2011;55:3954–7.
- [407] Braga TM, Marujo PE, Pombo C, Lopes MFS. Involvement, and dissemination, of the enterococcal small multidrug resistance transporter QacZ in resistance to quaternary ammonium compounds. *J Antimicrob Chemother* 2011;66:283–6.
- [408] Turner RJ, Taylor DE, Weiner JH. Expression of *Escherichia coli* TehA gives resistance to antiseptics and disinfectants similar to that conferred by multidrug resistance efflux pumps. *Antimicrob Agents Chemother* 1997;41:440–4.
- [409] Kitagawa H, Izutani N, Kitagawa R, Maezono H, Yamaguchi M, Imazato S. Evolution of resistance to cationic biocides in *Streptococcus mutans* and *Enterococcus faecalis*. *J Dent* 2016;47:18–22.
- [410] Jiao Y, Ma S, Wang Y, Li J, Shan L, Chen J. Epigallocatechin-3-gallate reduces cytotoxic effects caused by dental monomers: a hypothesis. *Medi Sci Monit* 2015;21:3197–202.
- [411] Suzuki T, Motohashi H, Yamamoto M. Toward clinical application of the Keap1-Nrf2 pathway. *Trends Pharmacol Sci* 2013;34:340–6.
- [412] Shi Z, Niu Y, Wang Q, Shi L, Guo H, Liu Y, et al. Reduction of DNA damage induced by titanium dioxide nanoparticles through Nrf2 in vitro and in vivo. *J Hazard Mater* 2015;298:310–9.
- [413] Kang SJ, Ryou IG, Lee YJ, Kwak MK. Role of the Nrf2-heme oxygenase-1 pathway in silver nanoparticle-mediated cytotoxicity. *Toxicol Appl Pharmacol* 2012;258:89–98.
- [414] de Carvalho FG, Puppim-Rontani RM, Soares LE, Santo AM, Martin AA, Nociti-Junior FH. Mineral distribution and CLSM analysis of secondary caries inhibition by fluoride/MDPB-containing adhesive system after cariogenic challenges. *J Dent* 2009;37:307–14.
- [415] Zhang N, Melo MA, Chen C, Liu J, Weir MD, Bai Y, et al. Development of a multifunctional adhesive system for prevention of root caries and secondary caries. *Dent Mater* 2015;31:1119–31.

- [416] Zhang N, Weir MD, Romberg E, Bai Y, Xu HH. Development of novel dental adhesives with double benefits of protein-repellent and antibacterial capabilities. *Dent Mater* 2015;31:845–54.
- [417] Zhang N, Ma J, Melo MA, Weir MD, Bai Y, Xu HH. Protein-repellent and antibacterial dental composite to inhibit biofilms and caries. *J Dent* 2015;43:225–34.
- [418] Marsh P. Controlling the oral biofilm with antimicrobials. *J Dent* 2010;38:S11–5.
- [419] Mauline L, Gressier M, Roques C, Hammer P, Ribeiro SJ, Caiut JM, et al. Bifunctional silica nanoparticles for the exploration of biofilms of *Pseudomonas aeruginosa*. *Biofouling* 2013;29:775–88.
- [420] Hidalgo G, Burns A, Herz E, Hay AG, Houston PL, Wiesner U, et al. Functional tomographic fluorescence imaging of pH microenvironments in microbial biofilms by use of silica nanoparticle sensors. *Appl Environ Microbiol* 2009;75:7426–35.